

Manuscript Number: MOLCAA-D-09-00378R1

Title: Ruthenium containing hydrotalcite as a solid base catalyst for >C=C< double bond isomerization in perfumery chemicals

Article Type: Full Length Article

Section/Category: Heterogeneous catalysis

Keywords: Methyl chavicol; Anethole; Eugenol; Hydrotalcite; Solid base catalyst

Corresponding Author: Dr. Raksh V Jasra,

Corresponding Author's Institution: CSMCRI

First Author: Sumeet K Sharma

Order of Authors: Sumeet K Sharma; Parimal A Parikh; Raksh V Jasra

Abstract: Ruthenium containing hydrotalcite (Ru-Mg-Al) is used as a solid base catalyst for >C=C< double bond isomerization in methyl chavicol, eugenol, safrole, allylbenzene, dimethoxy allylbenzene and 3-carene. The catalyst showed excellent conversion and selectivity for isomerization reaction in shorter reaction time (2 h). Catalytic activity and reusability of Ru-Mg-Al was compared with ruthenium impregnated catalysts such as, Ru-HT, Ru-MgO, Ru-CaO, Ru-SiO₂ and Ru-alumina for isomerization of methyl chavicol to trans-anethole. Ru-Mg-Al catalyst was reused four times without loss in its activity, however, significant loss in the conversion of methyl chavicol and selectivity of trans-anethole was observed on reusability of other ruthenium impregnated catalysts. The conversion of methyl chavicol and selectivity of trans-anethole was found to increase on increasing the reaction temperature as well as amount of catalyst. At 0.005 g catalyst amount, 55% conversion of methyl chavicol with 68% selectivity of trans-anethole was observed that increased to 93% with 82% selectivity of trans-anethole at 0.05 g catalyst amount. On further increased in the amount of catalyst to 1 g, conversion increased to 98% with 88% selectivity of trans-anethole.

Graphical Abstract

Ruthenium containing hydrotalcite as a solid base catalyst for >C=C< double bond isomerization of perfumery chemicals


Ruthenium containing hydrotalcite (Ru–Mg–Al) is reported as a solid base catalyst for double bond isomerization of methyl chavicol, eugenol, safrole, allylbenzene, dimethoxy allylbenzene and 3-carene. The activity of Ru–Mg–Al was compared with the various ruthenium impregnated catalysts such as, Ru–HT, Ru–MgO, Ru–CaO, Ru–SiO₂ and Ru–alumina.

Sumeet K Sharma^{a,b}, Parimal A Parikh^b and Raksh V Jasra^{a*,#}

^a Discipline of Inorganic Materials & Catalysis, Central Salt and Marine Chemicals Research Institute (CSMCRI), G.B. Marg, Bhavnagar – 364 002, Gujarat, India.

^b Department of Chemical Engineering, SV National Institute of Technology, Surat 395 007 Gujarat, India.

[#] Present address – R&D Centre, VMD, Reliance Industries Limited, Vadodara, 391 346, Gujarat, India.

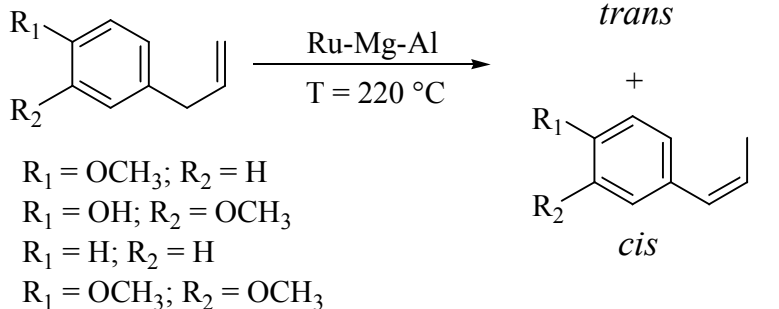

October 05, 2009

Dr. R.V. Jasra
Head, R&D
Reliance Industries Limited
VMD, Vadodara-391 346, Gujarat (India)

To,

Professor Abdelhamid Sayari
Editor
Journal of Molecular Catalysis A: Chemical

Sub.: Submission of a revised manuscript with response to the reviewer's comments

Ms. Ref. No. - MOLCAA-D-09-00378

Title - Ruthenium containing hydrotalcite as a solid base catalyst for $>C=C<$ double bond isomerization in perfumery chemicals

Dear Prof. Sayari

We have considered all suggestions of the referees in the revised manuscript and manuscript has been modified accordingly. The details of point-by-point reply to reviewers' comments and necessary modifications carried out are given on next page.

The revised manuscript is submitted for your kind perusal. We hope that the manuscript is now in acceptable format.

With regards

R.V. Jasra

Reply to Reviewers' comments

Ms. Ref. No.: MOLCAA-D-09-00378

Title: Ruthenium containing hydrotalcite as a solid base catalyst for >C=C< double bond isomerization in perfumery chemicals

Reviewer #1:

Comment 1

The catalytic activity of ruthenium-containing hydrotalcite is higher than that of the parent hydrotalcite in the isomerization of methyl chavicol to trans-anethole (Table 2). However, there is no discussion about the role of ruthenium in the isomerization. It is essential to do so.

Reply

The role of the ruthenium in the isomerisation is described on **page 10, lines 19 to page 11 Lines 2** as well as **page 14, lines 21 to page 15 lines 6** as shown below:

page 10, lines 19 to page 11 Lines 2

“The ruthenium metal complexes in homogeneous condition are well documented in the literature for isomerization of olefinic double bond [6]. The higher activity of Ru–Mg–Al catalyst as compared to HT(3.5) is due to presence of ruthenium in the brucite layer via isomorphic substitution of Mg or Al cations at the octahedral which is expected to be responsible for double bond isomerization reaction. Most of the active sites (hydroxyl groups coordinated to the ruthenium cations) are located at the outer surface of Ru–Mg–Al catalyst that makes it as an active and reusable catalyst.”

page 14, lines 21 to page 15 lines 6 as –

“The effect of ruthenium content on catalytic activity of Ru–Mg–Al for double bond isomerization of methyl chavicol was evaluated by varying the ruthenium content from 0.3 to 10% (by wt). At lower ruthenium loading (0.3%), 61% conversion of methyl chavicol was obtained which

increased to 98% on increasing the amount of ruthenium to 1.0% in Ru–Mg–Al catalyst (Table 5). The conversion of methyl chavicol increased to 100% on increase in the ruthenium loading to 1.5%. The selectivity of trans-anethole was not observed to change significantly upto 1.5% ruthenium content in Ru–Mg–Al catalyst, however, selectivity of trans-anethole decreased significantly to 80% on increasing the ruthenium content to 5% which further decreased to 73% at 10% ruthenium content in Ru–Mg–Al catalyst. The decrease in the selectivity of trans-anethole at higher ruthenium content in catalyst is due to the formation of other side products.”

Comment 2

I recommend that the authors discuss the effect of the solid supports on the reusability of the catalysts.

Reply

Discussion about the effect of solid supports on the reusability of the catalysts has been added in the revised manuscript on **page 12, Lines 12-16** as -

“Except Ru-CaO, no significant effect of solid supports was observed on the conversion of methyl chavicol and selectivity of trans-anethole for isomerization of methyl chavicol. However, leaching of ruthenium from the solid supports has significant effect on the catalytic activity and reusability of ruthenium impregnated catalysts. Lower activity of Ru-CaO may be due to the lower surface area of catalyst.”

Ruthenium containing hydrotalcite as a solid base catalyst for >C=C< double bond isomerization in perfumery chemicals

Sumeet K Sharma^{a,b}, Parimal A Parikh^b and Raksh V Jasra^{a*}

^a *Discipline of Inorganic Materials & Catalysis, Central Salt and Marine Chemicals
Research Institute (CSIR), G.B. Marg, Bhavnagar – 364 002, Gujarat, India.*

^b *Department of Chemical Engineering, SV National Institute of Technology, Surat 395 007
Gujarat, India.*

Abstract

Ruthenium containing hydrotalcite (Ru–Mg–Al) is used as a solid base catalyst for >C=C< double bond isomerization in methyl chavicol, eugenol, safrole, allylbenzene, dimethoxy allylbenzene and 3-carene. The catalyst showed excellent conversion and selectivity for isomerization reaction in shorter reaction time (2 h). Catalytic activity and reusability of Ru–Mg–Al was compared with ruthenium impregnated catalysts such as, Ru–HT, Ru–MgO, Ru–CaO, Ru–SiO₂ and Ru–alumina for isomerization of methyl chavicol to *trans*-anethole. Ru–Mg–Al catalyst was reused four times without loss in its activity, however, significant loss in the conversion of methyl chavicol and selectivity of *trans*-anethole was observed on reusability of other ruthenium impregnated catalysts. The conversion of methyl chavicol and selectivity of *trans*-anethole was found to increase on increasing the reaction temperature as well as amount of catalyst. At 0.005 g catalyst amount, 55% conversion of methyl chavicol with 68% selectivity of *trans*-anethole was observed that increased to 93% with 82% selectivity of *trans*-anethole at 0.05 g catalyst amount. On further increased in the amount of catalyst to 1 g, conversion increased to 98% with 88% selectivity of *trans*-anethole.

Keywords: Methyl chavicol; Anethole; Eugenol; Hydrotalcite; Solid base catalyst

* *Present address of Corresponding author:* R&D Centre, VMD, Reliance Industries Limited, Vadodara, 391 346, Gujarat, India. Tel: +91–265–6696313; Fax: +91–265–6693934 e-mail: rakshvir.jasra@ril.com (Raksh V Jasra)

1. Introduction

$>C=C<$ double bond isomerization reaction is of great interest because of its potential commercial applications for the synthesis of fine and perfumery chemicals [1]. For example, *trans*-anethole is a valuable perfumery chemical [2, 3] and intermediate for the synthesis of other chemicals. Synthetically, *trans*-anethole is produced via double bond isomerization of methyl chavicol [4] using strong liquid base like potassium hydroxide and sodium hydroxide in stoichiometric amounts. Highest conversion of methyl chavicol (56%) with 82:18 *trans* to *cis* anethole ratio has been reported in 12 h at 200 °C [4]. However, this method suffers from drawbacks like, post synthesis work-up to separate spent KOH or NaOH from reactant/product mixture, use of solvent, longer reaction time and lower conversion. Therefore, it is desirable to develop an environmentally benign catalytic process for the solvent free synthesis of *trans*-anethole *via* double bond isomerization of methyl chavicol in a shorter reaction time.

In our earlier reports, transition metal complexes of rhodium, ruthenium and palladium were demonstrated as potential catalysts for double bond isomerization of methyl chavicol to *trans*-anethole and eugenol to *trans*-isoeugenol in homogeneous reaction conditions [5, 6]. In another study, hydrotalcite, ion exchanged zeolites were used as catalysts for isomerization of methyl chavicol in 10 h reaction time [7]. Kishore et al., studied the catalytic activity of as-synthesized hydrotalcite of varied divalent and trivalent metals and their ratios for isomerization of eugenol [8], safrole [9-10], estragole [11] in various polar and non polar organic solvents. In another study, hydrotalcite of different composition and varied divalent to trivalent cations ratio were used as catalysts for the isomerization of methyl chavicol and eugenol in the presence of dimethyl formamide (DMF) as a solvent [8, 11]. Conversion of eugenol was achieved upto 75% with 85% selectivity of *trans*-isoeugenol in 6 h at substrate to catalyst ratio 2:1. The main drawbacks of these studies are the use of DMF as

a solvent, very low substrate to catalyst ratio, non-reusability of catalyst and lower conversion using impregnated catalyst.

Hydrotalcite or layered double hydroxides (HT; $[M(II)_{1-x}M(III)_x(OH_2)]^{x+}(CO_3^{2-})_{x/n} \cdot mH_2O$; where M(II) = Mg or divalent cation and M(III) = Al or trivalent cation) is an attractive catalyst due to the availability of wide variety of basicity which can be achieved by proper tuning of the M(II) and M(III) molar ratio, intercalation of suitable anion in the interlayer space or activation of hydrotalcite at 450 °C. Various metals can be introduced into the brucite layer via isomorphic substitution of M(II) or M(III) cations at the octahedral sites, which are expected to be the active sites for organic transformations [12-13]. Ruthenium incorporated hydrotalcite samples are reported to be highly active catalyst for oxidation of alcohols and aromatic compounds [14], direct alkylation of nitriles with primary alcohols [15] and for the one-pot synthesis of quinolines [16]. Apart from these applications, the literature is silent on the potential of ruthenium containing hydrotalcite as a catalyst for various organic transformations.

The present manuscript describes the use of ruthenium containing hydrotalcite (Ru–Mg–Al) as a reusable eco-friendly catalyst for solvent free double bond isomerization in perfumery chemicals such as methyl chavicol, eugenol, safrole, allylbenzene, dimethoxy allylbenzene and 3-carene (Scheme 1).

2. Experimental

2.1. Materials

Magnesium chloride [$MgCl_2 \cdot 6H_2O$; 98%], aluminum chloride [$AlCl_3 \cdot 9H_2O$; 98%], sodium carbonate [Na_2CO_3 ; 99.9%], sodium hydroxide [NaOH; 99.9%], silica [SiO_2 ; surface area = 200 m²/g], CaO [surface area = 92 m²/g], MgO [surface area = 130 m²/g] and alumina [Al_2O_3 ; surface area = 192 m²/g] were purchased from s. d. Fine Chemicals Ltd., Mumbai,

India and used as such received. Ruthenium trichloride $[\text{RuCl}_3 \cdot x\text{H}_2\text{O}]$, methyl chavicol, eugenol, safrole, allylbenzene, 3-carene, dimethoxy allylbenzene and tetradecane (98%) were procured from Sigma Aldrich, USA and used without further purification. The double distilled milli-pore deionized water was used for the synthesis of catalysts.

2.2. Catalyst preparation

2.2.1. Synthesis of ruthenium hydrotalcite $[\text{Ru-Mg-Al}]$

Ruthenium grafted hydrotalcite was prepared by co-precipitation method at a constant pH [12]. In a typical synthesis procedure, an aqueous solution (A) containing $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ (0.0522 mol), $\text{AlCl}_3 \cdot \text{H}_2\text{O}$ (0.0144 mol) and $\text{RuCl}_3 \cdot x\text{H}_2\text{O}$ (0.5 mmol) in 50 mL double distilled deionized water was prepared. The solution A was added drop wise into a second solution (B) containing Na_2CO_3 (0.079 mol) in 50 mL double distilled de-ionized water, in around 45 min under vigorous stirring at 30 °C. Constant pH of the mixture was maintained by adding 1 M NaOH solution. Content was then transferred into the teflon coated stainless steel autoclave and aged at 80 °C for 16 h under autogenous water vapor pressure. After 16 h, the precipitate formed was filtered and washed thoroughly with hot distilled water until the filtrate was free from Cl^- ions as tested by silver nitrate solution. The obtained filter cake was dried in an oven at 80 °C for 14 h. The solid material (yield = 5.1 g) named as Ru-Mg-Al, was ground and stored under vacuum. The activation of Ru-Mg-Al was carried out in a muffle furnace at 450 °C for 4 h. Synthesis of Mg-Al hydrotalcite sample with Mg/Al molar ratio of 3.5 [HT(3.5)] was done as per the above mentioned procedure without use of $\text{RuCl}_3 \cdot x\text{H}_2\text{O}$ solution.

2.2.2. Synthesis of ruthenium impregnated catalysts

Impregnation of ruthenium (Ru) metal on solid base supports namely HT(3.5), MgO, CaO, alumina, SiO_2 was carried out to compare the catalytic activity of Ru-impregnated

catalysts with Ru–Mg–Al by the following procedure. An aqueous solution of $\text{RuCl}_3 \cdot x\text{H}_2\text{O}$ (0.5 mmol) in 40 mL deionized double distilled water was added dropwise to the suspension of 5.1 g of respective solid support in 40 mL water under N_2 atmosphere. The mixture was vigorously stirred for 16 h at 30 °C. The slurry was filtered and washed with hot distilled water until the filtrate was free from Cl^- ions (silver nitrate test). Then the filter cake was dried at 80 °C for 14 h.

2.3. Characterization of catalysts

Powder X-ray diffraction (P-XRD) patterns of synthesized catalysts were recorded on a Philips X'Pert MPD system equipped with XRK 900 reaction chamber, using Ni-filtered $\text{Cu-K}\alpha$ radiation ($\lambda = 1.54056 \text{ \AA}$) over a 2θ range of 5–70°. Operating voltage and current were kept at 40 kV and 40 mA, respectively. The percentage crystallinity of HT(3.5) and Ru–Mg–Al were calculated by the summation of integral intensities of diffraction peaks corresponding to (003) and (006) planes. The values of unit cell parameters (a and c) of HT(3.5) and Ru–Mg–Al samples were calculated by the formula; $a = 2(d_{110})$ and $c = 3(d_{003})$; where d_{110} and d_{003} are the basal spacing values of (110) and (003) planes respectively [17].

Fourier transform infra-red (FT-IR) spectra of synthesized catalysts were recorded with a Perkin-Elmer Spectrum GX FT-IR spectrometer in the region of 400 to 4000 cm^{-1} using KBr pellets. Thermogravimetric analysis (TGA) of HT(3.5) and Ru–Mg–Al samples were carried out using a Mettler Toledo TGA/SDTA 851e equipment in nitrogen flow (flow rate = 50 mL/min) at a heating rate of 10 °C/min and the data were processed using star^e software. Surface area of synthesized catalysts was measured using ASAP 2010 Micromeritics, USA. The samples were activated at 120 °C for 4 h under vacuum (5×10^{-2} mmHg) prior to N_2 adsorption measurements. The specific surface area of the samples was calculated from N_2 adsorption isotherms measured at 77.4 K as per Brunauer, Emmett, Teller

(BET) method. Chemical analyses of the catalysts were carried out using Inductive Coupled Plasma (ICP) Spectrometer, Perkin Elmer, Optima 2000 instrument.

2.4. Isomerization reaction and products analysis

For the double bend isomerization reactions, calculated amount of reactant and catalyst were taken with 0.01 g tetradecane (used as an internal GC standard) in a 25 mL double necked round bottom flask. One neck of the flask was fitted with refluxing condenser and another neck of the flask was blocked with silicon rubber septa. The flask was kept in an oil bath equipped with temperature and agitation speed controllers and the reaction was carried out under nitrogen atmosphere. The analysis of product mixture was carried out by gas chromatography (GC; Shimadzu 17A, Japan), having 5% diphenyl and 95% dimethyl siloxane universal capillary column (60 m length and 0.25 mm diameter) and flame ionization detector (FID). The initial column temperature was increased from of 100 to 220 °C at the rate of 10 °C/min using nitrogen as a carrier gas. The temperature of injection port and FID were kept 250 and 300 °C, respectively, during the analysis of product mixture. The retention times for each compound were determined by injecting pure compound under identical GC conditions.

Experiments were repeated under identical reaction conditions to ensure the reproducibility of the reaction. Conversion and selectivity data were found to be reproducible within $\pm 2\%$ variation. For kinetic studies, samples (0.1 mL) were taken out during the course of experiment using glass syringe at different time intervals. For reusability of the catalysts, spent catalyst was washed with methanol to remove adsorbed reactant/products from the surface of catalysts. After that the catalyst was dried for 10 h at 100 °C and re-used for isomerization reaction.

3. Results and Discussion

3.1. Characterization of catalyst

The sharp and symmetric reflections of (003) and (006) planes at low values of 2θ angles ($11\text{--}23^\circ$) and broad, asymmetric reflections at higher 2θ angles ($34\text{--}66^\circ$) were observed in the P-XRD patterns of HT(3.5) and Ru-Mg-Al samples (Fig. 1). These reflections at respective 2θ angles are typical characteristics of the hydrotalcite and revealed a good dispersion of aluminum and ruthenium in the brucite layers [18]. The P-XRD pattern of Ru-Mg-Al sample shows that the characteristic original planes of HT(3.5) are retained after incorporation of ruthenium in the brucite sheet. Presence of CO_3^{2-} anions in the interlayer space of HT(3.5) and Ru-Mg-Al samples was confirmed by the characteristic basal spacing of (003) plane; $d_{003} = 7.65\text{\AA}$. Any additional peaks corresponding to other crystalline phases were not observed in the P-XRD pattern of Ru-Mg-Al. The intensities of (003) and (006) planes, which are directly related to the crystallinity were observed to decrease to 88% for Ru-Mg-Al sample as compared to pristine HT(3.5) (Table 1). Decrease in the crystallinity on introducing the ruthenium cations in hydrotalcite structure (Ru-Mg-Al) could be attributed to the increase in the number of cations of higher ionic radii in brucite sheet. Increase in the value of a was also observed for Ru-Mg-Al sample (3.069\AA) as compared to pristine hydrotalcite (3.064\AA) due to larger ionic radii of ruthenium (0.68\AA) as compared to aluminum (0.53\AA). Decrease in the value of unit cell parameter c was observed for Ru-Mg-Al sample (23.38\AA) as compared to the value for HT(3.5) (23.41\AA). This results into decrease in charge density on layers due to weaker interaction (or decrease in Coulombic attractive force) between the negatively charged interlayer anions and positively charged brucite like layers [12, 16, 18]. P-XRD patterns of Ru-HT(3.5), Ru-MgO, Ru-CaO, Ru-alumina and Ru-SiO₂ were observed similar to their pristine counterparts (Fig. 1; Supporting Information).

FT-IR spectra of HT(3.5) and Ru-Mg-Al samples (Fig. 2) showed all the characteristic peaks of hydrotalcite structure [18, 19]. The peak at around 3450–3480 cm^{-1} is due to the ν_{OH} mode of H-bonded hydroxyl groups in the layers and broadening of this peak is dependent on the strength of hydroxyl bonds. Shoulder present at 3000 cm^{-1} is attributed to the hydrogen bonding of hydroxyl groups of layered lattice and/or water molecules with interlayer carbonate anions [18]. Band that appeared at around 1640 cm^{-1} is due to the deformation mode of interlayer water molecules. Intensity of this band suggests the content of water molecules in the material. The sharp, intense vibrational band at around 1370 cm^{-1} is assigned to the asymmetric ν_3 mode of interlayer carbonate anions and absence of the band at around 1050 cm^{-1} suggests the retention of D_{3h} symmetry of carbonate anions in the interlayer space. The bands in low frequency region (below 1000 cm^{-1}) are related with Mg-OH, Al-OH and Ru-OH vibrational modes in brucite-type layers. The bands at 950 cm^{-1} for the deformation of Al-OH and at 780 cm^{-1} for Al-OH translation were also observed. The peak at around 660 cm^{-1} (ν_4) is attributed to the in-plane carbonate bending. The band at 560 cm^{-1} is assigned to the translation modes of hydroxyl groups, influenced by Al^{3+} cations (Mg/Al-OH translation) [20]. The presence of band at 418 cm^{-1} is attributed to the Mg-OH vibrational mode.

Thermogravimetric analysis (TGA) curves of HT(3.5) and Ru-Mg-Al shown in Fig. 3 reveal two stage weight loss accompanied by endothermic transformations. TGA curves of HT(3.5) and Ru-Mg-Al samples showed similar weight loss patterns. The 13% weight loss was observed in the Ru-Mg-Al sample at first stage (180–200 °C) which is attributed to the loss of physically adsorbed water molecules with relatively smaller amounts of condensed water molecules and CO_2 . The 26 % weight loss in second stage (300–450 °C) was observed due to removal of condensed water molecules and carbon dioxide from the carbonate anion present in the interlayer space of Ru-Mg-Al. During this temperature range, interlayer

carbonate anions were thermally oxidized by a nearby interlayer water molecule to produce volatile CO₂ and interlayer hydroxyl anions. Observed lower weight loss in the Ru–Mg–Al sample as compared to HT(3.5) is due to the presence of ruthenium cations in the matrix of brucite sheet which led to higher thermal stability of the catalyst. Ruthenium content in the Ru–Mg–Al hydrotalcite sample was calculated by ICP and EDX analysis. The percentage ruthenium content in the Ru–Mg–Al hydrotalcite sample was found to be 1.0% (by wt).

BET surface area of HT(3.5) and Ru–Mg–Al samples was found to be 76 and 80 m²/g, respectively (Table 1). Increase in the surface area for ruthenium containing hydrotalcite sample is attributed to the observed decrease in the crystallinity as compared to [HT(3.5)] sample which is also seen from P–XRD patterns. Surface area of other ruthenium impregnated samples, Ru-HT, Ru-alumina, Ru-MgO, Ru-SiO₂, Ru-CaO was found to be 82, 161, 92, 172, 80 m²/g, respectively. The catalytic activity of Ru–Mg–Al was investigated for double bond isomerization of methyl chavicol to anethole, a base catalyzed reaction, by varying the amount of catalyst and reaction temperature.

3.2. Catalytic activity of Ru–Mg–Al for double bond isomerization of methyl chavicol

Catalytic activity of Ru–Mg–Al was evaluated for the isomerization of methyl chavicol to *trans*-anethole and the corresponding data on methyl chavicol conversion and *trans*-anethole selectivity are shown in Fig. 4. Conversion of methyl chavicol and selectivity of *trans*-anethole was observed to increase with increase in the amount of catalyst upto 0.1 g. On further increase in the amount of catalyst, no significant effect on conversion and selectivity of *trans*-anethole was observed. Therefore, 0.1 g catalyst amount was chosen as an optimum catalyst amount for further study. Lower catalytic activity at low catalyst amount is due to the unavailability of sufficient active sites for isomerization reaction. As the amount of catalyst increased, availability of the active sites for double bond isomerization increases

significantly. Therefore, higher conversion of methyl chavicol was observed on increasing the amount of catalyst. No conversion of methyl chavicol was observed in the absence of the catalyst.

The conversion of methyl chavicol was found to increase on increasing the reaction temperature (Fig. 5). At 100 °C, only 41% conversion of methyl chavicol was observed, which increased to 98% on increasing the reaction temperature to 210 °C. At lower temperature (100 °C), 74% selectivity of *trans* isomer was observed that increased to 88% at 210 °C.

3.3. Catalytic activity and reusability of various ruthenium impregnated catalysts

The catalytic activity and reusability of Ru–Mg–Al was compared with ruthenium impregnated catalysts namely, hydrotalcite [Ru–HT(3.5)], magnesium oxide (Ru–MgO), calcium oxide (Ru–CaO), silica (Ru–SiO₂) and alumina (Ru–Al₂O₃) (Table 2) by keeping similar ruthenium content at optimum reaction conditions. Pristine hydrotalcite, magnesium oxide, calcium oxide, silica and alumina were also used as catalysts to observe the role of ruthenium on their catalytic activity. Ruthenium incorporated in the brucite layer (Ru–Mg–Al) catalyst gave 98% conversion of methyl chavicol with 88% selectivity of *trans*-anethole within 2 h reaction time. Conversion and selectivity data for isomerization of methyl chavicol were observed to remain unchanged even after fourth run, confirming that the catalyst is reusable for the isomerization reaction without loss in its activity. The ruthenium metal complexes in homogeneous condition are well documented in the literature for isomerization of olefinic double bond [6]. The higher activity of Ru–Mg–Al catalyst as compared to HT(3.5) is due to presence of ruthenium in the brucite layer via isomorphous substitution of Mg or Al cations at the octahedral which is expected to be responsible for double bond isomerization reaction. Most of the active sites (hydroxyl groups coordinated to the

ruthenium cations) are located at the outer surface of Ru–Mg–Al catalyst that makes it as an active and reusable catalyst. Another reason for higher activity of Ru–Mg–Al catalyst is the increased surface area of Ru–Mg–Al sample which favors the enhanced catalytic activity of the material as compared to the pristine hydrotalcite. No significant leaching of the ruthenium metal from the Ru-Mg-Al catalyst was observed in the ICP analysis of filtrate, due to the strong coordination of ruthenium cations in the hydrotalcite matrix as well as to the hydroxyl groups.

Ru–HT(3.5) showed comparable results, i.e. 97% conversion of methyl chavicol and 87% selectivity of *trans*–anethole, to the Ru–Mg–Al catalyst. However, conversion and selectivity were observed to decrease on reusability of the catalyst for the isomerization of methyl chavicol. For example, the conversion of methyl chavicol decreased from 97 to 88% with 76% selectivity for *trans*–anethole at the end of fourth cycle. Decrease in the conversion and selectivity is attributed to the leaching of ruthenium cations as 6% leaching was confirmed by ICP analysis from the surface of impregnated catalyst [Ru–HT(3.5)] during the catalytic reaction. 20% conversion of methyl chavicol was achieved with 80% selectivity of *trans*–anethole in 2 h using pristine hydrotalcite of Mg/Al molar ratio (3.5) [HT(3.5)] as a catalyst. On reuse of the catalyst, only 4% conversion of methyl chavicol was observed, which shows that the [HT(3.5)] is not a reusable catalyst in the present study for double bond isomerization reaction. On impregnation of ruthenium on MgO, the conversion of methyl chavicol increased from 24% (using pristine MgO as a catalyst) to 97% with 85% selectivity of *trans* isomer. The activity of Ru–MgO was observed to decrease on reusability experiments. At the end of fourth cycle, conversion of methyl chavicol decreased to 84% with 71% selectivity of *trans*–anethole. Among all ruthenium impregnated catalysts, Ru–CaO showed lower conversion of methyl chavicol (62%) with higher selectivity of *trans*–anethole (90%). The conversion was found to decrease very rapidly on the reusability experiments.

Only 3% conversion of methyl chavicol was achieved at the end of fourth cycle, which is lower than the conversion observed by the use of pristine CaO as a catalyst (15%). Rapid decrease in the conversion and selectivity data is due to the faster leaching of ruthenium metal. ICP analysis of Ru–CaO shows that the 86% of ruthenium was leached out from the catalyst after third cycle. Ruthenium impregnated silica and alumina also gave similar conversion of methyl chavicol (98%). However, higher selectivity of *trans*-anethole was observed with Ru–alumina (84%) as compared to Ru–SiO₂ (79%). On reusability of catalyst, rapid decrease in the conversion and selectivity was observed for Ru–SiO₂ as compared to Ru–alumina. The lower conversions of methyl chavicol, i.e. 5 and 10% were found when pristine SiO₂ and alumina, respectively, were used as catalysts. From the above data, Ru–Mg–Al was observed as a reusable catalyst for the double bond isomerization of methyl chavicol to *trans*-anethole. Except Ru–CaO, no significant effect of solid supports was observed on the conversion of methyl chavicol and selectivity of *trans*-anethole for isomerization of methyl chavicol. However, leaching of ruthenium from the solid supports has significant effect on the catalytic activity and reusability of ruthenium impregnated catalysts. Lower activity of Ru–CaO may be due to the lower surface area of catalyst.

3.4. Kinetic study for isomerization of methyl chavicol at optimum reaction conditions

For the kinetic study, reaction was carried out by taking 10 g methyl chavicol with 1 g Ru–Mg–Al as a catalyst at 210 °C reaction temperature. The kinetic profile for conversion of methyl chavicol and formation of *cis*- and *trans*-anethole with respect to time is shown in Fig. 6. 60% conversion of methyl chavicol was achieved within 2 min of reaction time that was observed to increase to 95% in 10 min. Most of the methyl chavicol was consumed for the formation of thermodynamically stable *trans*-anethole, however, small amount of *cis*-anethole was also observed at beginning of the reaction. As the reaction proceeded, formation of *cis*-anethole was also observed to increase. Initial rate of reaction for consumption of

methyl chavicol was found to be $0.0026 \text{ mol.g}_{\text{cat}}^{-1}.\text{min}^{-1}$ in the conversion range upto 25%. The initial rate of reaction for the formation of *cis*- and *trans*-anethole was calculated as 0.0003 and $0.0023 \text{ mol.g}_{\text{cat}}^{-1}.\text{min}^{-1}$, respectively. The higher initial rate of reaction shows that the formation of *trans*-isomer is more favorable in the present reaction conditions as compared to *cis*-isomer.

3.5. Isomerization of other perfumery chemicals using Ru–Mg–Al as a catalyst

In view of observed higher catalytic activity and reusability of Ru–Mg–Al sample for isomerization of methyl chavicol, double bond isomerization in other perfumery compounds such as, eugenol, allylbenzene, dimethoxy allylbenzene, safrole, 3-carene was studied using Ru–Mg–Al as a catalyst. 98% conversion of methyl chavicol with 88% selectivity of *trans*-anethole was observed within 2 h reaction time (Table 3). Double bond isomerization of eugenol showed 94% conversion of eugenol with 89% selectivity of *trans*-isoeugenol. Lower conversion of eugenol as compared to methyl chavicol could be attributed to the higher boiling point and viscosity of the reactant. The allylbenzene isomerization showed 96% conversion with 88% selectivity for *trans* isomer. In case of isomerization of dimethoxy allylbenzene, 92% conversion was observed. For isomerization of safrole, 97% conversion with 89% selectivity of *trans*-isosafrole was achieved. The data presented in this study for solvent free catalytic isomerization of safrole and eugenol is comparable with the results reported by Kishore et al., using hydrotalcite as a catalyst (substrate to catalyst ratio 2:1) in the presence of solvent, DMSO [9]. 88% conversion of 3-carene with 72% selectivity of 2-carene was observed using Ru–Mg–Al as a catalyst for isomerization of 3-carene. These data indicates that the Ru–Mg–Al is a highly active and reusable catalyst for double bond isomerization of variety of substrates related to the fine and perfumery chemicals.

3.6. Effect of activation of catalysts on their activity for isomerization of methyl chavicol

The catalytic activity of Ru–Mg–Al and pristine hydrotalcite of varied Mg/Al molar ratio was observed to decrease on activation at 450 °C for 4 h (Table 4). For example, conversion of methyl chavicol and selectivity of *trans*–anethole were observed to decrease from 98 to 48% and 88 to 80%, respectively, on activation of Ru–Mg–Al catalyst. With pristine hydrotalcite, the conversion of methyl chavicol was observed to increase on increasing the Mg/Al molar ratio of activated hydrotalcite from 2.0 to 3.5. For activated hydrotalcite of Mg/Al molar ratio 2.0, 8% conversion of methyl chavicol was observed with 70% selectivity of *trans*–anethole in 10 h reaction time. The conversion increased to 20% with 80% selectivity of *trans*–anethole using activated hydrotalcite of Mg/Al molar ratio 3.5 as a catalyst. The conversion of methyl chavicol is achieved even in longer reaction time (10 h) when pristine hydrotalcite was used as a catalyst as compared to the Ru–Mg–Al (2 h) for double bond isomerization of methyl chavicol. As–synthesized hydrotalcite of varied Mg/Al molar ratio showed higher conversion and selectivity of *trans* isomer as compared to activated hydrotalcite as a catalyst. These results confirmed that the hydroxyl groups present in the hydrotalcite are playing an important role for the relocation of double bond. When the catalyst was calcined at 450 °C, the material converted into mixed oxides phase of higher surface area and strong basic in nature (rich in Lewis basic sites) as compared to the as–synthesized hydrotalcite (Brønsted basic sites) [21]. In case of hydrotalcite based catalysts, the observed results in the present study clearly showed that the catalyst having strong (Lewis) basic sites is less active as compared to the catalyst rich in Brønsted basic sites (as–synthesized hydrotalcite).

The effect of ruthenium content on catalytic activity of Ru–Mg–Al for double bond isomerization of methyl chavicol was evaluated by varying the ruthenium content from 0.3 to 10% (by wt). At lower ruthenium loading (0.3%), 61% conversion of methyl chavicol was obtained which increased to 98% on increasing the amount of ruthenium to 1.0% in Ru–Mg–

Al catalyst (Table 5). The conversion of methyl chavicol increased to 100% on increase in the ruthenium loading to 1.5%. The selectivity of *trans*-anethole was not observed to change significantly upto 1.5% ruthenium content in Ru-Mg-Al catalyst, however, selectivity of *trans*-anethole decreased significantly to 80% on increasing the ruthenium content to 5% which further decreased to 73% at 10% ruthenium content in Ru-Mg-Al catalyst. The decrease in the selectivity of *trans*-anethole at higher ruthenium content in catalyst is due to the formation of other side products.

4. Conclusions

Ruthenium incorporated hydrotalcite (Ru-Mg-Al) was used as a catalyst for the isomerization of methyl chavicol, eugenol, safrole, allylbenzene, dimethoxy allylbenzene and 3-carene. Ru-Mg-Al showed excellent catalytic activity for isomerization reaction in shorter reaction time. For example, 98% conversion of methyl chavicol with 88% selectivity of *trans*-anethole was observed in 2 h reaction time. The activity of Ru-Mg-Al was compared with the other ruthenium impregnated catalysts such as, Ru-HT, Ru-MgO, Ru-CaO, Ru-SiO₂ and Ru-alumina. Ru-Mg-Al catalyst was recycled upto fourth cycles without significant loss in its activity. Other ruthenium impregnated catalyst also showed comparable activity but significant loss in the catalytic activity was observed on reuse of the catalysts for isomerization of methyl chavicol. Reaction temperature was observed to have a significant effect on conversion and selectivity of *trans*-isomer. Conversion of methyl chavicol increased from 41 to 98% and selectivity of *trans*-anethole increased from 74 to 88% on increasing the temperature from 100 to 210 °C using Ru-Mg-Al as a catalyst. Kinetic study at optimum reaction conditions showed that 95% conversion of methyl chavicol was achieved within 10 min reaction time. The initial rate of reaction was calculated from the kinetic profile and found to be 0.0026 mol.g_{cat}⁻¹.min⁻¹.

Acknowledgements

SKS thanks to Council of Scientific and Industrial Research (CSIR), New Delhi, India for the award of a Senior Research Fellowship.

References

- [1]. J.D. Atwood, Mechanism of Inorganic and Organometallic Reactions, Brooks/Cole, California, (1985); P.N Rylander, Organic Synthesis with Nobel Metal Catalysts; Academic Press: New York, (1973).
- [2]. International Flavors & Fragrances Inc., New Release, New York, January 28, (2004); K. Bauer, D. Garbe, H. Surberg, Ullmann Encyclopedia of Industrial Chemistry, Electronic Release, 6th ed., (2002).
- [3]. P. Gandilhon, US Patent, 4138 411 (1979).
- [4]. A.P. Wagner, Manuf. Chemist 23 (1952) 56–60.
- [5]. S.K. Sharma, V.K. Srivastava, R.V. Jasra, J. Mol. Catal. A: Chem. 245 (2006) 200–209.
- [6]. S.K. Sharma, V.K. Srivastava, P.H. Pandya, R.V. Jasra, Catal. Commun. 6 (2005) 205–209; P.N Rylander, Organic Synthesis with Nobel Metal Catalysts, Academic Press, New York, 1973.
- [7]. V.K. Srivastava, H.C. Bajaj, R.V. Jasra, Catal. Commun. 4 (2003) 543–548.
- [8]. D. Kishore, S. Kannan, Appl. Catal. A: Gen. 270 (2004) 227–235.
- [9]. D. Kishore, S. Kannan, J. Mol. Catal. A: Chem. 223 (2004) 225–230.
- [10]. D. Kishore, S. Kannan, Green Chem. 4 (2002) 607–610.
- [11]. D. Kishore, S. Kannan, J. Mol. Catal. A: Chem. 244 (2006) 83–92.
- [12]. F. Basile, L. Basini, G. Fornasari, M. Gazzano, F. Trifiro, A. Vaccari, Chem. Commun. (1996) 2435–2436.

- [13]. K. Kaneda, T. Yamashita, T. Matsushita, K. Ebitani, *J. Org. Chem.* 63 (1998) 1750–1751.
- [14]. T. Matsushita, K. Ebitani and K. Kaneda, *Chem. Commun.* (1999) 265–266.
- [15]. K. Motokura, D. Nishimura, K. Mori, T. Mizugaki, K. Ebitani and K. Kaneda, *J. Am. Chem. Soc.* 126 (2004) 5662–5663.
- [16]. F. Basile, G. Fornasari, M. Gazzano, A. Vaccari, *J. Mater. Chem.* 12 (2002) 3296–3303.
- [17]. Y. Zhao, F. Li, R. Zhang, D.G. Evans, X. Duan, *Chem. Matter.* 14 (2002) 4286–4291.
- [18]. F. Cavani, F. Trifiro, A. Vaccari, *Catal. Today* 11 (1991) 173–301.
- [19]. N. Kuznik, O.F. Wendt, *J. Chem Soc. Dalton Trans.* (2002) 3074–3078.
- [20]. S. Abello, F. Medina, D. Tichit, J.P. Ramirez, J.C. Groen, J.E. Sueiras, P. Salagre, Y. Cesteros, *Chem. Eur. J.* 11 (2005) 728–739.
- [21]. S.K Sharma, P.A Parikh, R.V Jasra, *J. Mol. Catal. A Chem.* 286 (2008) 55–62; S.K Sharma, P.A Parikh, R.V Jasra, *J. Mol. Catal. A: Chem.* 278 (2007) 135–144.

List of Figure Captions -

Fig. 1. P-XRD patterns of HT(3.5) and Ru-Mg-Al samples

Fig. 2. FT-IR spectra of HT(3.5) and Ru-Mg-Al samples

Fig. 3. TGA of HT(3.5) and Ru-Mg-Al samples

Fig. 4. Catalytic activity of Ru-Mg-Al sample for isomerization of methyl chavicol to trans-anethole at varied amount of catalyst

Fig. 5. Effect of reaction temperature on conversion of methyl chavicol and selectivity of trans-anethole using Ru-Mg-Al as a catalyst

Fig. 6. Progress of double bond isomerization of methyl chavicol to anethole with respect to time using Ru-Mg-Al as a catalyst

Scheme Captions-

Scheme 1. Double bond isomerization of methyl chavicol

Table 1

Physical characterization of the catalysts

	HT(3.5)	Ru-Mg-Al
Crystallinity, %	100	88
Unit cell parameter (a), Å	3.064	3.069
Unit cell parameter (c), Å	23.41	23.38
W ₁ , %; (T ₁ , °C)	8; (80–160)	13; (180–220)
W ₂ , %; (T ₂ , °C)	36; (300–550)	26; (320–450)
Surface area, m ² /g	76	80

Table 2

Conversion and selectivity data of various ruthenium containing catalysts for isomerization of methyl chavicol to anethole

Catalyst	Cycle	% Conversion	% Selectivity ^a	
			<i>trans</i> -Anethole	<i>cis</i> -Anethole
Ru-Mg-Al	first	98	88	12
	second	98	88	12
	third	98	88	12
	fourth	97	87	13
Ru-HT(3.5)	first	97	87	13
	second	95	85	15
	third	92	81	19
	fourth	88	76	24
HT(3.5)	first	20	80	20
	second	4	81	19
Ru-MgO	first	97	85	15
	second	97	82	18
	third	89	78	22
	fourth	84	71	29
MgO	first	24	72	28
	second	6	70	30
Ru-CaO	first	62	90	10
	second	15	87	13
	third	7	85	15

	fourth	3	84	16
CaO	first	15	75	25
	second	2	65	35
Ru-SiO ₂	first	98	79	21
	second	85	73	27
	third	77	62	38
	fourth	70	59	41
SiO ₂	first	5	45	55
	second	–	–	–
Ru-Alumina	first	98	84	16
	second	94	80	20
	third	90	77	23
	fourth	87	73	27
Alumina	first	10	72	28
	second	2	–	–

^a **Reaction conditions:** methyl chavicol = 5.0 g, catalyst = 0.5 g, temperature = 210 °C, reaction time = 2 h

Table 3

Conversion and selectivity data for double bond isomerization of various chemicals with Ru–Mg–Al as a catalyst

Run	Reactant	% Conversion ^a	% Selectivity	
			<i>trans</i> -isomer	<i>cis</i> -isomer
1	Methyl chavicol	98	88	12
2	Eugenol	94	89	11
3	Allylbenzene	96	88	12
4	Dimethoxy allylbenzene	92	88	12
5	Safrole	97	89	11
6	3-Carene	88	72	-

^a **Reaction conditions:** reactant = 5.0 g, catalyst = 0.5 g, temperature = 210 °C, reaction time = 2 h.

Table 4

Isomerization of methyl chavicol to anethole using thermally activated catalysts *

Run	Reactant	Catalyst	% Conversion ^a	% Selectivity		T, h
				<i>trans</i> -isomer	<i>cis</i> -isomer	
1	Methyl chavicol	Ru-Mg-Al	48	80	20	2
2	Eugenol	Ru-Mg-Al	41	81	19	2
3	Safrole	Ru-Mg-Al	43	77	23	2
4	Allylbenzene	Ru-Mg-Al	40	79	21	2
5	3-Carene	Ru-Mg-Al	38	70	30	2
6	Methyl chavicol	HT (3.5)	20	80	20	10
7	Methyl chavicol	HT (3.0)	16	78	22	10
8	Methyl chavicol	HT (2.5)	14	74	26	10
9	Methyl chavicol	HT (2.0)	8	70	30	10

^a **Reaction conditions:** reactant = 5.0 g, catalyst = 0.5 g, temperature = 210 °C, reaction time = 2 h.

*Activated at 450 °C for 4 h

Table 5

Effect of ruthenium content on catalytic activity of Ru–Mg–Al for double bond isomerization of methyl chavicol

Run	% (wt) Ruthenium content in Ru-Mg-Al	% Conversion ^a	% Selectivity	
			<i>trans</i> -isomer	<i>cis</i> -isomer
1	0.3	61	89	11
2	0.5	79	89	11
3	1.0	98	88	12
4	1.5	100	88	12
5	5	100	80	14
7	10	100	73	17

^a **Reaction conditions:** reactant = 5.0 g, Ru–Mg–Al = 0.5 g, temperature = 210 °C, reaction

time = 2 h.

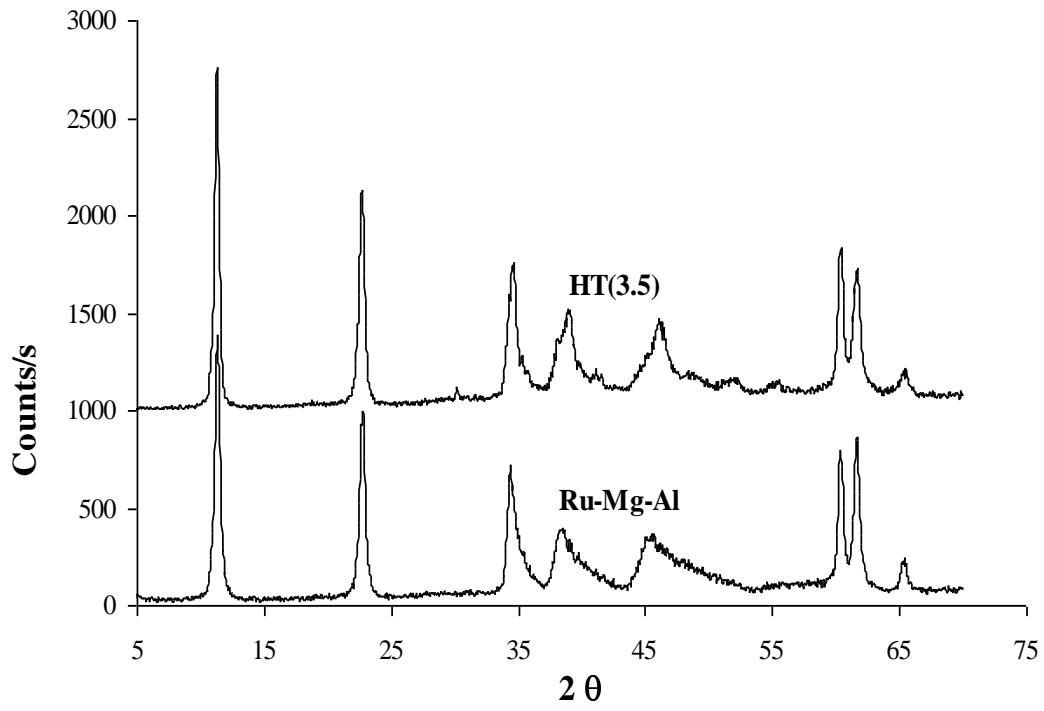


Fig. 1. P-XRD patterns of HT(3.5) and Ru-Mg-Al samples

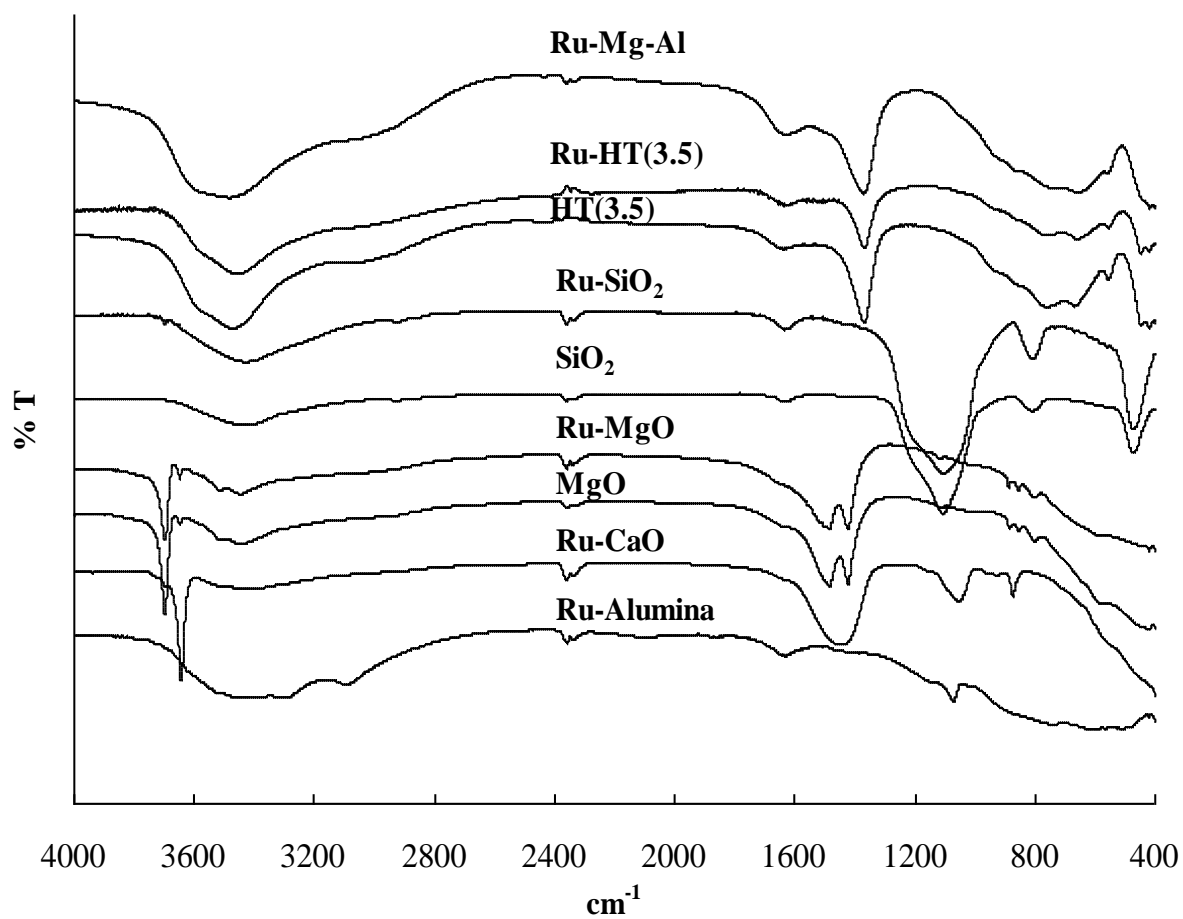


Fig. 2. FT-IR spectra of studied catalysts

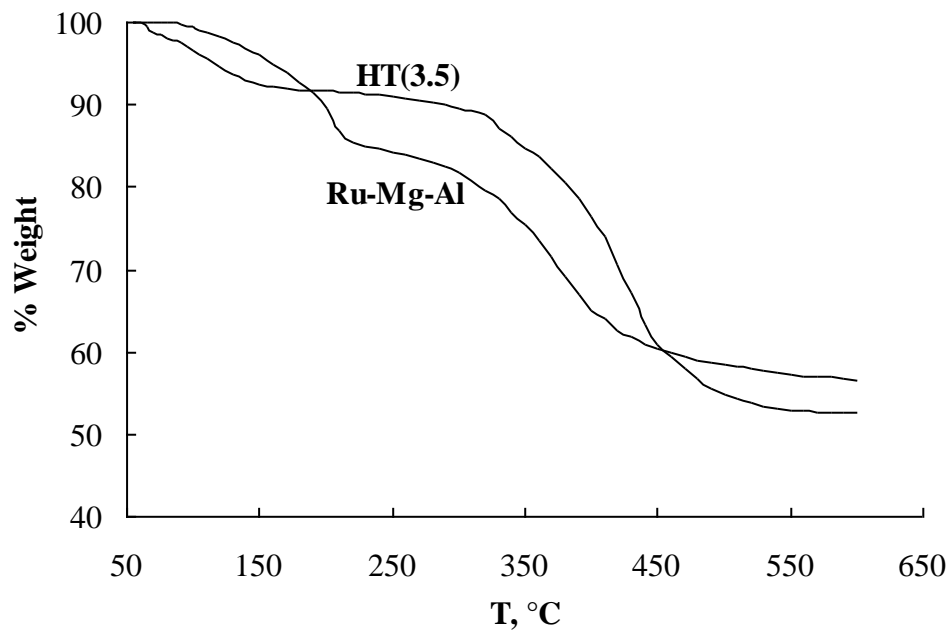


Fig. 3. TGA of HT(3.5) and Ru-Mg-Al samples

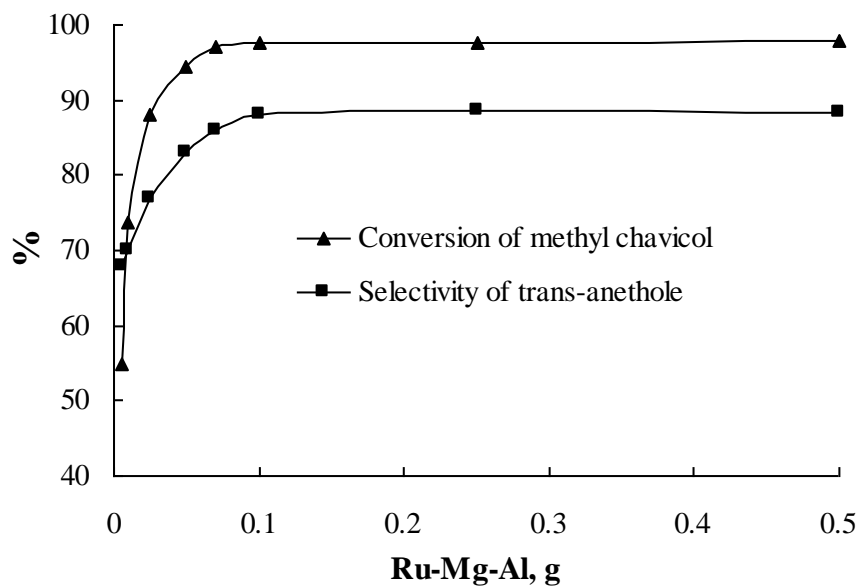


Fig. 4. Catalytic activity of Ru-Mg-Al sample for isomerization of methyl chavicol to *trans*-anethole at varied amount of catalyst

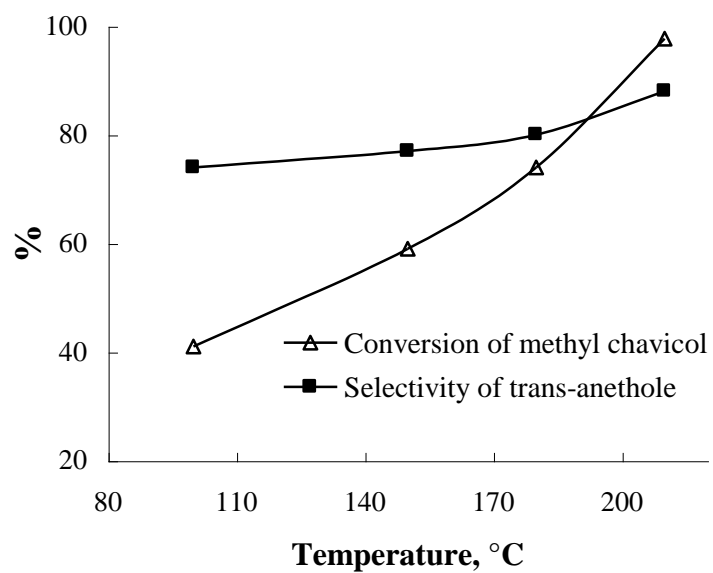


Fig. 5. Effect of reaction temperature on conversion of methyl chavicol and selectivity of *trans*-anethole using Ru-Mg-Al as a catalyst



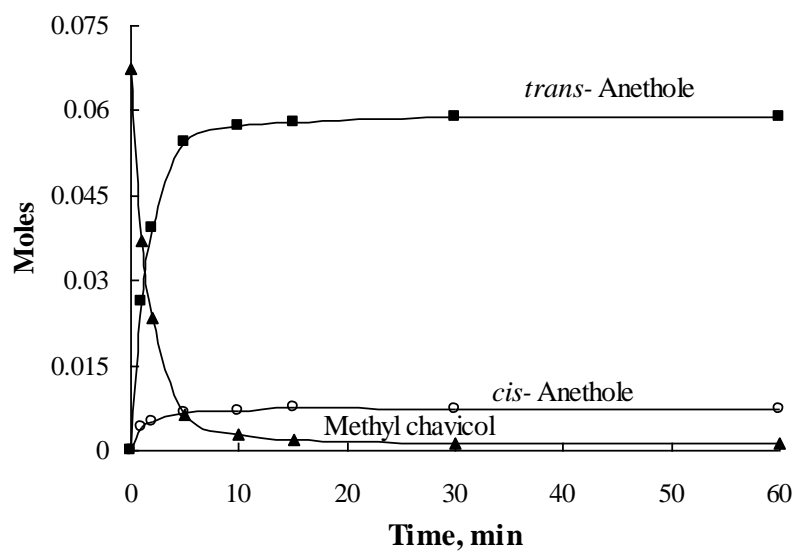



Fig. 6. Progress of double bond isomerization of methyl chavicol to anethole with respect to time using Ru–Mg–Al as a catalyst

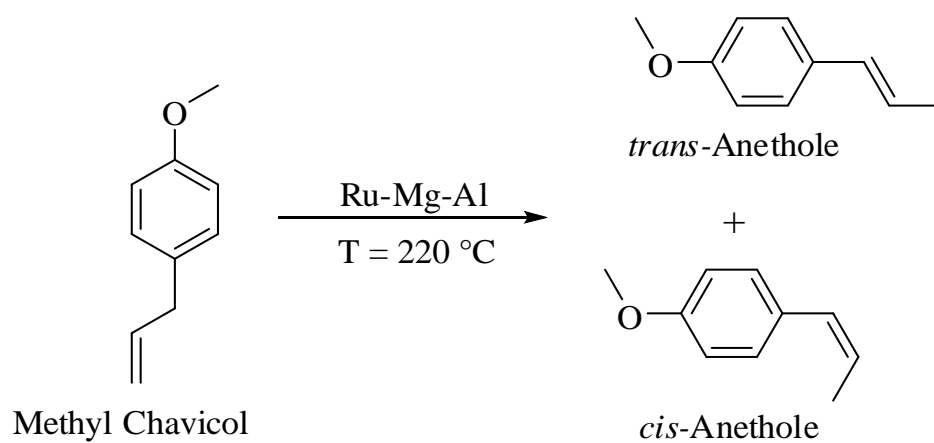


Scheme 1. Double bond isomerization of methyl chavicol

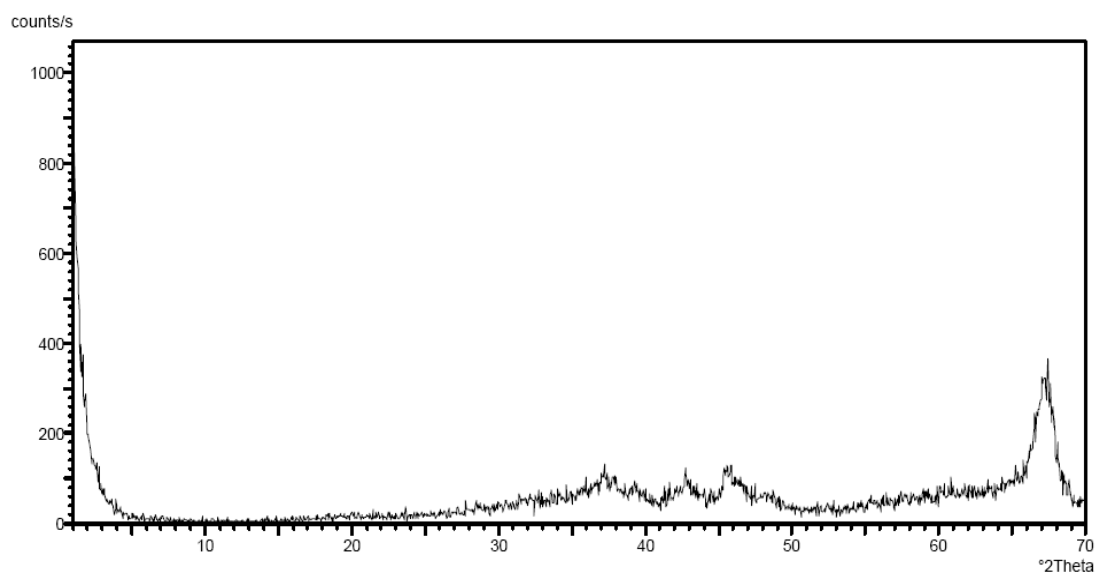


P-XRD pattern of Ru-Alumina

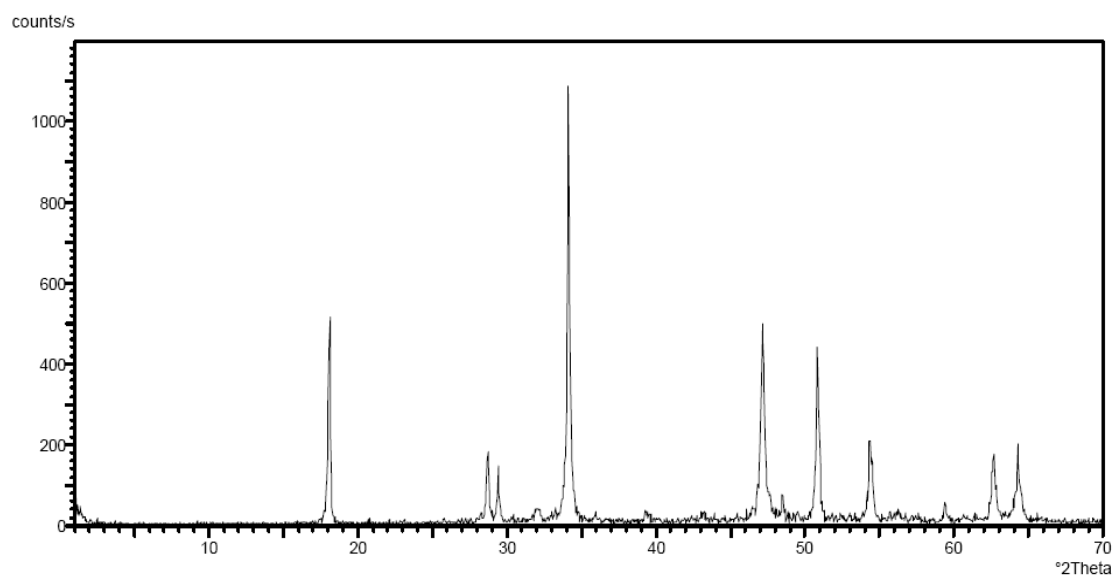


P-XRD pattern of Ru-CaO

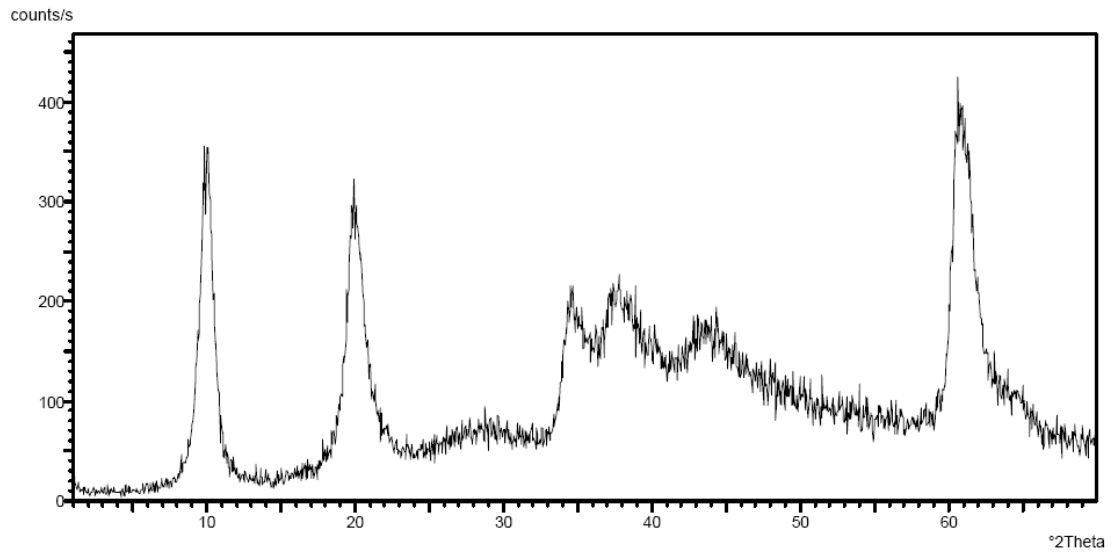

P-XRD pattern of Ru-HT

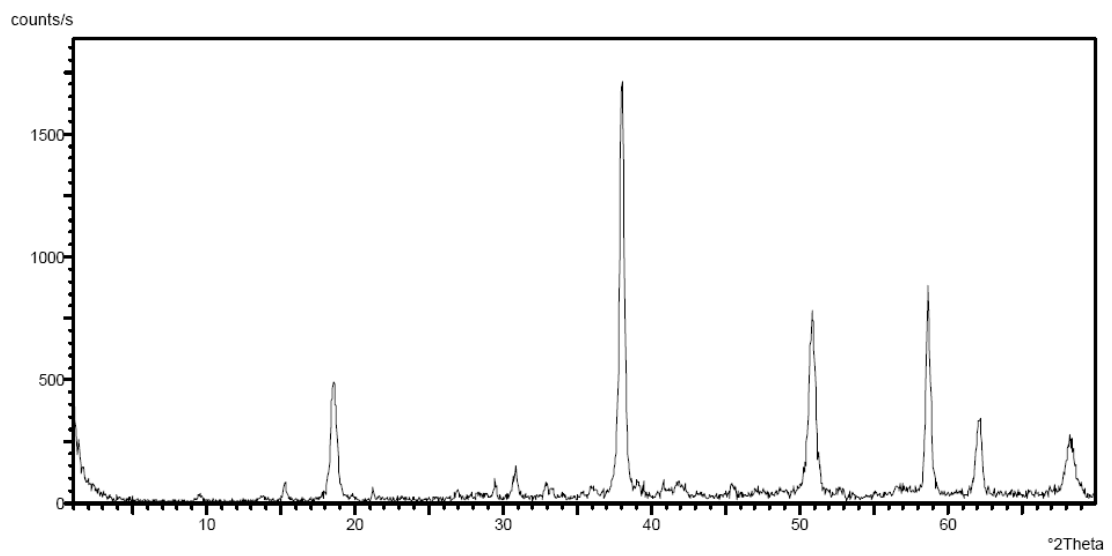

P-XRD pattern of Ru-MgO

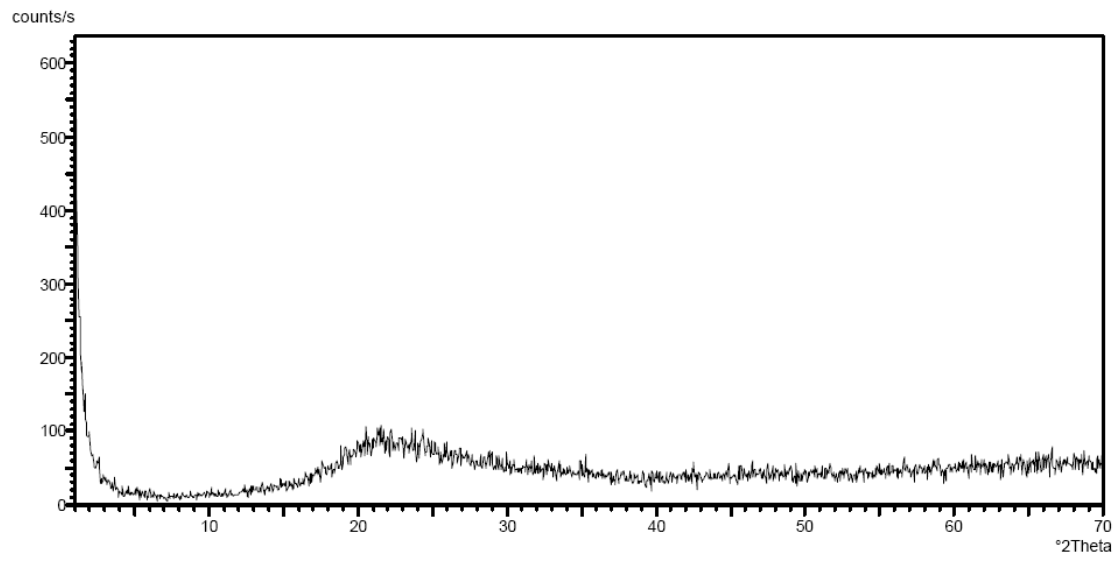

P-XRD pattern of Ru-SiO₂