



Catalyst Preparation

FHI-AC Lecture Series on Heterogeneous Catalysis

Malte Behrens

Fritz Haber Institute, Inorganic Chemistry Department
behrens@fhi-berlin.mpg.de

Catalyst preparation

- Target configuration (active sites) often unknown
- Material and pressure gap in heterogeneous catalysis
- High surface area material are desired (“porous” / “nano”)
- Defects play a role
- Homogeneity is an issue

- Mostly empirical (trial & error) optimization
- Application requires reproducibility, scalability and economic / environmental feasibility

Progress of catalyst synthesis

Table 1.2 Survey of selected catalysts with their main applications.

Catalyst	Applications
Ni/SiO ₂	Hydrogenation
K ₂ O/Al ₂ O ₃ /Fe	Ammonia synthesis
Ag/ α -Al ₂ O ₃	Epoxidation
CrO _x /SiO ₂	Polymerization
CoMoS ₂ / γ -Al ₂ O ₃	Hydrotreating
Co/SiO ₂	Fischer-Tropsch synthesis
Cu/ZnO/Al ₂ O ₃	Methanol synthesis
Zeolite Y composite	Catalytic cracking
Pt/Mordenite	Hydroisomerization of light alkanes
V ₂ O ₅ /TiO ₂	NO _x abatement
Pt/C	Hydrogenation; fuel cell

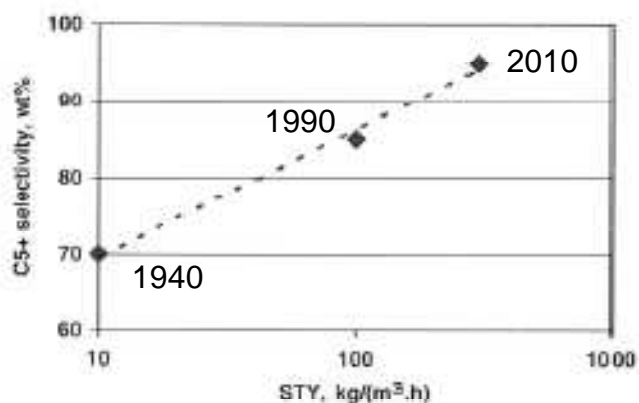


Figure 1.1 Development of cobalt-based Fischer-Tropsch synthesis in terms of both activity (STY = space time yield) and selectivity to hydrocarbons of five or more C-atoms. Data from 1940 to 2010 with data points from left to right at years 1940, 1990, and 2010, respectively.


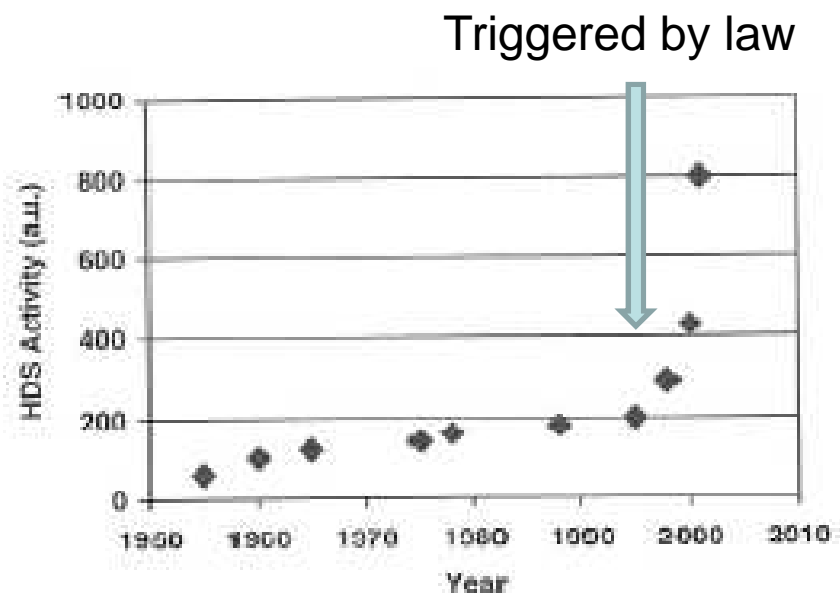



Figure 1.2 Development of hydrodesulfurization (HDS) catalyst activity over the years [8].

Krijn P. de Jong (ed): Synthesis of solid catalysts, Wiley 2009

Catalyst Microstructures

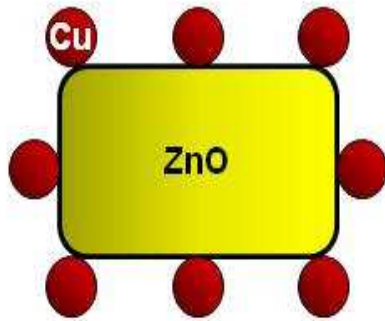

a) Supported catalyst

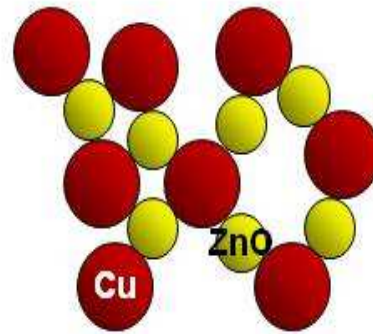

b) Porous bulk catalyst



c) Skeletal catalyst



Distribute a liquid precursor *uniformly* on a pre-formed support




Form active phase and stabilizer by thermal treatment of a *homogeneous* solid precursor



Leach pores into a previously *homogenous* alloy

Aspects of solid state chemistry

- Reactivity of solids is limited by slow diffusion processes: Increase in temperature required for solid-solid reactions ($T > 600^\circ\text{C}$)
 - Formation of thermodynamically stable compounds of high density (low porosity), high crystallographic symmetry and low variation in building blocks
 - High temperatures favour sintering
- Catalyst preparation procedures avoid high temperatures
 - Homogeneous distribution achieved by other measures than diffusion
 - Liquid phases involved
 - Catalysts are meta-stable systems

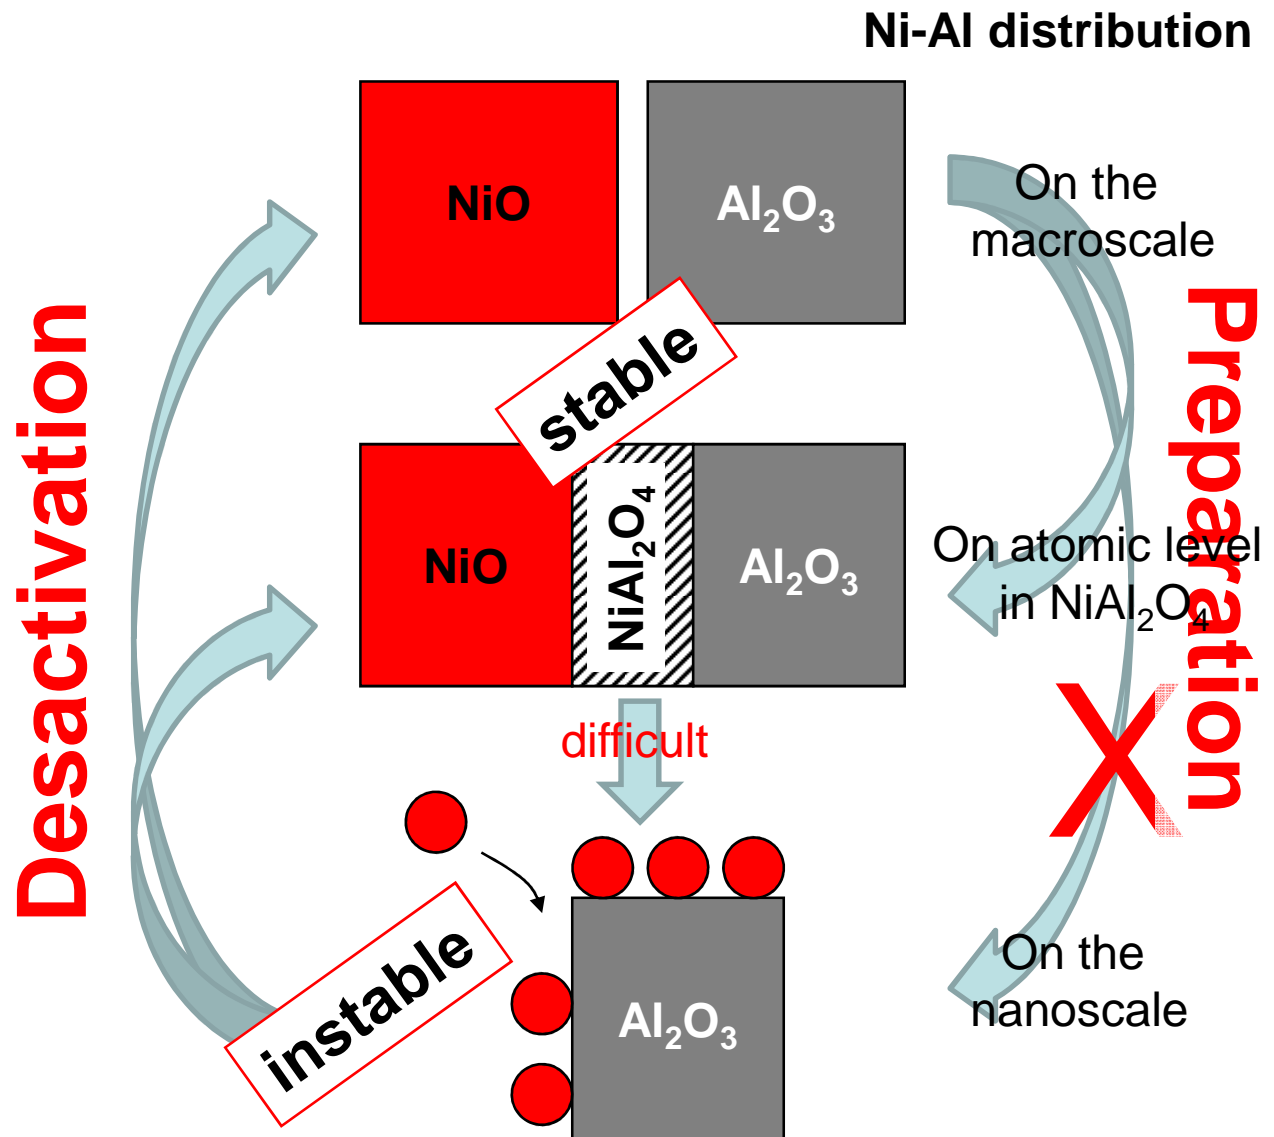


Outline


- Impregnation
 - Support materials
 - Key experimental parameters
 - Example: 3-way catalyst
- Co-precipitation
 - Precursor chemistry
 - Example: Methanol synthesis catalyst
- Skeletal catalysts
 - Leaching of alloys
 - Example: Raney nickel
- Hydrothermal synthesis
 - Principles of hydrothermal synthesis
 - Example: Zeolites
- Summary

Impregnation: Role of supports

- Why (most) catalysts need to be supported: Sintering
- Support:
 - carries the active components
 - provides surface area (porosity)
 - keeps high dispersion of active component
 - is thermostable and chemically inert (?)
- Maximum active surface area of the active component desired
 - per unit weight (expensive precious metals, typical loading ~ 1 wt.-%)
 - per unit volume (base metals, oxides, typical loadings ~20 wt.-%)

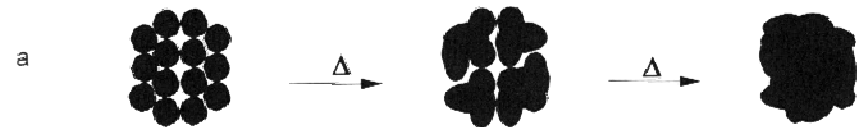

Supported Precious Metal Catalyst

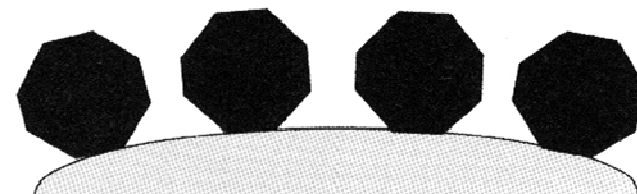

Supported Base Metal Catalyst

Preparation of supported catalysts

- Deposition of a precursor of the active phase onto the surface of the support
 - At the solid-liquid (wet) interface
 - Impregnation
 - Deposition precipitation
 - At the solid-gas (dry) interface
 - Vapor deposition
- Transformation of the precursor into the active phase


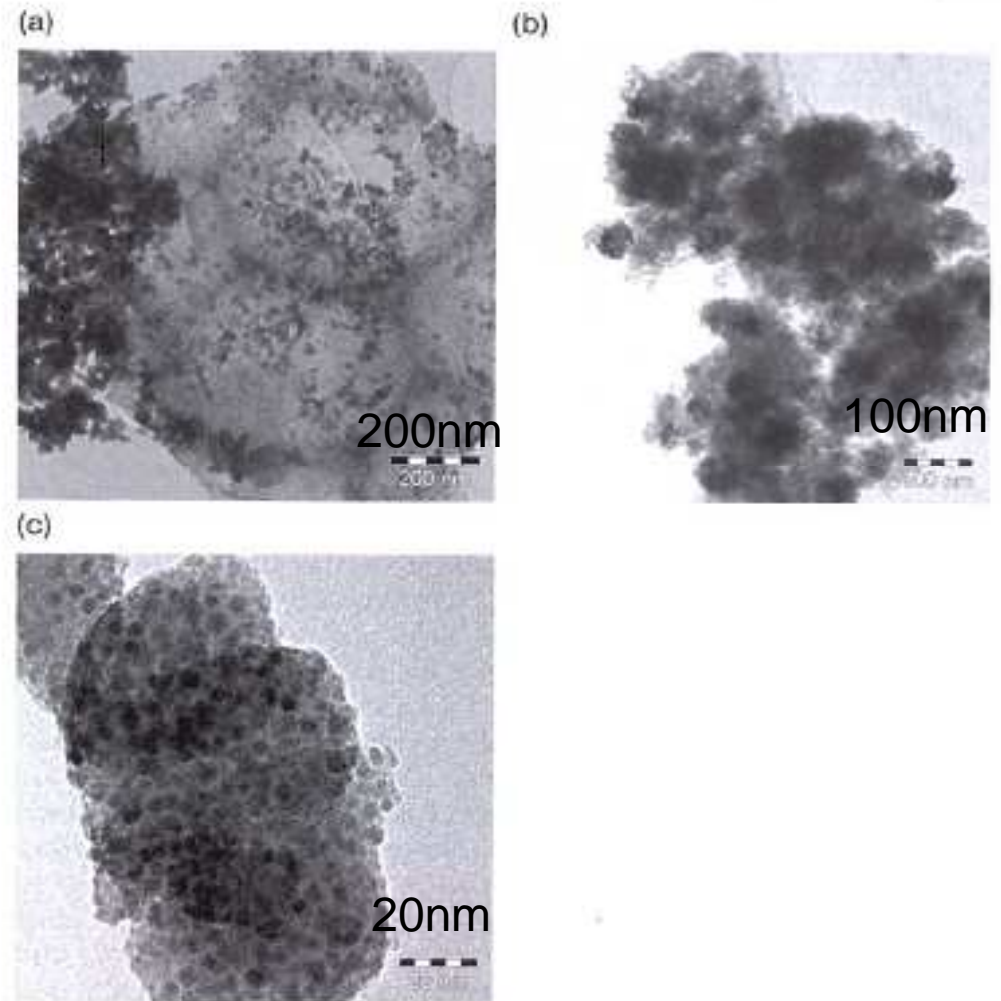


Figure 1.5 Three generations of silica-supported cobalt catalyst. (a) 50 wt% Co/kieselguhr prepared by precipitation; (b) 18 wt% Co on silica gel obtained by

calcination in air flow; and (c) 18 wt% Co on silica gel obtained by calcination in NO/He flow.



Typical supports

- Alumina
 - mostly γ -phase
 - SA up to $400 \text{ m}^2\text{g}^{-1}$
- Silica
 - amorphous
 - SA up to $1000 \text{ m}^2\text{g}^{-1}$
- Carbon
 - amorphous, unstable in oxidative environment
 - SA up to $1000 \text{ m}^2\text{g}^{-1}$
- Zeolites / ordered mesoporous materials
 - highly defined pore system
- also: TiO_2 , MgO , ...


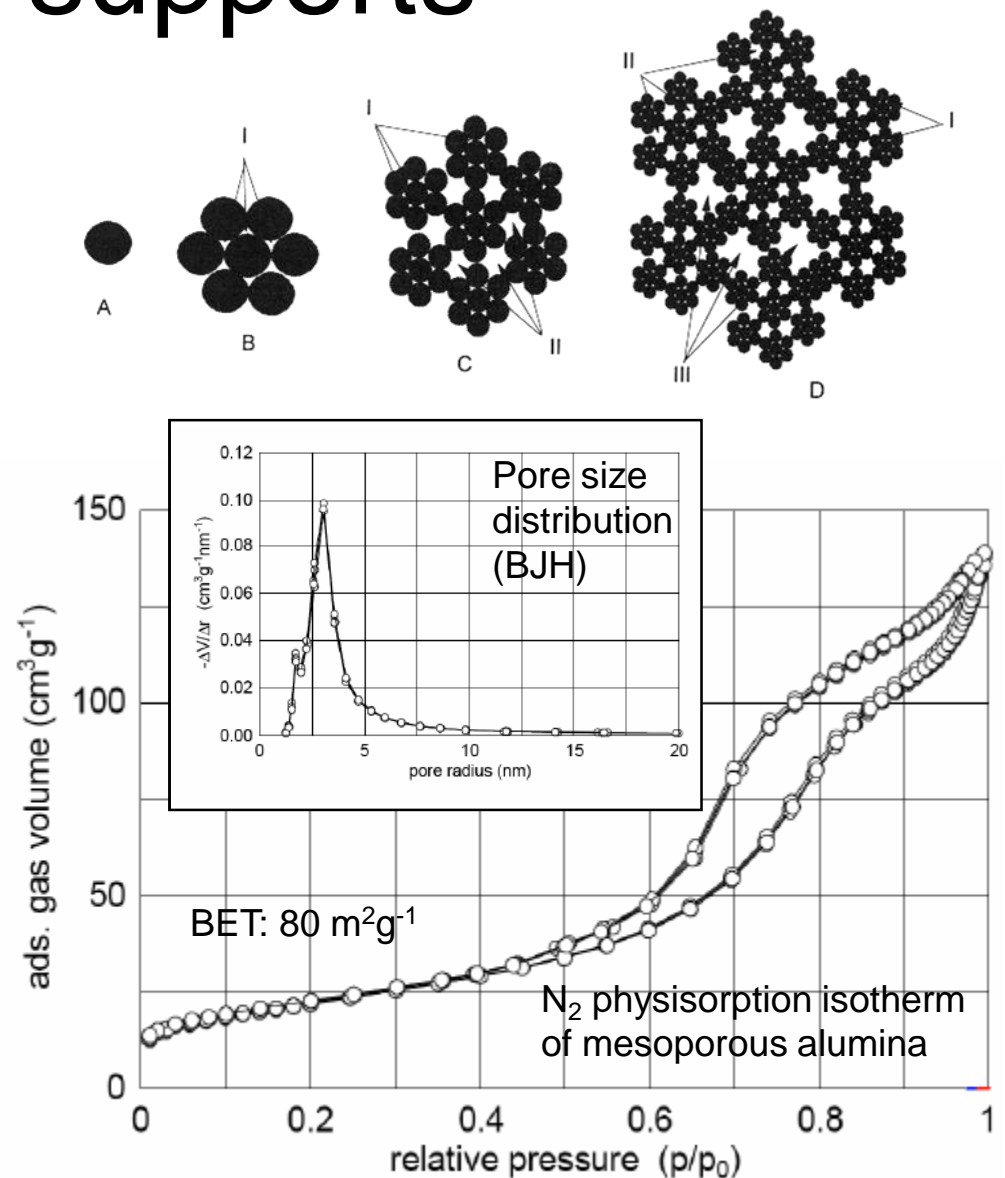


Synthesis of supports: Alumina

- Porous aluminas are obtained by controlled dehydration of $\text{Al}(\text{OH})_3$ (Gibbsite, Bayerite) or $\text{AlO}(\text{OH})$ ((Pseudo-)Boehmite)
 - transition aluminas: $\text{Al}_2\text{O}_3 \cdot x \text{H}_2\text{O}$
 - active aluminas: γ and η
 - full dehydration: non-porous α - Al_2O_3 (corundum)
- The non-porous hydroxides can be precipitated from Al salt solutions by increasing pH
 - Bayerite: high T and pH
 - (Pseudo-)Boehmite: low pH
- High purity aluminas are prepared by hydrolysis of Al-alcoholates

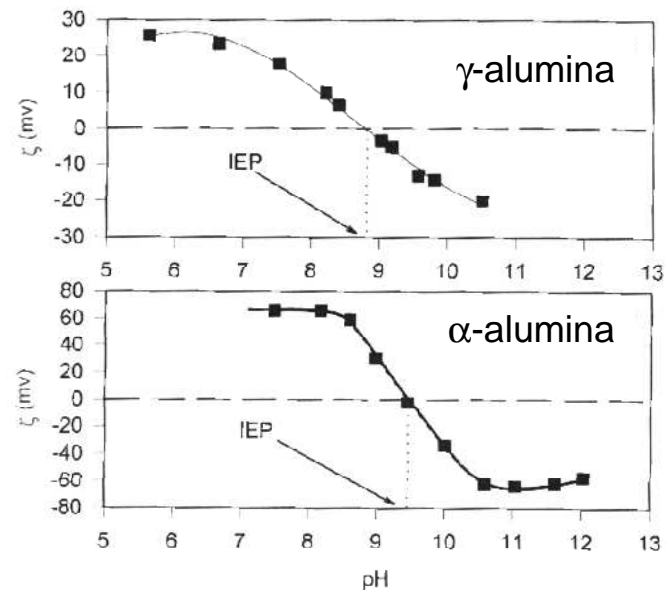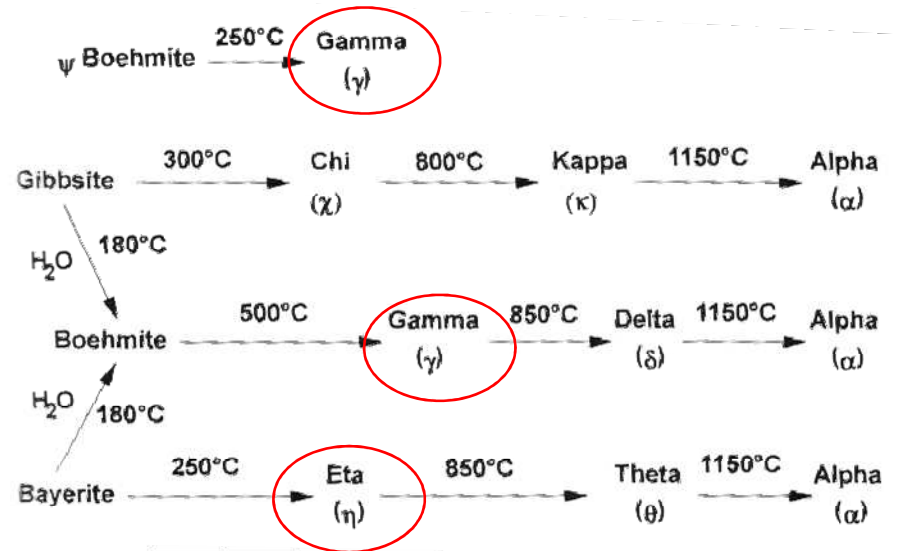




Surface charge and Zeta potential

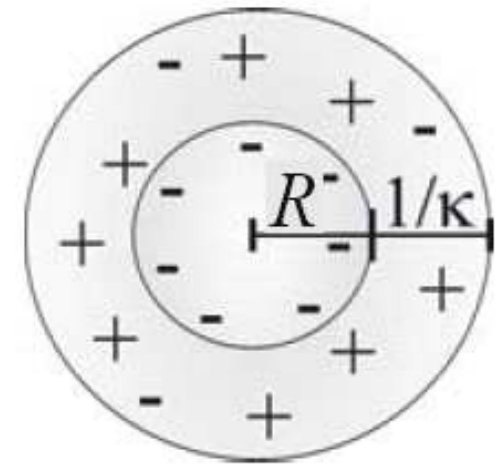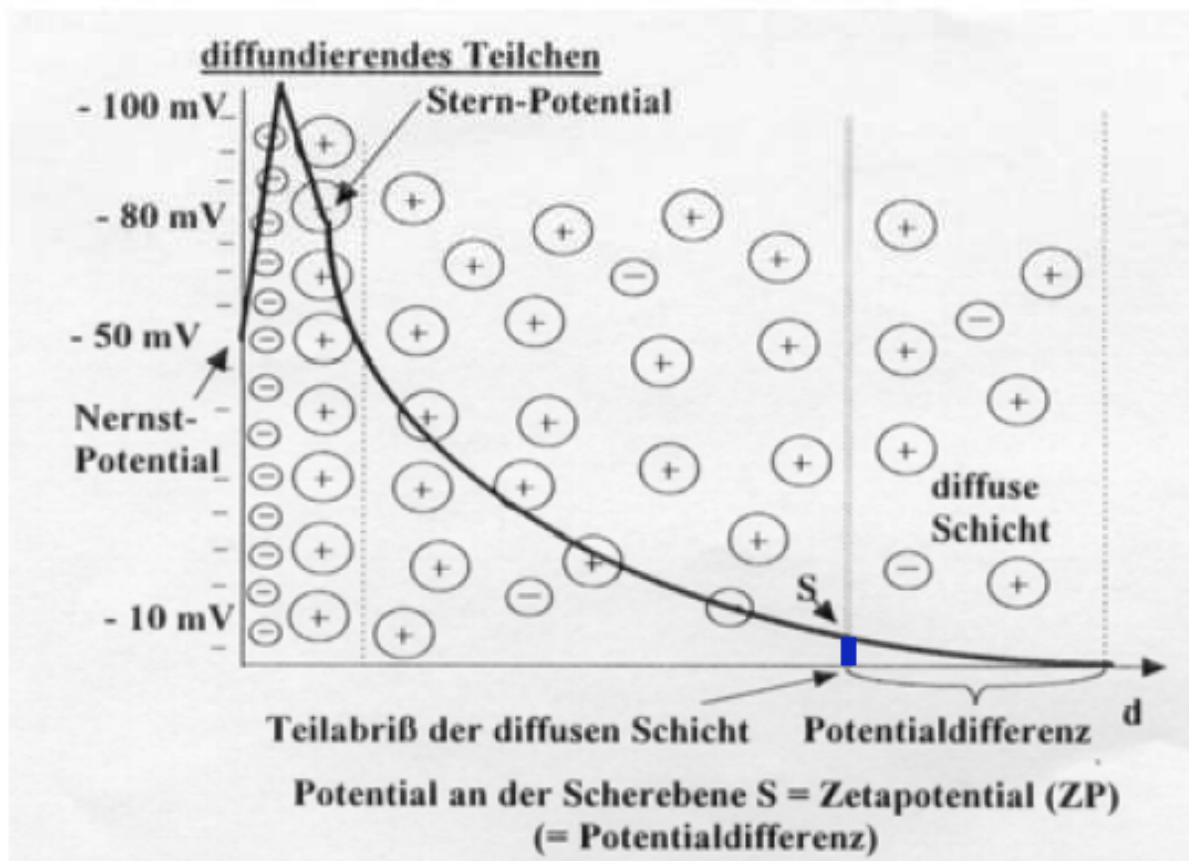


R : Partikelradius
 κ^{-1} : rezipr. Debyesche
 Abschirmlänge

Surface charge of oxide supports

- In contact with water hydroxyl groups are formed on the oxide surface (M-OH)
- M-OH may behave as Brønsted acids or bases
 - $M-OH + OH^- \rightarrow M-O^- + H_2O$
 - $M-OH + H^+ \rightarrow M-OH_2^+$
- Surface charge depends on solution pH
- Zeta (ζ -) potential is an estimation of surface charge

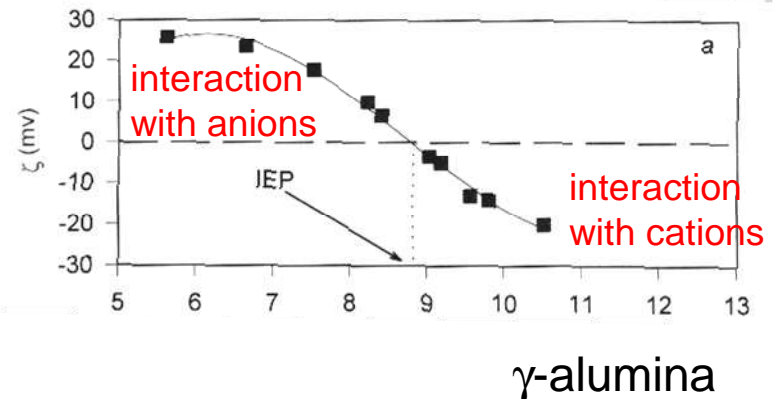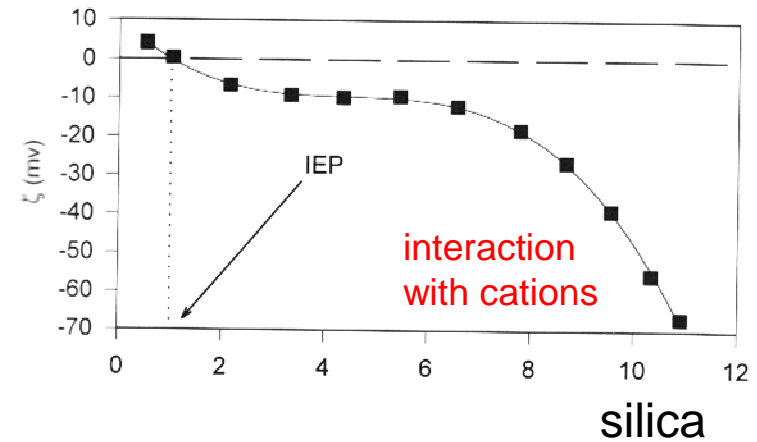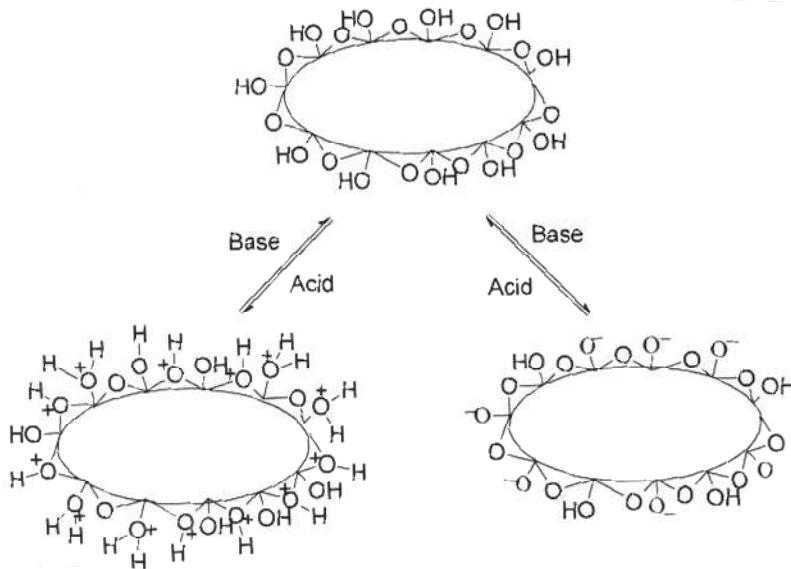


Zeta potential measurement

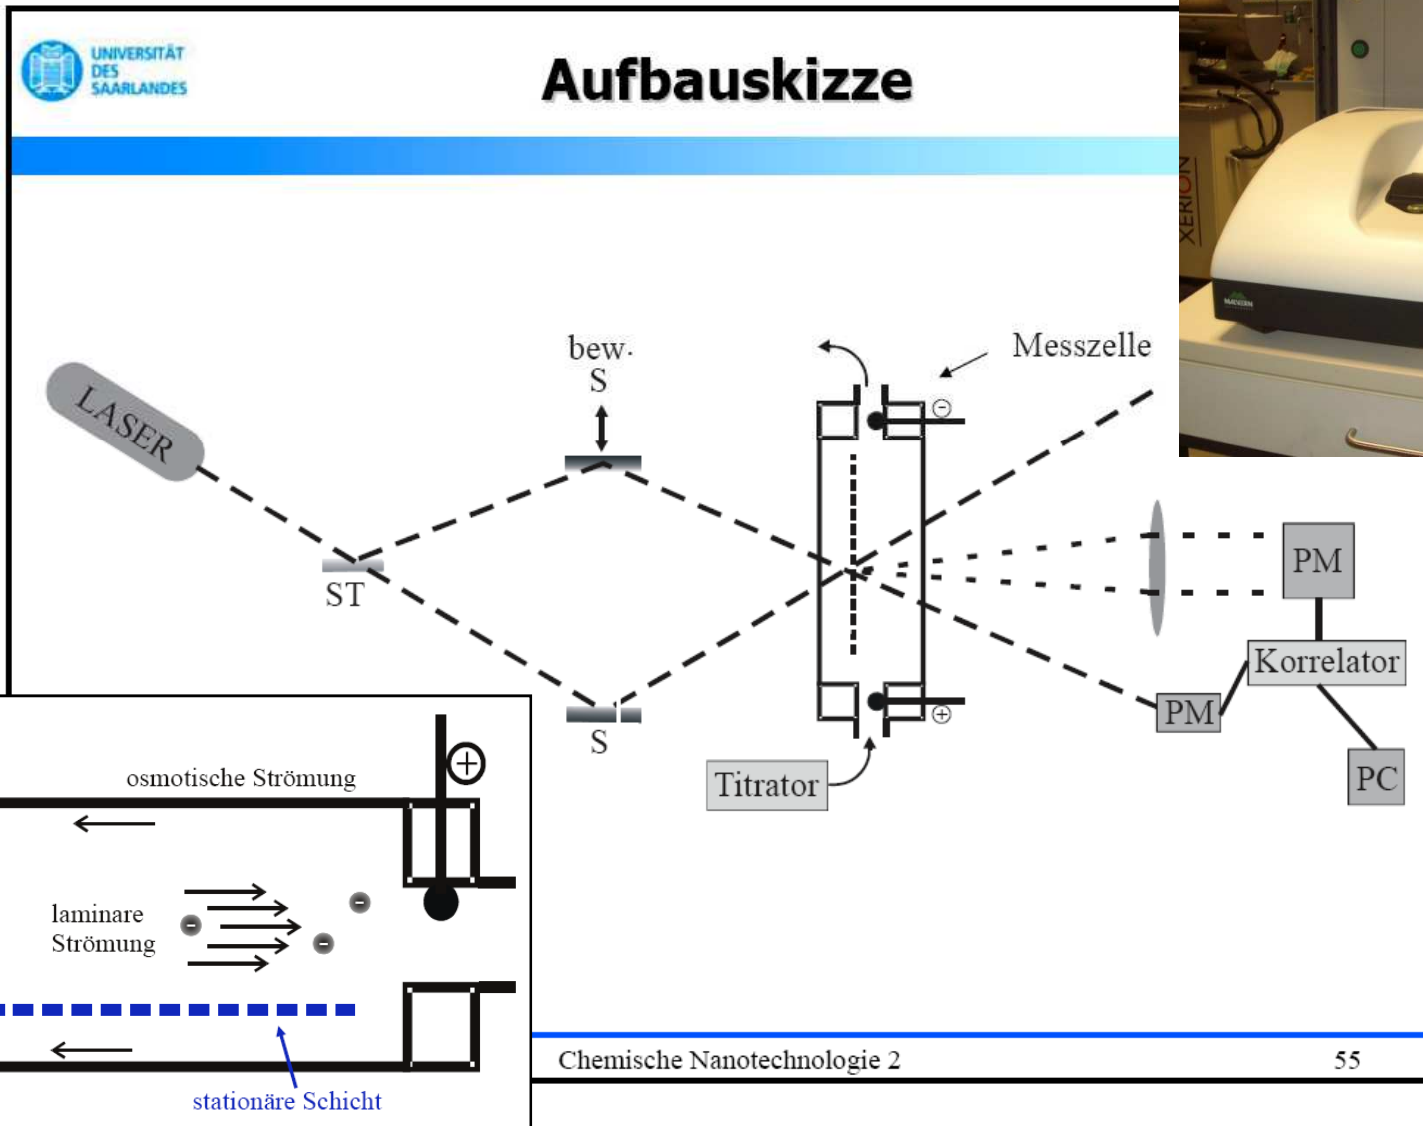

Impregnation

- Low volume of precursor solution (usually a transition metal salt) is mixed with the support and the mixture is dried
- The whole precursor is expected to retain on the support (no washing)
- Precursor solution contains decomposable counter ions and ligands (NH_4^+ , NO_3^- , $\text{C}_2\text{O}_4^{2-}$, ...)
- Two types
 - Pores of the support are initially filled with air: Capillary impregnation
 - Pores of the support are initially filled with liquid: Diffusional impregnation

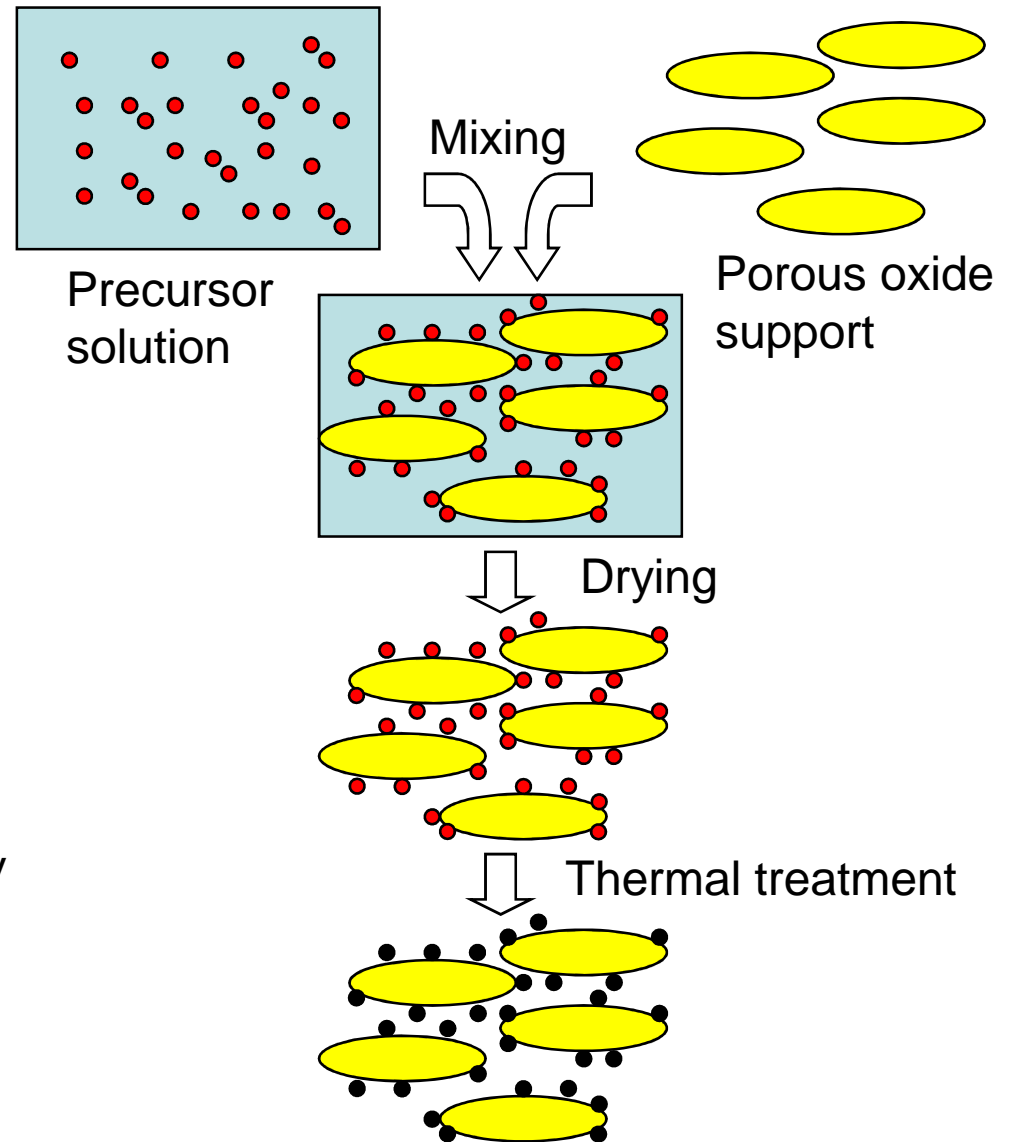


Capillary vs. diffusional impregnation

Support of pore volume V_p is in contact with the precursor solution of volume V


- $V_p = V$: dry or incipient wetness impregnation
- exothermal process, increase in T
 - Pre-treatment with super-heated steam
- air bubbles are trapped as the solution is sucked into the pores by capillary forces and may burst the support particles lowering the mechanical strength
 - Operation in vacuum, usage of surfactants
- filling of pores theoretically finished in seconds, but trapped air leads to delay of the process and possibly inhomogeneous distribution of the active component
- $V_p < V$: wet impregnation
- Pores of the support are pre-filled with pure solvent
- Solvent-saturated support is immersed into the precursor solution
- Concentration gradient between external precursor solution and pores leads to migration of precursor salt into the pores
- non-exothermic, but longer process

Distribution of the active phase

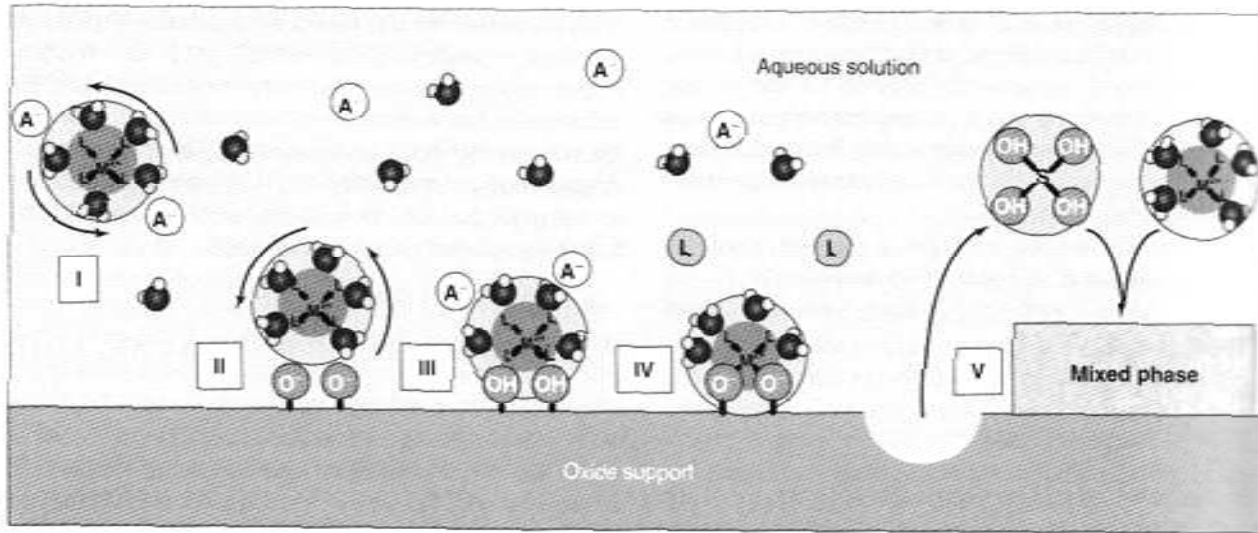

- Homogeneous distribution on the macroscale is not always desired
- Distribution of the active phase is determined by the interaction of the precursor and the support surface (adsorption)


- If interaction is too high strong adsorption on the edge sites is observed
 - precursor concentration is locally decreased, no concentration gradient between inner particle and outer shell, migration of precursor is hindered → eggshell distribution

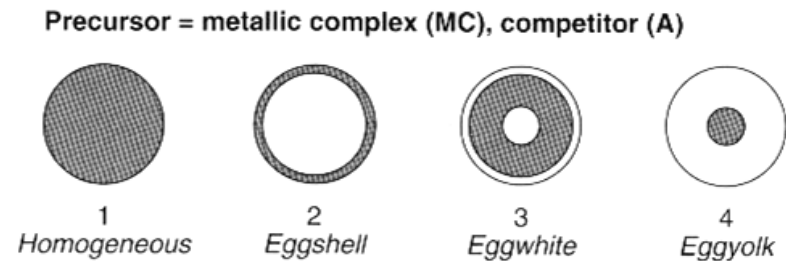


- 1: roughly same affinities of MC and A
- 2: high affinity of MC; no competition
- 3: high affinity of A, low affinity of MC; low A/MC ratio
- 4: high affinity of A, low affinity of MC; high A/MC ratio

Key experimental parameters I

- IEP (alumina: pH ~9, silica: pH ~2)
 - electrostatic interaction of solid oxide surface and precursor complex (anions adsorbed for pH < 9, cations for pH > 9)
 - can be regulated by varying T (IEP at higher pH at higher T), selective adsorbates (Na⁺: abrupt increase of pzc/IEP, F⁻: decrease of pzc/IEP)
- pH
 - determines the surface charge of the solid oxide
 - determines the solution species of the precursor complex (NH₃- or H₂O-complexes, monomers or oligomers, ...)
- Type of ligands
 - charge, bulkiness, stability, ...
- Competitive ions
 - blocking of edge sites forcing precursor complexes further into the pores of the support particle

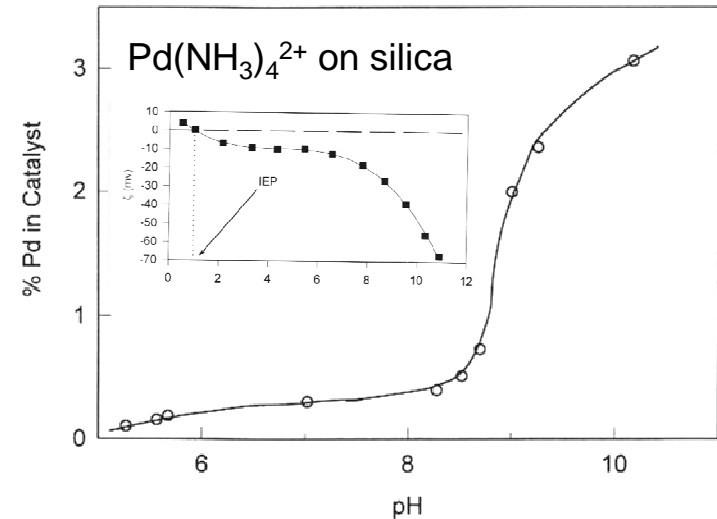

(for [PtCl₆]²⁻ on alumina: acidic environment required)

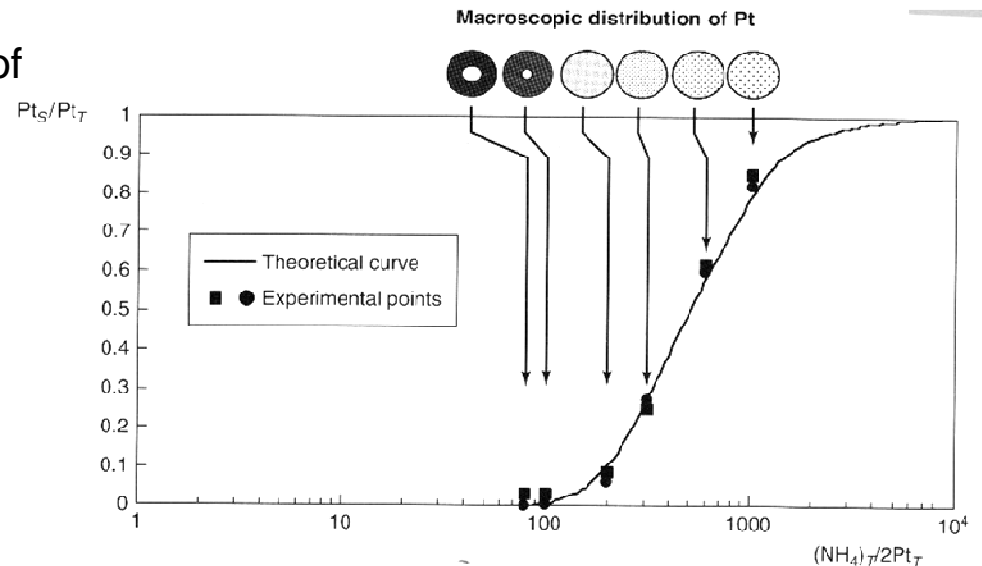

Key experimental parameters II

- Solvent
 - influences the interaction of solvated complex and surface of support
- Kinetics
- Drying
 - if interaction of precursor and oxide surface is too low, precursor species may migrate out again as the liquid leaves the pores









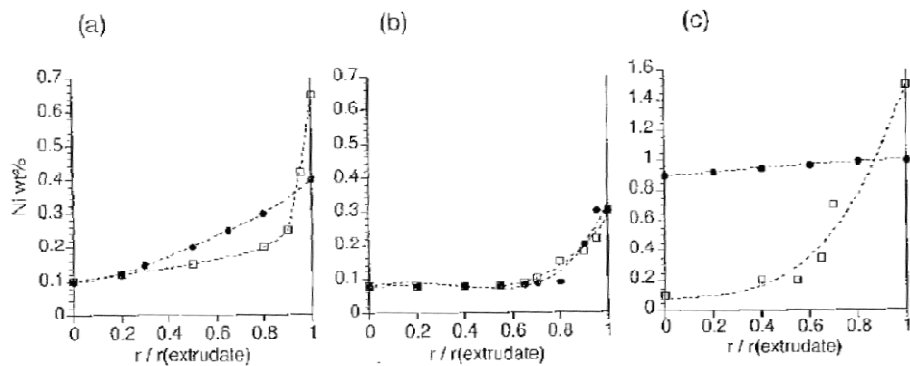


Figure 4.2 Profiles of nickel content in spherical extrudates before drying (black circles) and after drying (white squares). The origin of axis x corresponds to the center of the extrudate. (a) Low drying rate to 110°C; (b) high drying rate to 110°C; and (c) drying at 200°C. (Data have been collected from [41] (a and b) and [31] (c).)

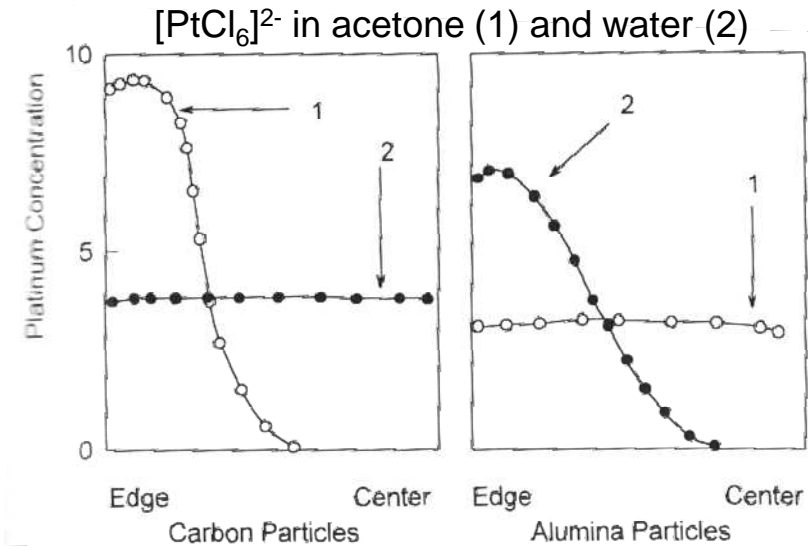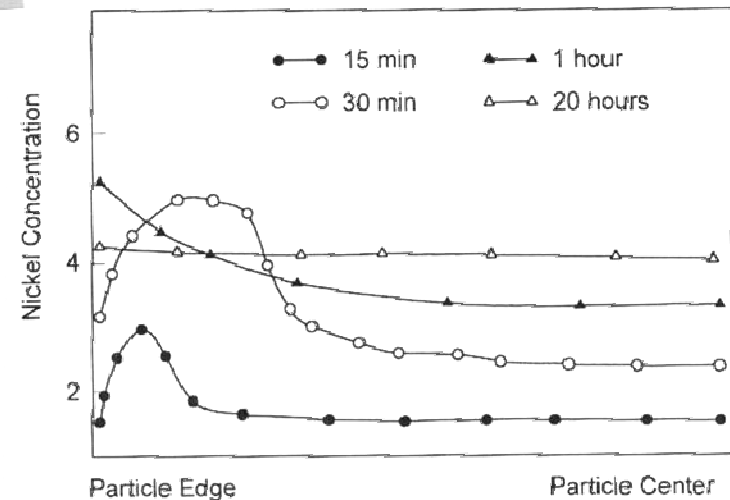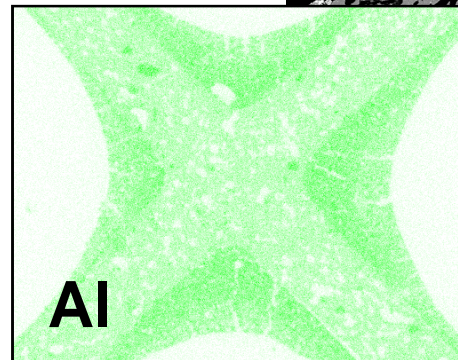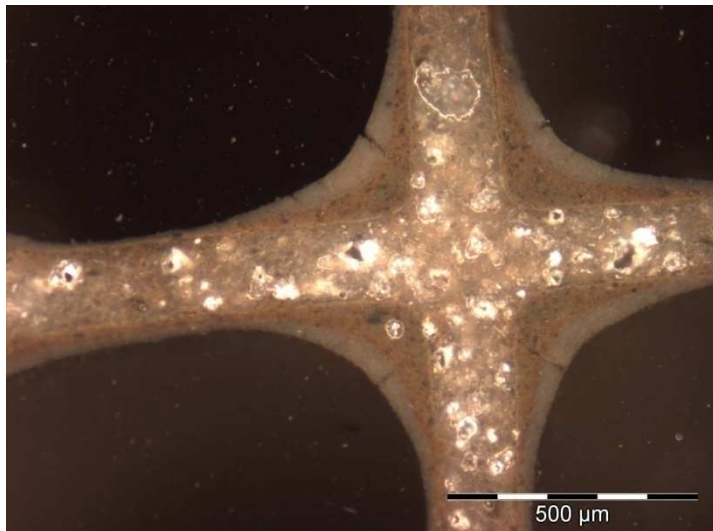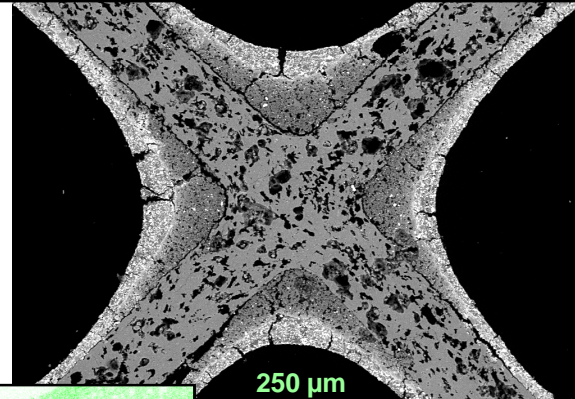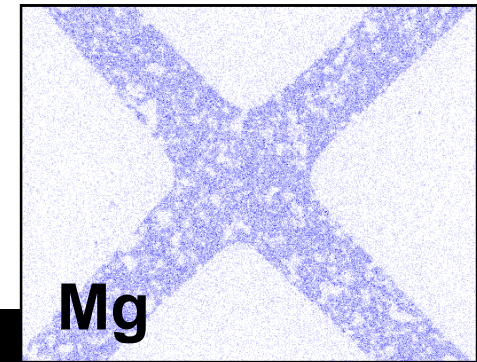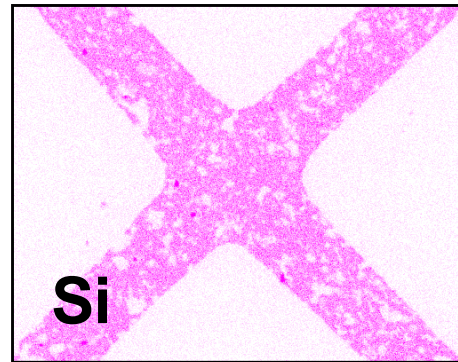


Impregnation of alumina with aqueous Ni(NO₃)₂

Three-way-catalyst

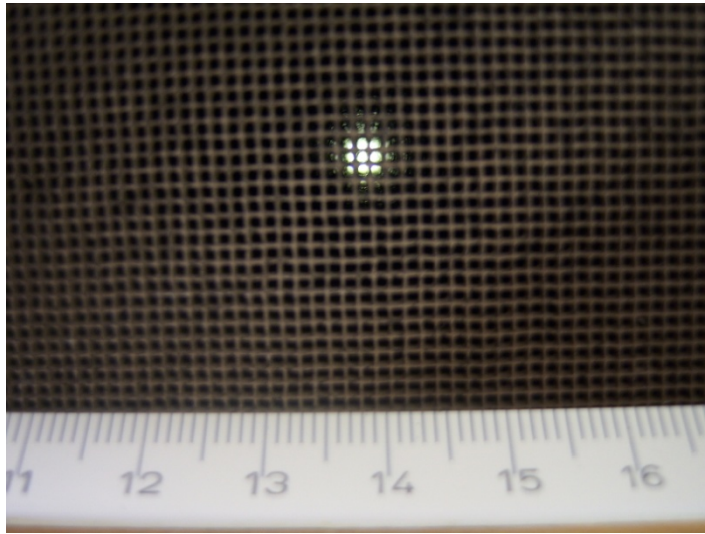


250 μm
File | Pressure
kat_BSE_002.tif* | 60.0 Pa

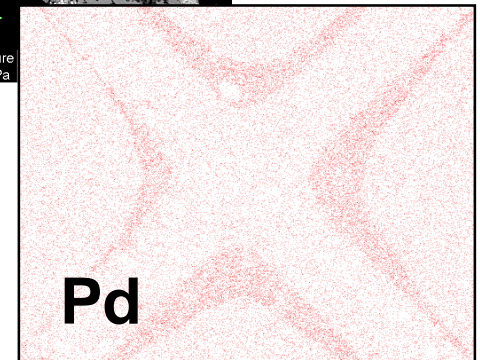

Co-precipitation

- Precipitation of a mixed solution to form a precursor containing several species in a homogeneous distribution (preferably within a single phase)
- Thermal decomposition of counter ions by calcination (NO_3^- , CO_3^{2-} , NH_4^+ , $\text{C}_2\text{O}_4^{2-}$, ...),
- Sometimes further thermal treatment (activation)

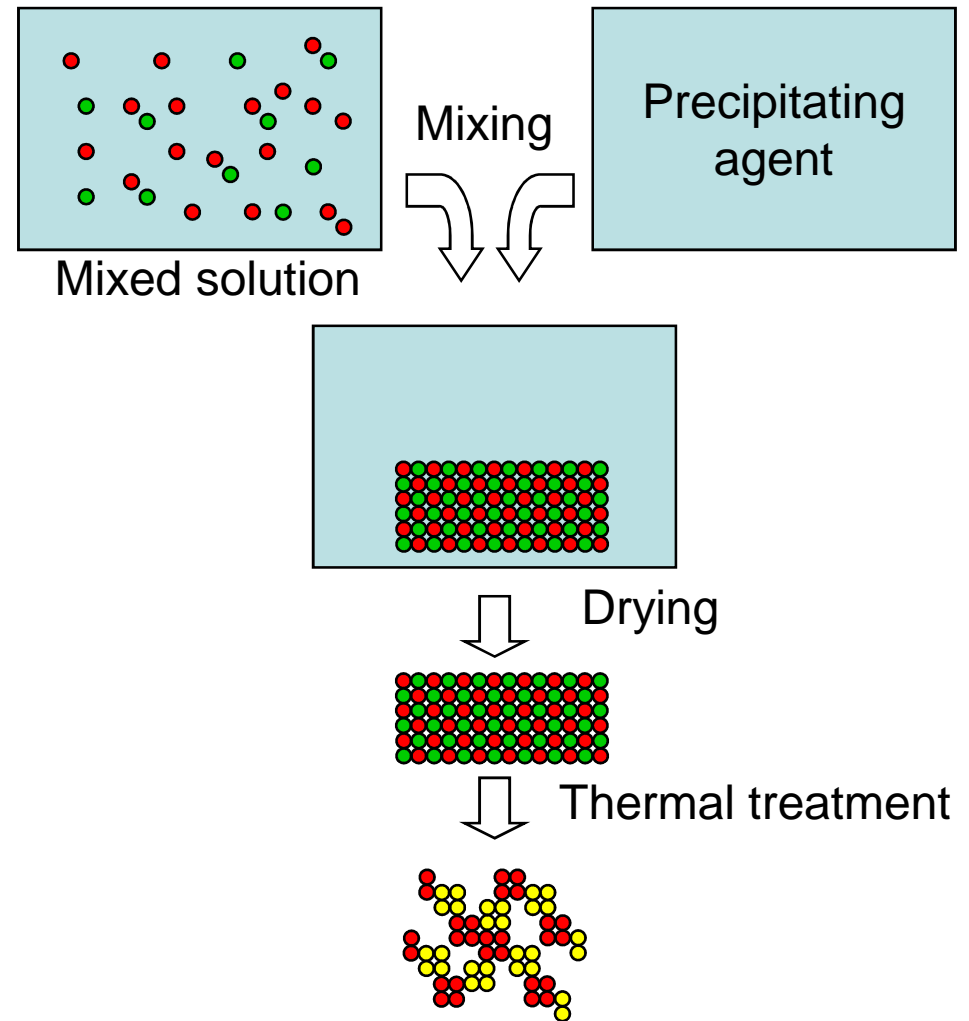

Precipitation – Nucleation & growth

- Homogeneous nucleation
 - $\Delta G = \Delta G_{\text{bulk}} + \Delta G_{\text{interface}} (+ \Delta G_{\text{others}})$
 - r_{critical} : size of the nucleus
 - nucleus: smallest solid-phase aggregate of atoms, which is capable of spontaneous growth
 - The more nucleation is favoured compared to growth, the smaller the particles will be
 - Nucleation is temperature-dependent


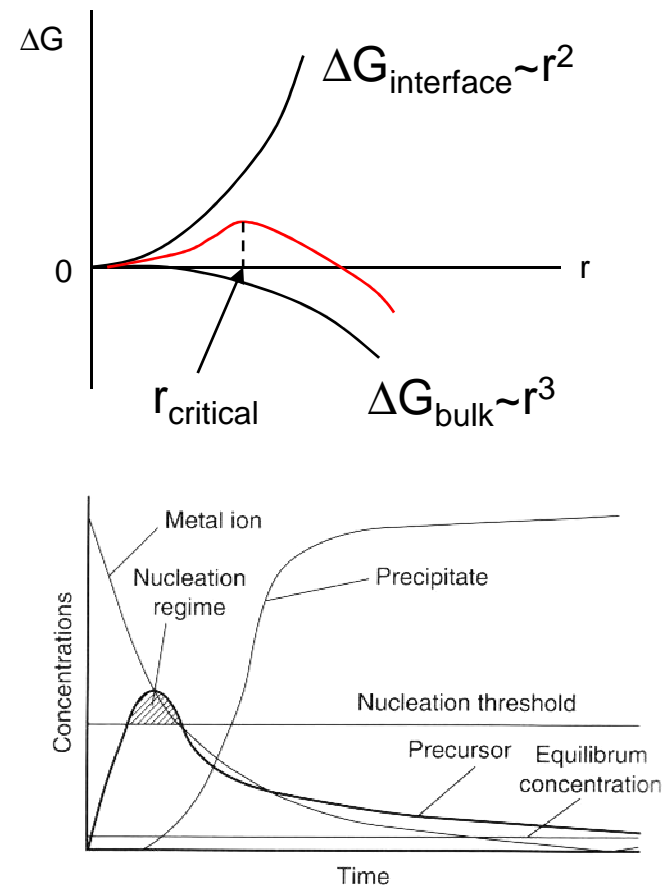


Fig. 2 Simplified scheme for the formation of a solid product from solution. From the metal ions a precursor species is formed, for example by hydrolysis or raising the pH. When the concentration of the precursor species exceeds the nucleation threshold, precipitation of the product begins, consuming the precursor by nucleation and growth. New nuclei are formed only in the shaded area.

Cu/ZnO methanol synthesis catalysts

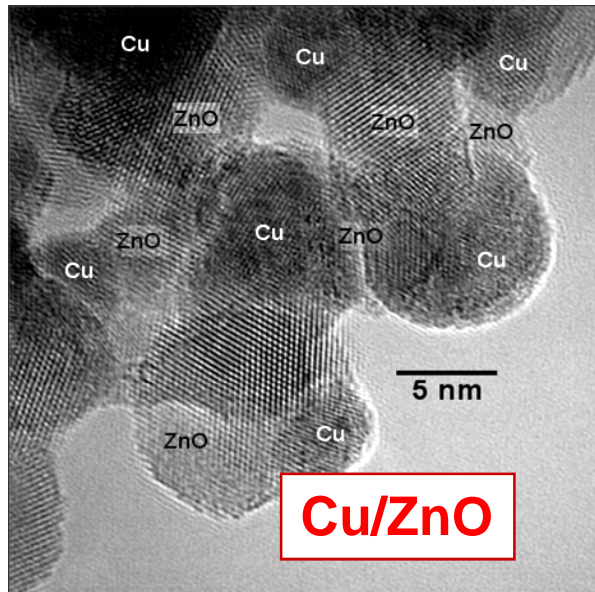

Cu-, Zn-, Nitrates // Na_2CO_3 solution
Co-Precipitation and Ageing

Reduction
←




Calcination
↑






Washing / Drying
←

Composition:
Cu:Zn ~ 70:30

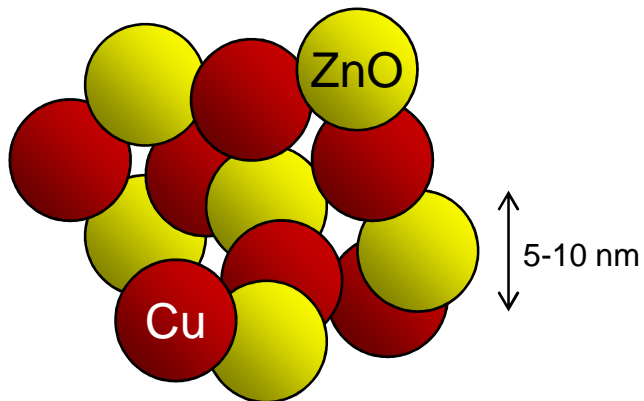

Cation hydrolysis

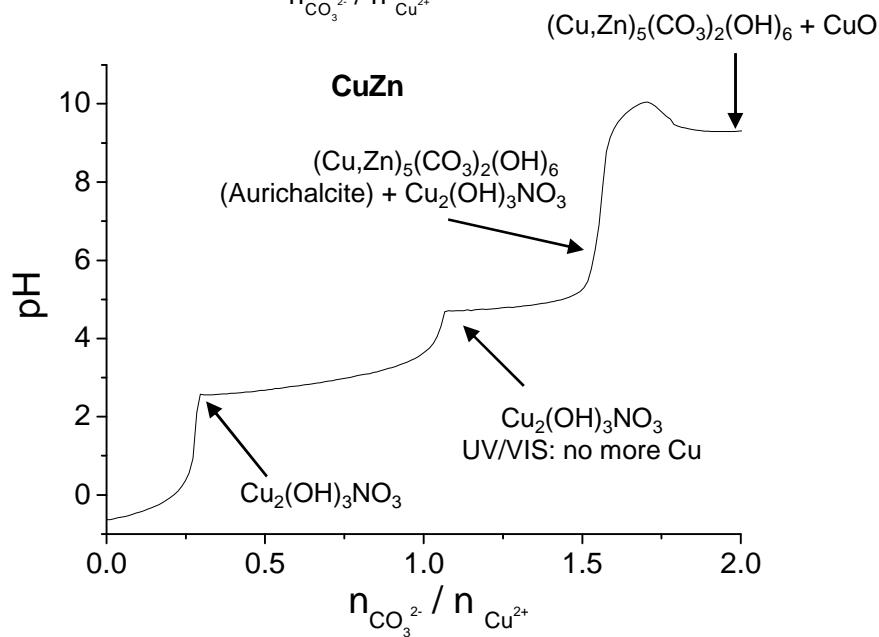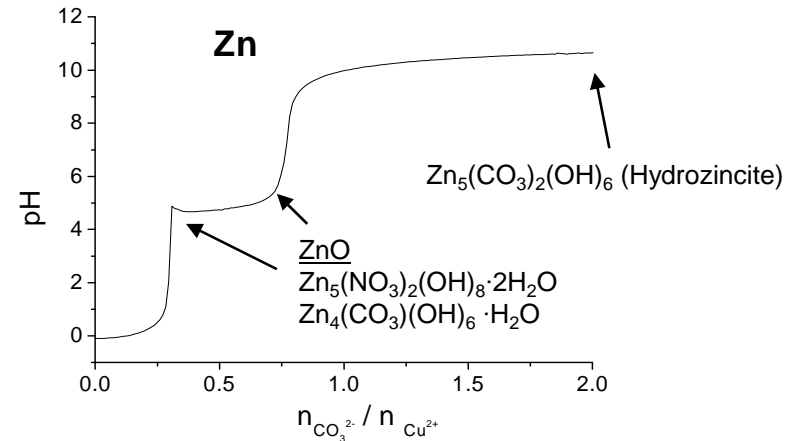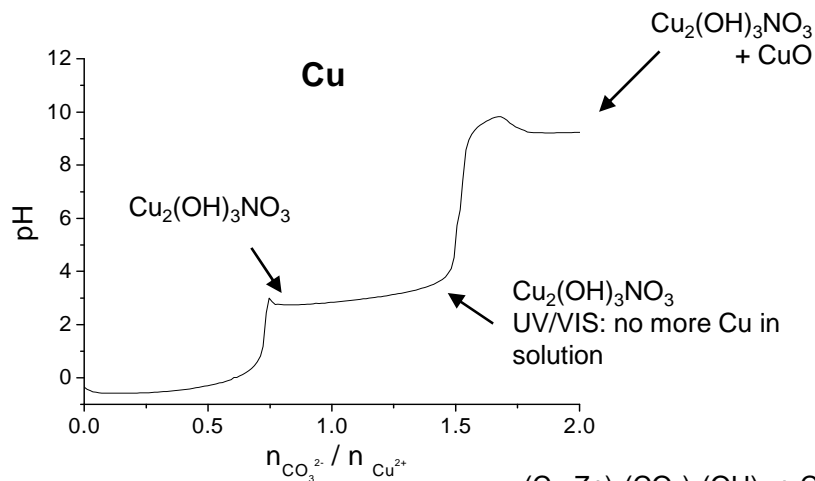

- Titration curve of the binary system is composed from the curves of the single systems
- No real co-precipitation under increasing pH conditions

Constant pH co-precipitation

CuZn solution
 Na_2CO_3 solution



automatic reactor

constant pH 7
 $T = 65^\circ\text{C}$




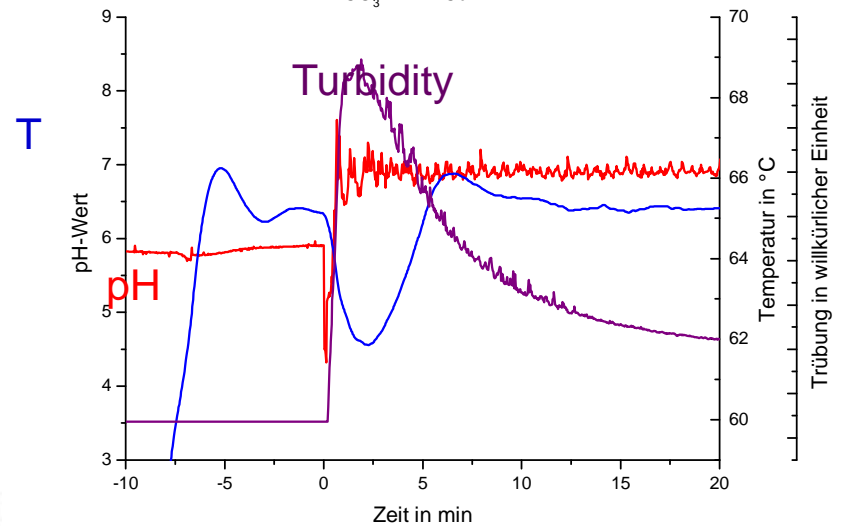







Figure 7.3 Precipitation processing routes: forward (base to acid) and reverse (acid to base) precipitation, continuous precipitation, and corresponding pH profiles.

Parameters for Cu/ZnO/(Al₂O₃) preparation


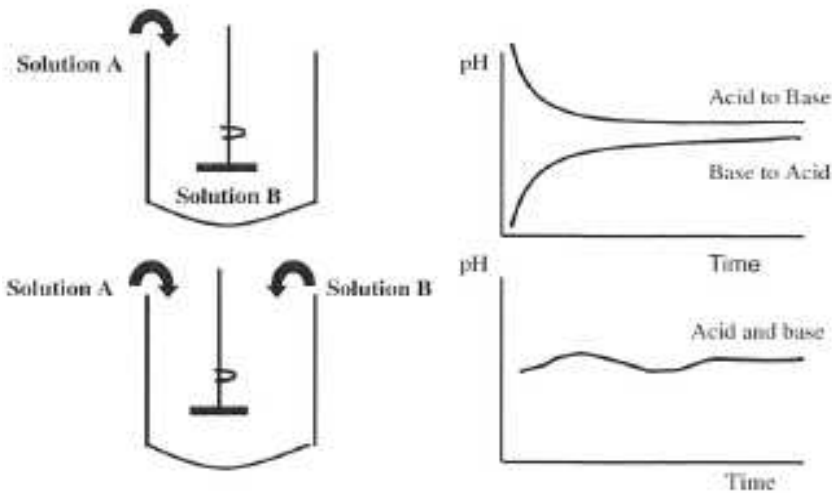
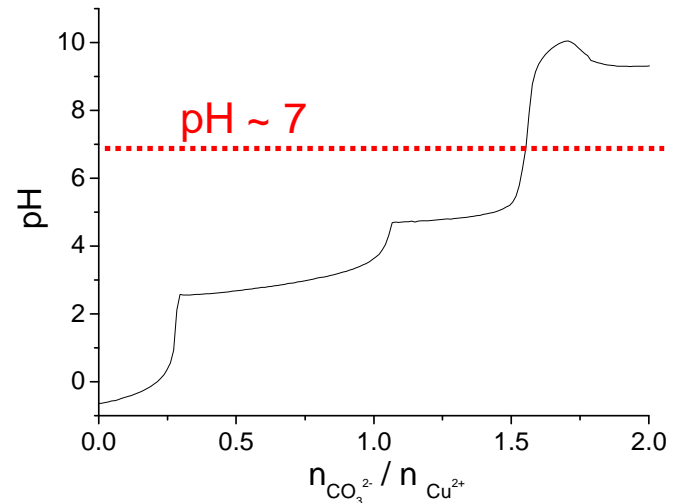
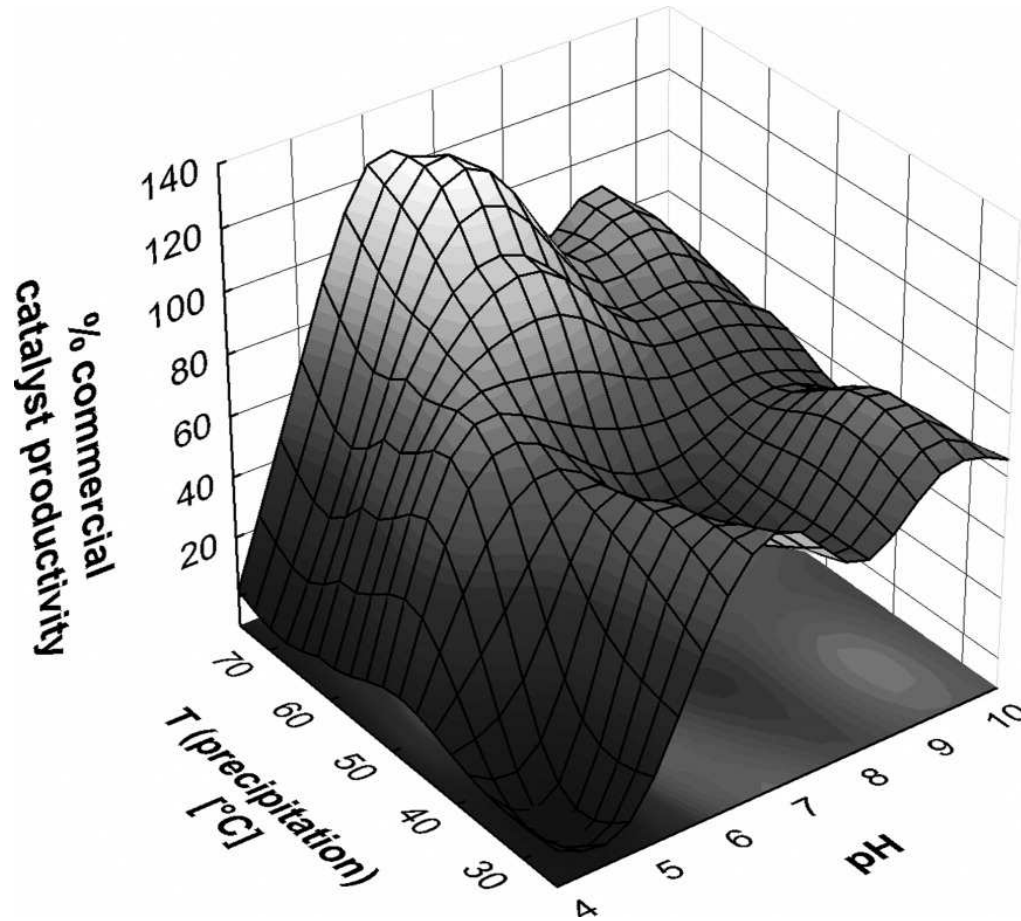


“Chemical memory”


Effects of ageing

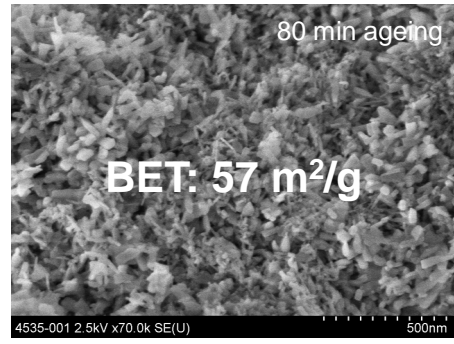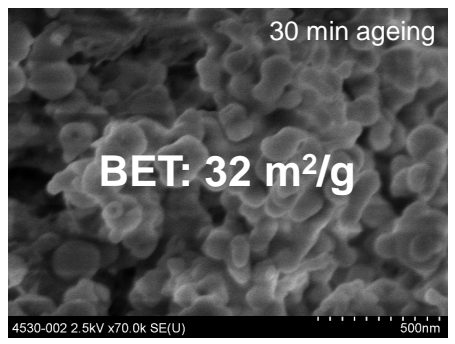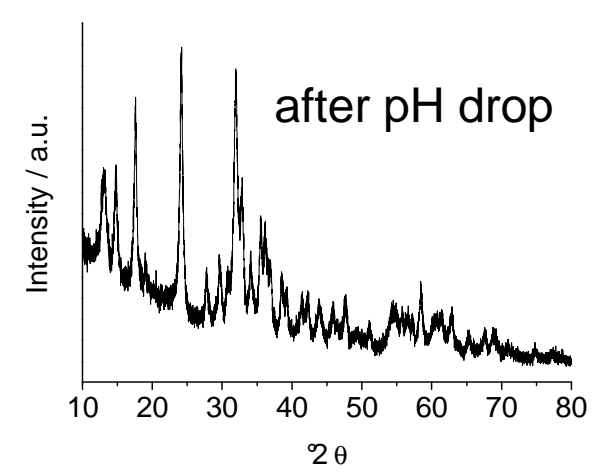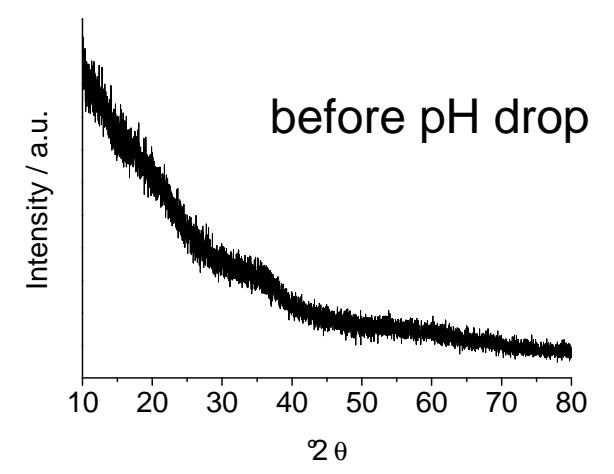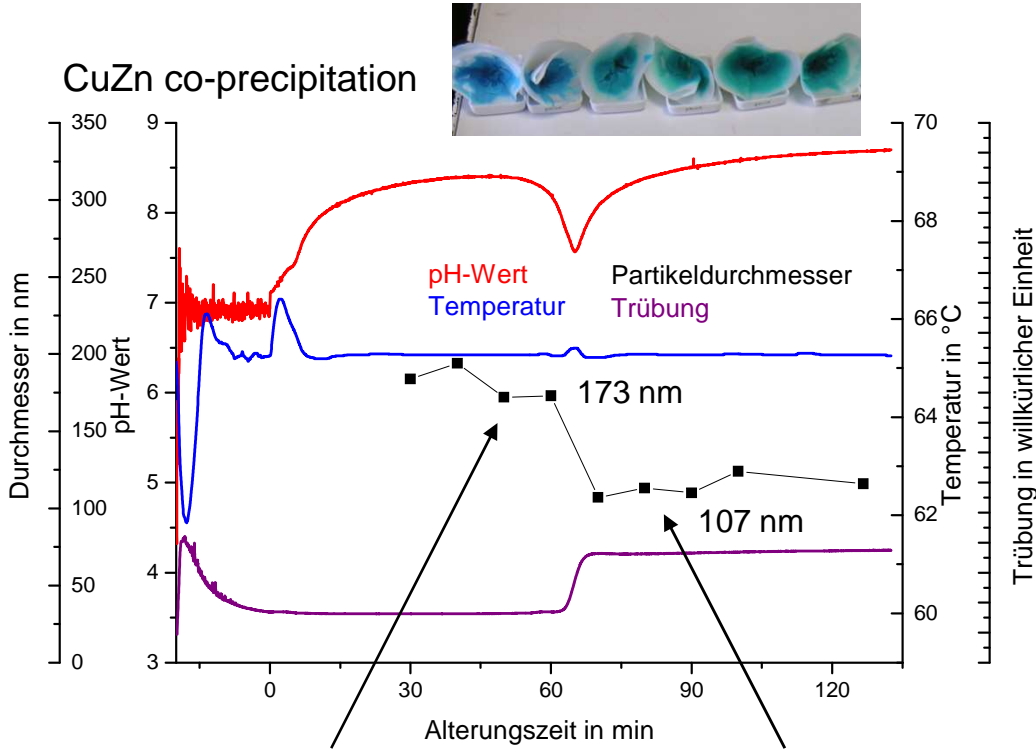


The importance of precursor chemistry

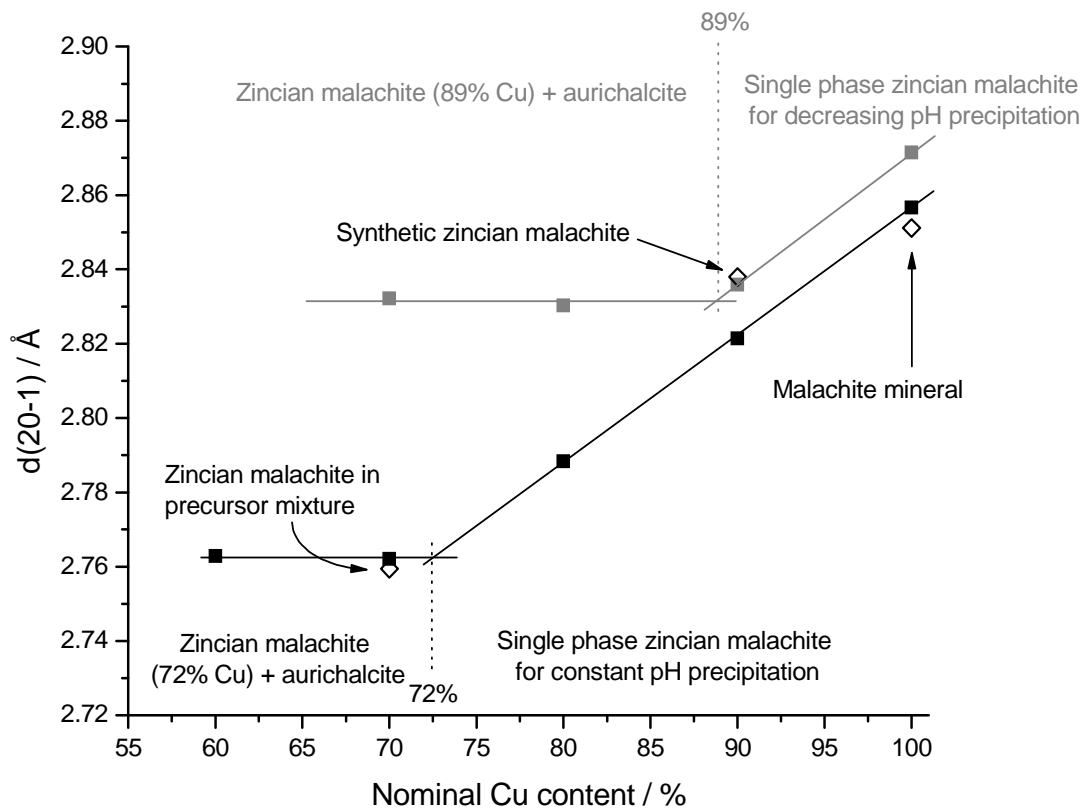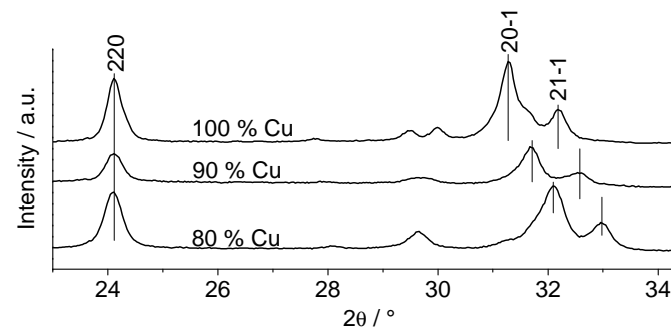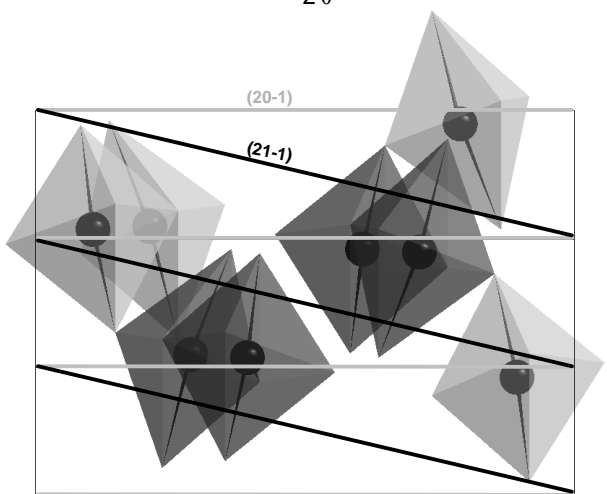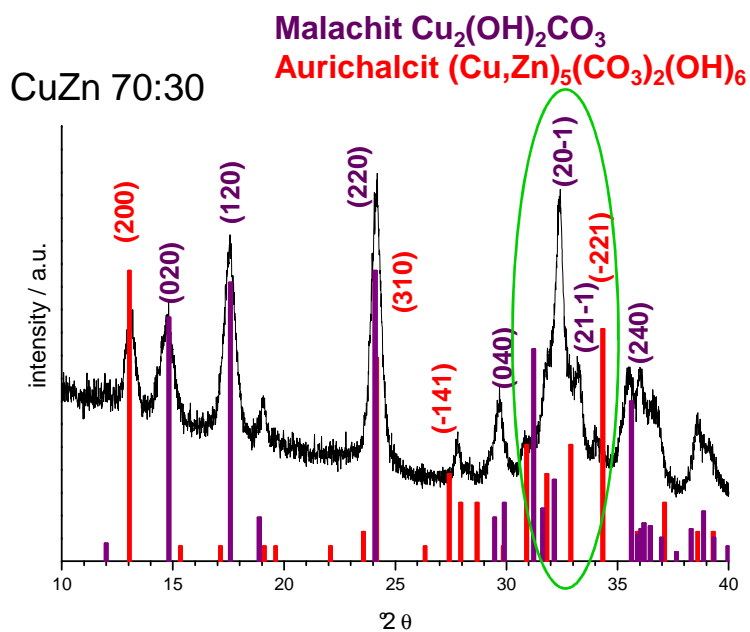

The right precursor composition

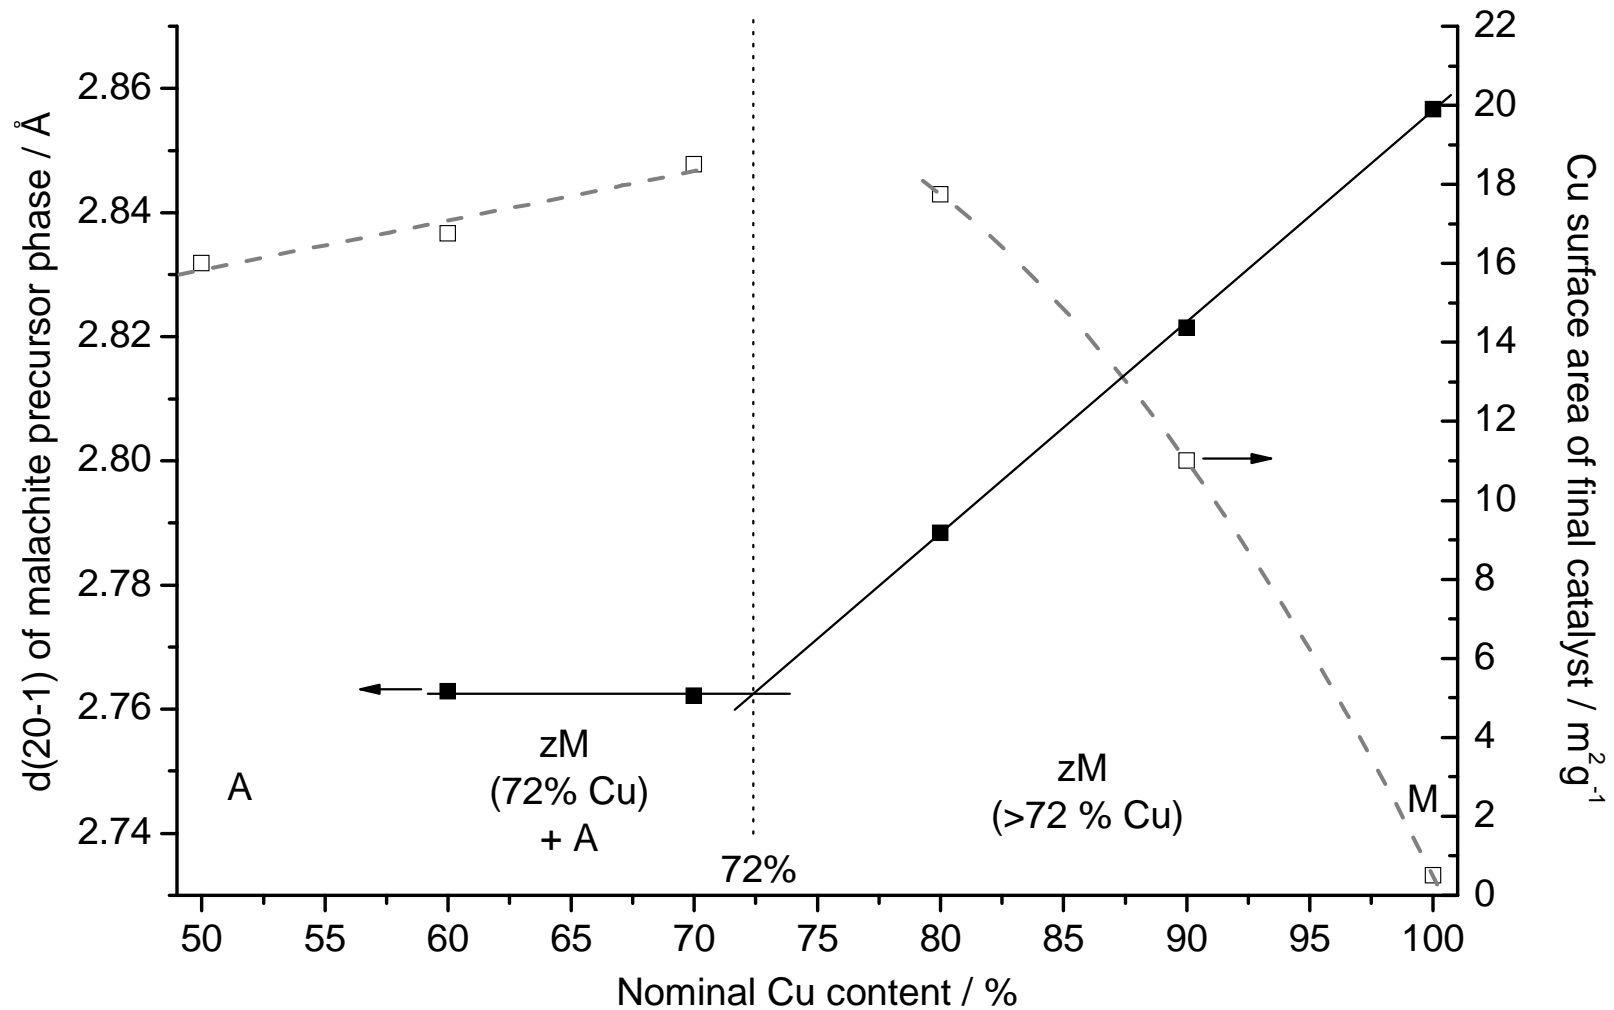

Structuring of the Cu/ZnO catalysts

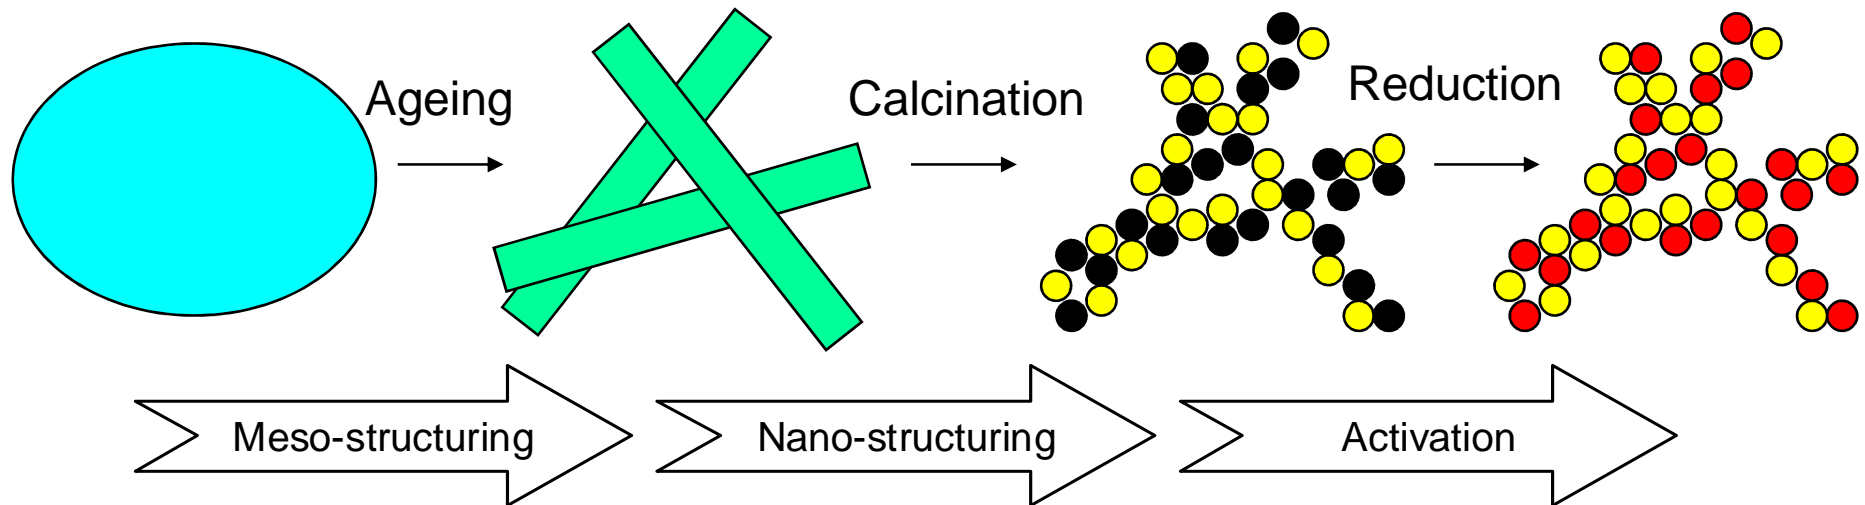


Initial precipitate
Zincian georgeite


Aged precipitate
Zincian malachite

Calcination product
CuO / ZnO



Active catalyst
Cu / ZnO

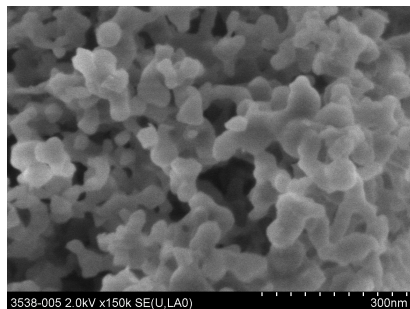


undefined compact shape
size ca. 100 nm

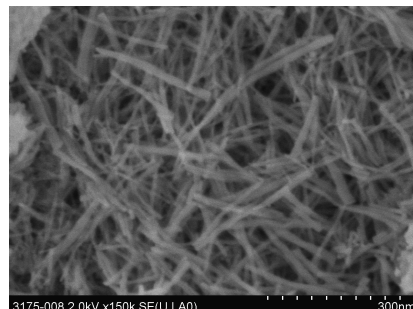

thin needles
size ca. 20 × 200 nm


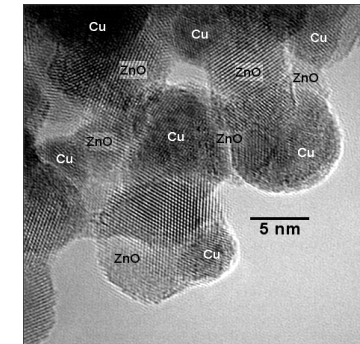
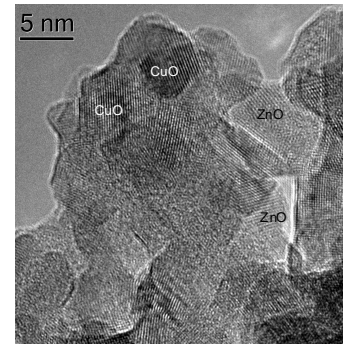


spherical particles
size ca. 10 nm

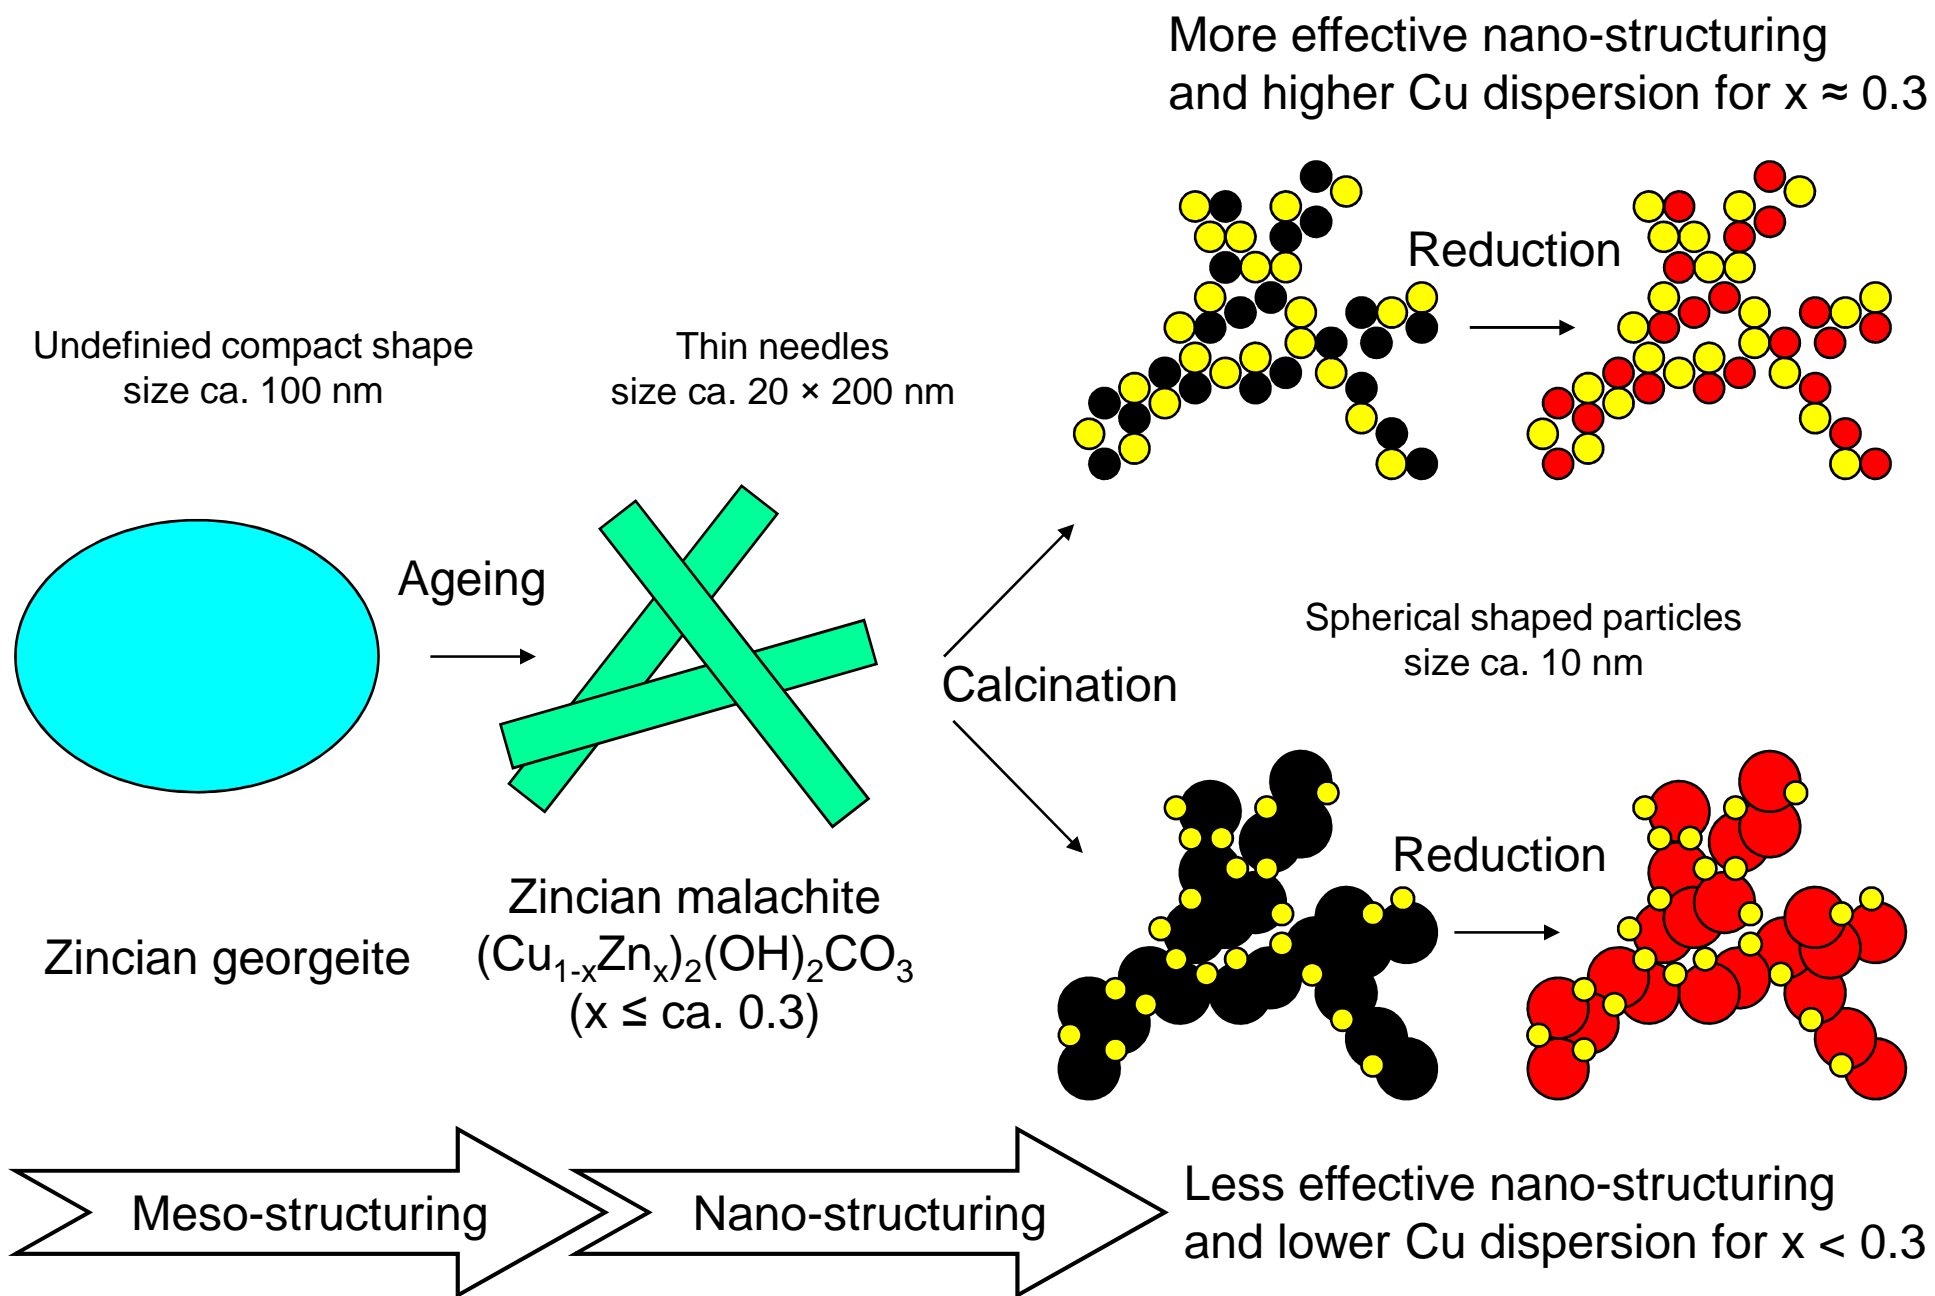

Skeletal catalysts


- Skeletal catalysts are prepared from an M-Al alloy (M: Ni, Cu, ...) by leaching of Al with sodium hydroxide (20-40 wt.-%)
- Alloys are prepared by melting the active metal and Al, quenching and crushing
- Porosity can be controlled by composition of the alloy, T of leaching
- No activation necessary

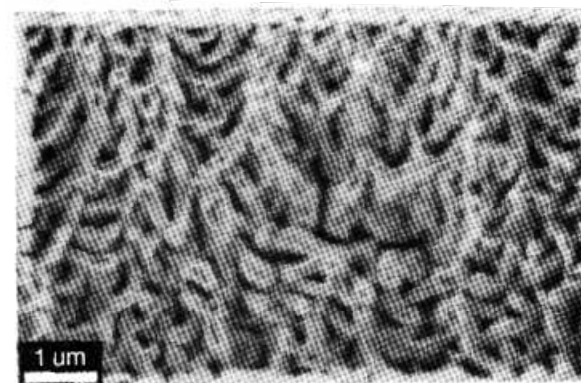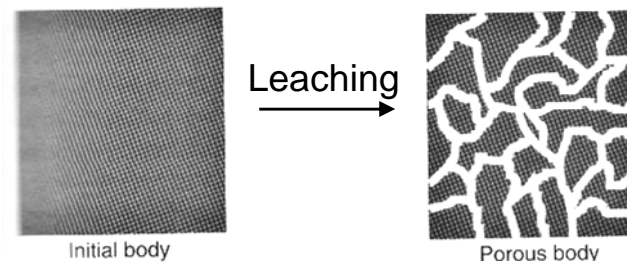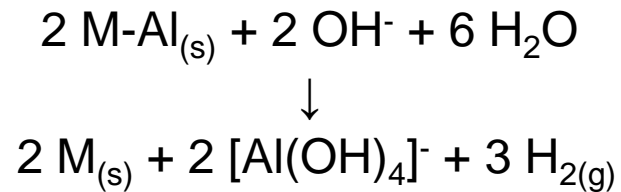

Skeletal Cu catalysts prepared from a 50 wt.-% Cu-Al alloy

Raney nickel



- Used for hydrogenation reactions and as electrocatalyst
- 5 times more active than supported Ni catalyst used before (M. Raney, 1925)
- Ni-Al alloys (40-50% Ni) produced by dissolution of Ni in molten Al and quenching
- Phases: Ni_2Al_3 , NiAl_3
- NiAl_3 is leached more rapidly → smaller crystallite, but mechanically weak
- Ni_2Al_3 is more difficult to leach → strong residual material

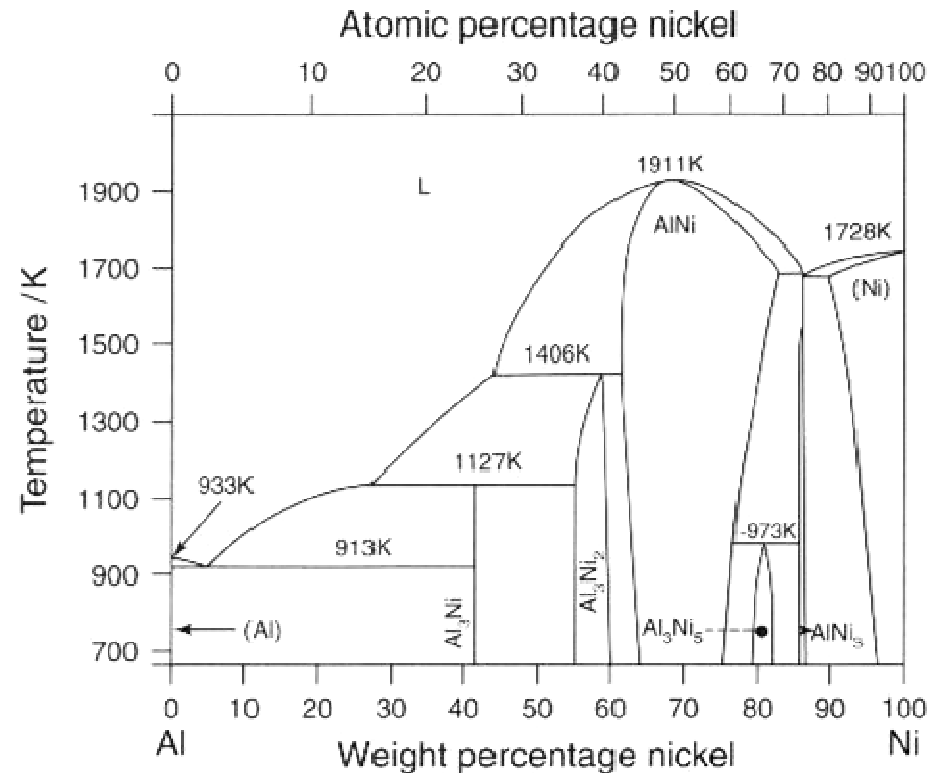

- BET SA 50-100 m^2g^{-1}
- crystallite size and pore diameter: 2 – 6 nm
- highly pyrophoric, has to be stored under liquid (water pH~9)




Hydrothermal synthesis

- Educts and solvent (water) are heated in a close reaction vessel (autoclave)
- At $T > 100^\circ\text{C}$ an autogeneous pressure builds up and the properties of water change
 - viscosity decreases \rightarrow higher mobility of ions
 - water self dissociation increases \rightarrow hydrolysis favoured
- If 2-5 % of educts dissolve (sometimes mineralizer required) \rightarrow rearrangement of building blocks (SBUs) to form new structures
- Conditions mild enough to allow crystallization of open framework structures

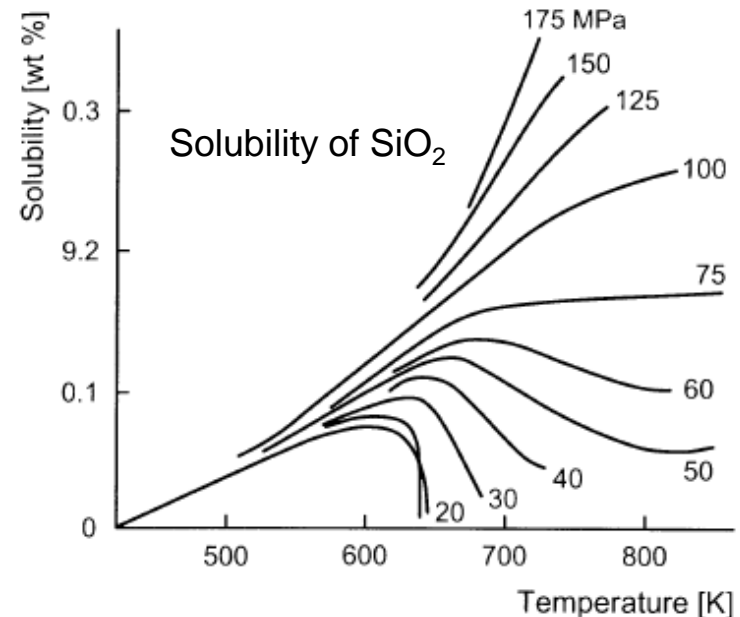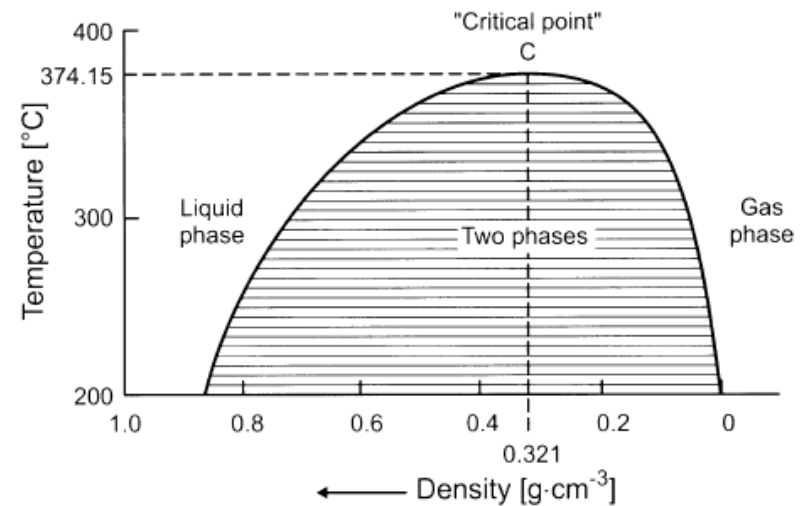

Zeolites

- General composition
 $M_{x/n}(Al_xSi_yO_{2(x+y)}) \cdot z H_2O$
 - M: cation of charge n
 - M: H⁺, group 1 or 2 or organic cation
- Si/Al varies between 1 and ∞
- Zeolite type obtained is determined by synthesis parameters

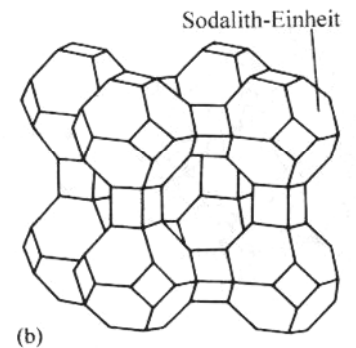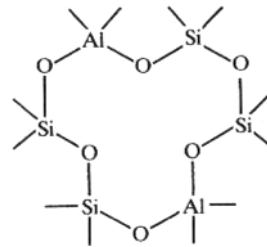


cage diameter:
window diameter:

1140 pm
410 pm



Properties of zeolites

- highly defined pore structure
- application as molecular sieves
- inner surface accessible for catalysis
- ion exchange possible
- proton exchanged zeolites: solid state acids
- after heating: Lewis acids
- shape selective catalysts
- used for catalytic cracking

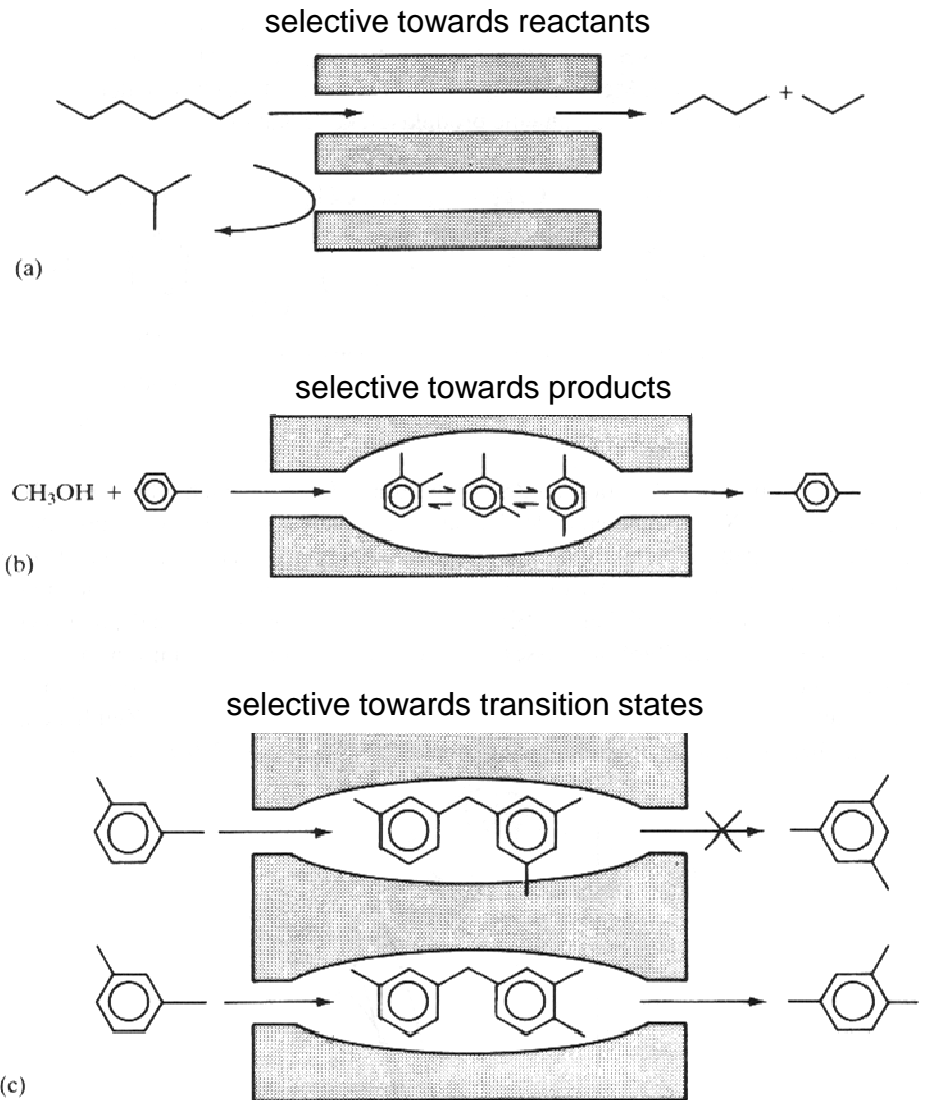



Hydrothermal synthesis of zeolites

- Si- and Al-sources form a mixed hydrogel
- OH^- as mineralizer (pH 9-13)
- Formation of polyanionic species in solution
- Nucleation and growth
 - by addition of preassembled elementary units
 - by aggregation

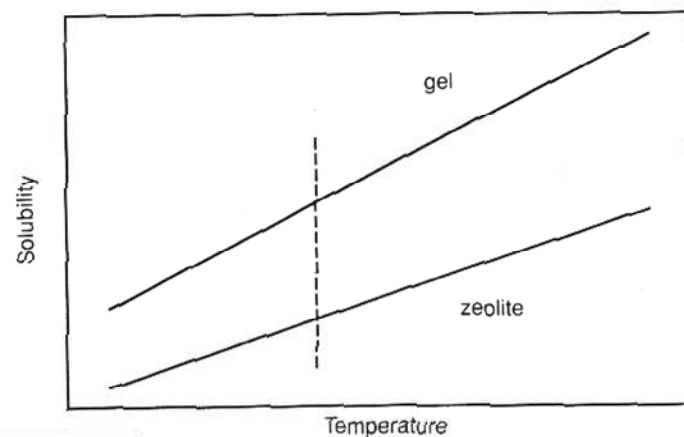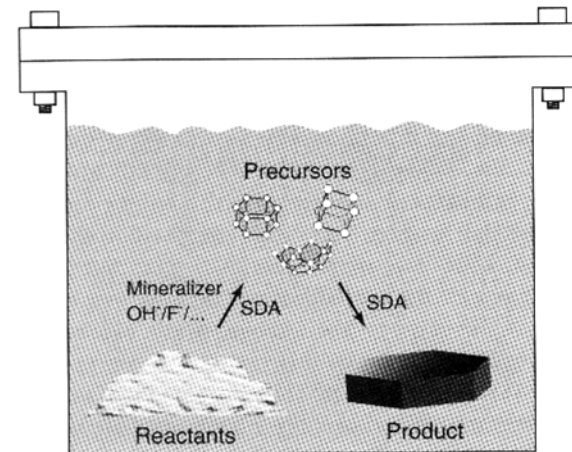

Template assisted synthesis

- Building blocks present in solution arrange around a structure-directing agent
- SDA acts as a template for the pore structure
- SDA can be removed by heating

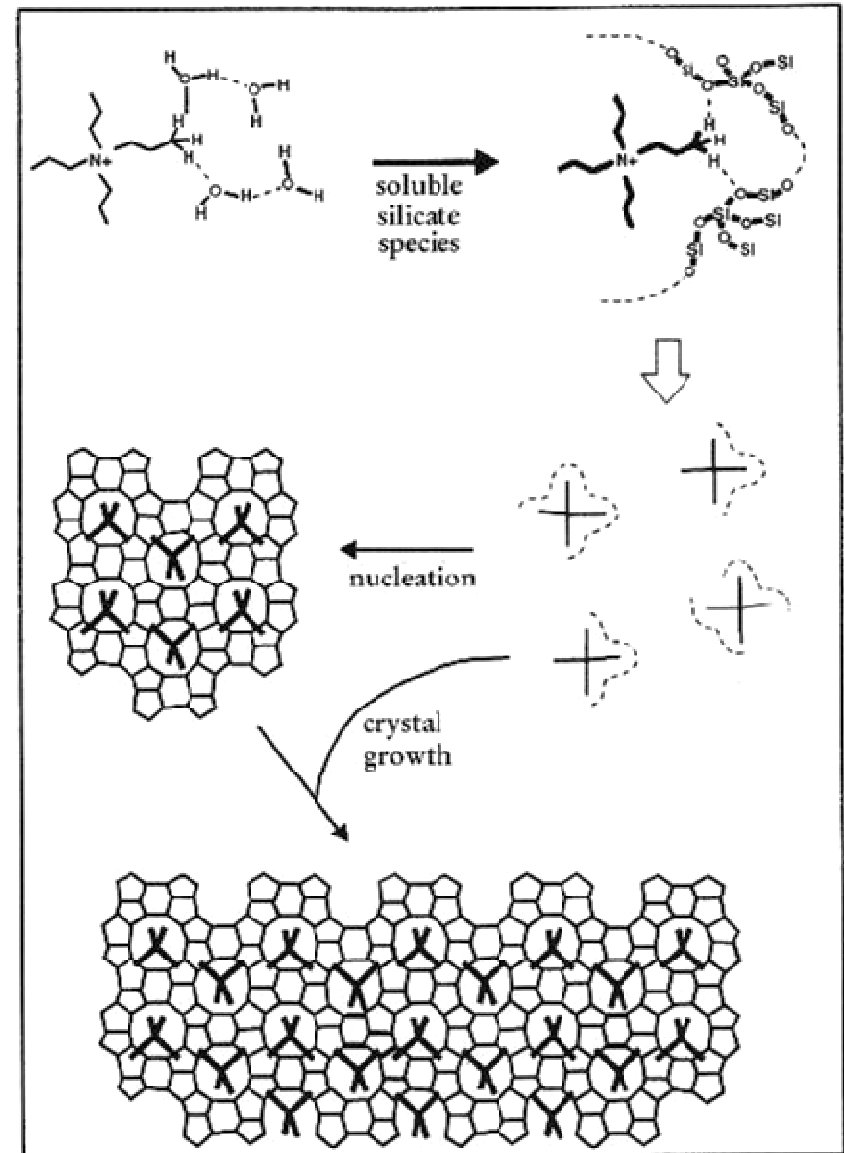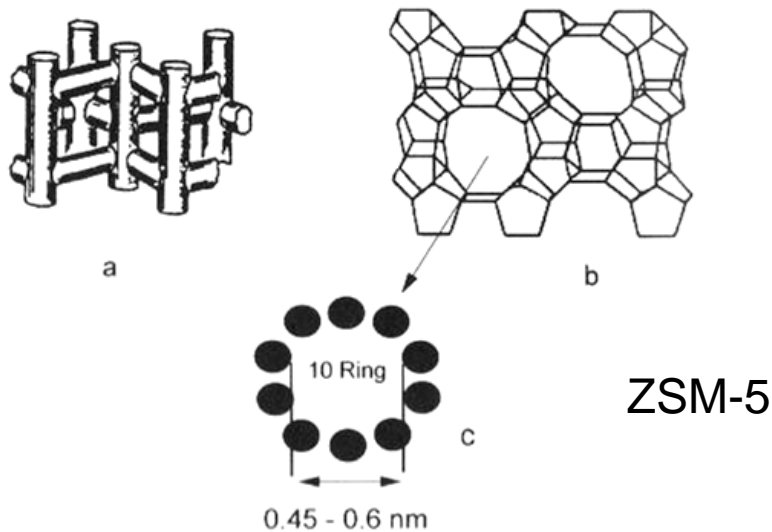

Summary

- Supported catalysts can be prepared by impregnation
 - The interaction of the support surface and the precursor species in solution is the key factor for a homogeneous distribution
- Co-precipitation may provide intimate porous mixtures of active and refractory components
 - Properties of the precipitate pre-determine the final catalyst's properties, complex processes
- Skeletal catalysts exhibit high metal surface areas
 - Leaching process parameters control porosity
- Hydrothermal synthesis yields crystalline porous framework materials
 - Template assisted synthesis can lead to ordered and well defined pore structure
- (Other important preparation methods for catalysts are deposition precipitation, sol-gel processes, chemical vapour deposition, mechano-chemical routes, solid state reactions, ...)

Literature & references (figures)

- Handbook of Heterogenous Catalysis, G. Ertl, H. Knözinger, F. Schüth, J. Weitkamp (ed.), Vol. 1, 2. Preparation of Catalysts, Wiley-VCH, Weinheim 2008
 - A. James Smith, M.S. Wainwright “Skeletal catalysts”, p. 92
 - F. Schüth, M. Hesse K. K. Unger “Precipitation and Coprecipitation”, p. 100
 - C.E.A. Kirschhock, E.J.P. Feijen, P.A. Jacobs, J.A. Martens “Hydrothermal zeolite synthesis”, p. 160
 - J. W. Geus, A.J. van Dillen “Preparation of supported catalysts by deposition precipitation”, p. 428
 - E. Marceau, X. Carrier, M. Che, O. Clause, C. Marcilly “Ion exchange and impregantion”, p. 467
- Synthesis of soild catalysts, K.P. de Jong (ed.), Wiley-VCH, Weinheim 2009
- Heterogeneous catalysts for the synthetic chemist, R.L. Augustine, Marcel Dekker, New York 1996
- Molecular Sieves – Synthesis, H.G. Karge, J. Weitkamp (ed.), Springer, Heidelberg 1998
 - R.W. Thompson “Recent advances in the understanding of zeolite synthesis”, p. 1
- Kurs “Chemische Nanotechnologie” Uni Saarbrücken