

Nanoscale Advances in Catalysis and Energy Applications

Yimin Li, and Gabor A. Somorjai*

Department of Chemistry and Lawrence Berkeley National Laboratory, University of California, Berkeley

ABSTRACT In this perspective, we present an overview of nanoscience applications in catalysis, energy conversion, and energy conservation technologies. We discuss how novel physical and chemical properties of nanomaterials can be applied and engineered to meet the advanced material requirements in the new generation of chemical and energy conversion devices. We highlight some of the latest advances in these nanotechnologies and provide an outlook at the major challenges for further developments.

KEYWORDS Nanotechnology, nanocatalysis, chemical conversion, energy conversion, energy conservation, nanomaterial synthesis

We just completed the second edition of the textbook, "Introduction to Surface Chemistry and Catalysis", 16 years later after the first edition.¹ It was an opportunity to take stock of the surface science and catalysis fields where the most significant developments occurred in recent years. Among the fields that experienced impressive advances, nanoscience and nanotechnology have been undergoing the most explosive growth. Nanotechnology refers to techniques capable of design, synthesis, and control of nanomaterials that offer advanced material properties for novel applications.

Among the fields that experienced impressive advances, nanoscience and nanotechnology have been undergoing the most explosive growth.

Nanomaterials were not totally unfamiliar within the various fields of surface science in the past. For example, heterogeneous catalysts in the form of nanosize transition metal particles dispersed onto microporous supports have been applied to chemical conversion technologies for many decades. The tremendous advances in modern nanotechnology are reflected in our expanded ability to design and control nanomaterials, their size, shape, chemi-

cal composition, and assembly structure for advanced applications.^{2–4}

This perspective discusses the technical foundation for nanoscience development: synthesis approaches and characterization techniques. We also discuss the latest advances in nanomaterial applications for heterogeneous catalysis, energy conversion, and energy conservation technologies.

Nanostructure Synthesis and Characterization. Well-controlled synthesis of nanomaterials and nanoscale characterization enables us to unambiguously correlate the structural properties with the physical, chemical, and biological properties of nanomaterials, which form the core of nanoscience research. A basic requirement for nanomaterial synthesis is the uniformity of the final product in size, shape, and chemical composition. Recently, many synthesis approaches have been developed to produce high quality nanoparticles, nanorods, nanowires, or other nanostructures using metals, semiconductors, and oxides.^{5–15} An example (Figure 1) is the shape- and size-controlled Pt nanoparticles synthesized by the colloid-chemistry-controlled approach.¹⁶ These nanoparticles can be readily deposited as films or dispersed into a mesoporous oxide support for studying size and shape dependence of catalytic properties.^{17,18}

Because of the high spatial and chemical resolution requirements, a combination of techniques is usually applied to characterize nanomaterials. Commonly used characterization techniques for nanomaterials are listed in Table 1. Many of them, which are indicated by asterisks in Table 1, have been developed and applied to characterize the properties of nanomaterials under working conditions and provide the molecular level knowledge for further performance optimizations.

Nanocatalysis. A catalyst is an entity that accelerates a chemical reaction without being consumed in the process. This ability is usually referred to as the activity of a cata-

* To whom correspondence should be addressed. E-mail: Somorjai@berkeley.edu.
Published on Web: 06/04/2010

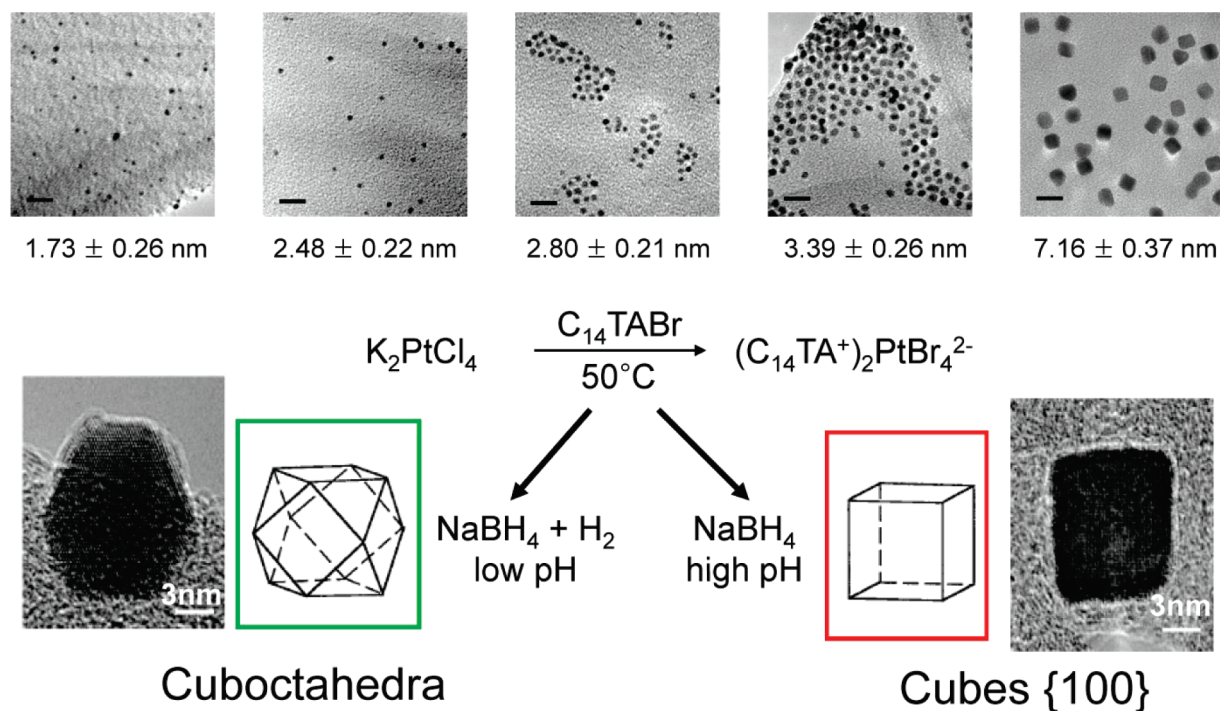


FIGURE 1. The size and shape-controlled Pt nanoparticles prepared by the colloid-chemistry-controlled method.

TABLE 1. Commonly Used Characterization Techniques for Nanomaterials

techniques	properties characterized
transmission electron microscopy* (TEM)	size, shape, and crystallinity
X-ray diffraction* (XRD)	crystal structure
UV-vis-nIR Spectroscopy*	light absorption and scattering
photoluminescence spectroscopy* (PL)	light emission
X-ray photoelectron spectroscopy* (XPS)	chemical composition
chemisorption, physisorption	surface area
scanning electron microscopy (SEM)	shape, and assembly structure
small angle X-ray scattering* (SAXS)	characteristic distances of partially ordered nanomaterials
energy dispersive X-ray analysis (EDX)	chemical composition
scanning tunneling microscopy* (STM)	shape, size, and surface structure
atomic force microscopy* (AFM)	shape, size, and work function
ultraviolet photoelectron spectroscopy (UPS)	electron valence band
X-ray emission spectroscopy* (XES)	electron band gap
near-edge X-ray absorption fine structure* (NEXAFS)	chemical composition
extended X-ray absorption fine structure* (EXAFS)	chemical composition and bonding environment

lyst. For a chemical reaction with multiple possible products, a catalyst may promote the production of one of the products, which is referred to as catalytic selectivity. Catalysis plays an important role in the technologies for transportation fuel production from fossil fuels or alternative energy resources, bulk chemical production, and pollution control, where efficient and selective chemical conversion processes are of great concern. The major goal for catalysis research in this century is to design new catalysts with desirable activity and higher selectivity to alleviate energy and process requirements for separation and purification using current technologies based on fossil raw materials, and to protect our environment by reducing the need for disposal of waste chemicals.¹⁹

Heterogeneous catalysts promote reactions at the active sites on their surfaces, so they are usually in the form

of nanoparticles with a large concentration of surface active sites. Advances in nanoscience provide opportunities for developing next-generation catalytic systems with high activities for energetically challenging reactions, high selectivity to valuable products, and extended life times.^{4,20} The development of next-generation nanocatalysts relies on surface science techniques that identify and characterize surface active sites at the atomic scale²¹ and synthesis approaches that are capable of producing stable surface active sites through controlling the size, shape, and chemical composition of nanocatalysts.

Highly-Active Nanocatalysts. The best example for demonstrating the exceptional catalytic activity of nanomaterials is a catalyst with gold nanoparticles in the 5 nm regime dispersed on a titania support. This catalyst exhibits high activities for hydrocarbon epoxidation and

CO oxidation at room temperatures.²² It has been suggested that the quantum confinement effects change the electronic structure of this noble metal and lead to the unusual catalytic activities observed.^{23,24} This discovery has spurred extensive research efforts in searching novel nanocatalysts for the important catalytic reactions with low reactivity, such as activation of saturated hydrocarbons in reforming reactions,^{25,26} oxygen reduction reactions in fuel cells,²⁷ and lingo-cellulose biomass hydrolysis.^{28–32} For example, it has been reported that small, charged metal clusters exhibit facile activation and dehydrogenation of methane molecules.^{33,34}

Highly-Selective Nanocatalysts. Highly selective catalysts may help reduce the energy consumption required for product separation and waste disposal processes in chemical industries. The development of alternative energy resources also relies on highly selective catalysts. The selective conversion of biomass-derived carbohydrates to liquid fuels and valuable chemicals is a key step in biomass conversion.^{35–39} Many molecular level factors affecting catalytic selectivity have been identified in our laboratory using surface science studies during the few last decades, which allow for nanotechnology to design and engineer highly selective catalysts.²¹

For a multiple-path catalytic reaction, the rate-determining steps for different products usually occur at different active sites on the catalyst surface. Consider a catalytic reaction involving a cyclic hydrocarbon reactant (Figure 2), the scission of the C–C bonds leads to the ring-opening product (product 1), while the dissociation of a C–H bond gives a dehydrogenation product (product 2). The ratio of product 1 to product 2 produced at a given surface site is controlled by the relative heights of the Gibbs free energy barriers for the two products. At the step sites on platinum surfaces, the scission of C–H bond occurs more readily than that of the C–C bond, which leads to a higher probability for forming the dehydrogenation product. At the kink sites, the breaking of the C–C bond becomes more facile and the increase of the ring-opening product is expected. From this simple picture, the selectivity of heterogeneous catalytic reactions is ultimately determined by the relative concentrations of active sites for different reaction pathways. For nanoparticle catalysts, the concentration of active sites is determined by the size and shape of the nanoparticles. Advances in nanoparticle synthesis enable the precise control of surface active sites by manufacturing monodisperse and shape-controlled catalysts. An example is shown in Figure 3, where the selectivity of pyrrole hydrogenation over Pt nanoparticles exhibits both size and shape dependence.^{40,41} The

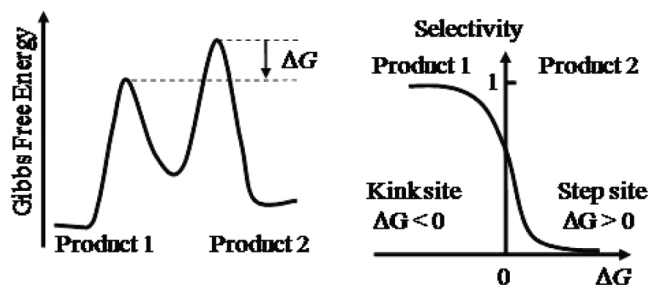
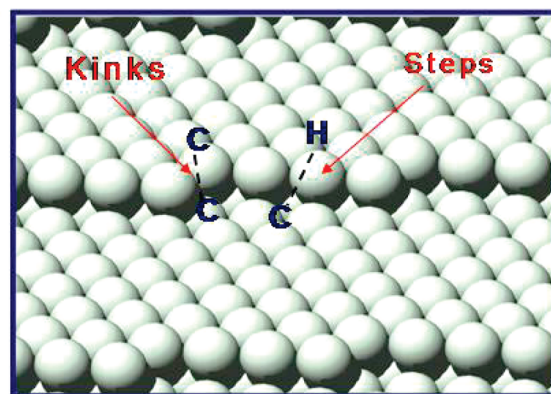


FIGURE 2. (Upper panel) The model-kinked Pt surface. The C–C bond and C–H bond are dissociated at the kink and step site, respectively. (Lower left panel) The schematic free energy potential surface for two-pathway reaction. Product 1 is formed by breaking the C–C bond, and Product 2 is formed by breaking the C–H bond. The activation barrier for Product 1 is lowered at the kink site, which leads to the difference in selectivity between the step and kink sites, as shown in the lower right panel.

selectivity change is induced by the surface structure change of the nanocatalysts with different sizes and shapes.

An important class of selective catalysts are bimetallic alloys that provide surface active sites with special atomic arrangements of metal components.⁴² Recently, this field has been revolutionized by the emergence of rational catalyst design at nanoscale.^{43,44} High-throughput, computer-based screening provides the elements and atomic arrangement of alloy candidates that may have optimal catalytic properties. Then, nanoalloys are synthesized and tested. The successful synthesis of alloy catalysts with intended composition relies on the fact that the size reduction of alloy particles usually results in the lowering of the immiscible gap.⁴⁵ Following this approach, a Ni₁Zn₅ alloy catalyst has been discovered with a higher selectivity for partial hydrogenation of acetylene.⁴⁶

In a more recent study, in situ X-ray photoelectron spectroscopy has been applied to monitor the surface segregation of bimetallic nanoparticles under reaction conditions.⁴⁷ It has been observed that the bimetallic composition on nanoparticle surfaces alternates upon switching the chemical gas environment between oxidizing and reducing conditions. This new insight may

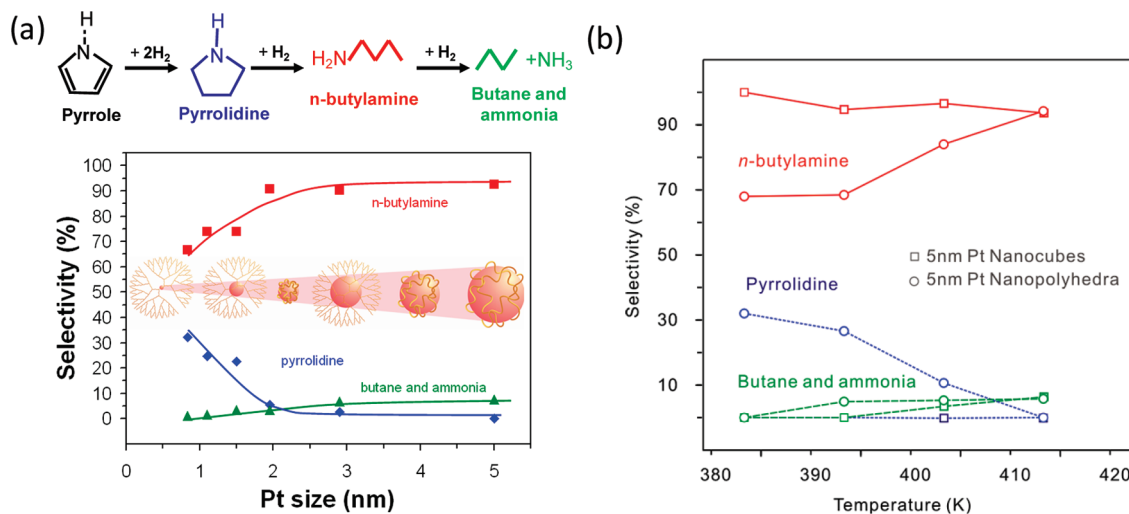


FIGURE 3. (a) The nanoparticle size dependence of the selectivity of pyrrole hydrogenation under the following reaction conditions: 4 Torr pyrrole, 400 Torr H₂, 413 K. Small nanoparticles exhibit high selectivity to pyrrolidine. (b) The nanoparticle shape dependence of the selectivity of pyrrole hydrogenation under the following conditions: 4 Torr pyrrole, 400 Torr H₂. At relatively lower temperatures, nanopolyhedra particles have a higher selectivity to pyrrolidine than nanocubes.

lead to the development of “smart” catalysts whose surface structure advantageously depends on the reaction environment.

Catalyst Support Nanomaterials. Catalyst supports are usually made of high-surface-area micro/mesoporous oxides or carbon nanomaterials. These support materials stabilize metal catalysts against sintering at high reaction temperatures. Some support materials, especially reducible oxides, can also promote the activity and selectivity of active metal catalysts. Many innovations have been made in designing nanostructured support materials. An example is the significant thermal stability enhancement of a core–shell catalyst in which the Pt nanoparticle is coated with a thin layer of mesoporous silica.⁴⁸ Another interesting example is using carbon nanotube-inorganic oxide hybrid nanoparticles as a support for phase-transfer reactions (reactants and products are in different phases) to simplify the separation and purification processes.^{35,49} These hybrid nanoparticles are amphiphilic and stabilize water–oil emulsions. The metal catalysts, immobilized on the hybrid support, preferentially stay at the water–oil interface, where catalytic phase-transfer reactions happen. The emulsions are extremely stable and can be easily separated from the biphasic liquid by a simple filtration. The recycled hybrid nanoparticles can be reused without any special treatment. It has been demonstrated that the hybrid materials can catalyze biphasic hydrodeoxygenation and aldol condensation reactions.

Nanotechnology in Energy Applications. At present, developing efficient and “clean” energy technologies is an urgent task and is crucial to the long-term energy and environmental security of our society.⁵⁰ Energy conversion and transport in nanomaterials differs significantly from that in bulk materials because of classical and quantum

size effects on energy carriers such as photons, phonons, electrons, and molecules. Nanoscience for energy applications is now focused on tailoring these nanoscale effects for efficient energy technologies such as photovoltaics, photochemical solar cells, thermoelectric, fuel cells, batteries, and so forth. For example, the efficient light absorption to generate charge carriers in a solid occurs at the scale of several hundreds of nanometers (wavelength of light). The mean free path of the excited charge carrier is much shorter than the wavelength of light. To achieve efficient photon absorption and collection of excited charge carriers in a photovoltaic device, an optimal design should be low-dimensional nanostructures, such as nanowires of semiconductors, in which at least one dimension is larger than the wavelength of light, and another dimension shorter than the mean free path of charge carriers.^{8,51}

Solar Energy Conversion. Solar energy is the most obvious “clean” and renewable alternative energy source (under ideal conditions, radiation power on a horizontal surface is 1000 W m⁻²).⁵² Photovoltaic cells convert the photon energy directly to electricity by separating the excited electron–hole pairs in photovoltaic materials. Photoelectrochemical cells use the excited electrons and holes to catalyze redox reactions, which may split water or CO₂ to generate fuels. Currently, photovoltaic and photoelectrochemical cells have not made a strong contribution to the energy supply because of their low conversion efficiencies.

i. Sunlight Harvesting. Nanostructured photovoltaic materials can significantly improve the efficiency of solar energy-based devices. To efficiently absorb sunlight over the entire spectrum range, several approaches, including embedding quantum dots⁵³ or quantum wells⁵⁴ into the

light absorption layer, using dye-sensitized semiconductor nanostructures^{55,56} and utilizing multiple exciton generation (MEG) observed in the semiconductor nanocrystallines,⁵⁷ have been proposed. MEG is one of the approaches promising extremely high efficiency to overcome the performance-cost issue. In the MEG process, absorption of a single photon produces multiple electron–hole pairs (excitons) and hence the internal quantum efficiency (IQE) for conversion photons into charge carriers may exceed 100%.⁵⁷ It was first suggested by Nozik that the efficiency of MEG might be enhanced in nanoscale semiconductor particles due to reduced rates of intraband relaxation and enhanced Coulomb interaction between electron–hole pairs.

ii. Charge Separation. Once electron–hole pairs form from an excited photon, they have a finite lifetime before recombination. To separate the electron and hole efficiently, various heterostructures consisting of nanomaterials such as thin films, nanowires,⁵¹ and dye-sensitized nanoparticles^{55,58} have been designed and synthesized. Dye-sensitized solar cells offer an inexpensive route to the development of highly efficient photovoltaic devices.⁵⁶ By attaching a sensitizer to semiconductor (such as TiO₂) nanoparticles, the photon-excited electrons in the dye sensitizer can be efficiently transferred onto the TiO₂ conduction band, which increases light-harvesting efficiency by reducing charge recombination.

iii. Chemical Fuel Production. There are several extra factors other than the light-to-charge conversion harvesting that limit the efficiency of photoelectrochemical (PEC) cells.^{59,60} A PEC cell is a photocatalytic system that catalyzes two redox reactions using photon-generated electron–hole pairs, one reacting with the holes at the surface of an anode and the second reacting with the electrons at the surface of a cathode. For the semiconductor-based PEC cells, the semiconductor must satisfy the following requirements: (1) The band gap of the semiconductor must be greater than the equilibrium potential difference between the two redox reactions. (2) The conduction band energy level must be higher than the potential of the redox reaction on the cathode and the valence band energy level must be lower than the potential of the redox reaction on the anode. (3) The surface area of the electrodes must be large enough to provide a high conversion rate, since the redox reactions occur on the surfaces.

There are two most valuable, but challenging, photocatalytic energy conversion processes currently under intensive research: the electrolysis of water to hydrogen and oxygen, and the conversion of carbon dioxide and water vapor into hydrocarbon fuels.^{61–63} Nanostructured electrodes provide large surface area for photocatalyzed reactions. By band engineering through

controlling the size, shape, chemical composition, and heterojunction of semiconductor materials, nanomaterials provide the opportunity to achieve high efficiencies for sunlight to charge conversion and chemical conversions at the electrode surfaces at the same time.^{51,64} It has been reported that the nanocomposite(Ga_{1-x}Zn_x)(N_{1-x}O_x) photocatalysts with Rh_{2-y}Cr_yO₃ as cocatalyst exhibits an apparent quantum efficiency for overall water splitting as high as 5.9% under a visible light of 420–440 nm.⁶⁵

Fuel Cells and Batteries. Fuel cells and batteries, such as polymeric-electrolyte-membrane fuel cells, solid-oxide fuel cells, and lithium batteries, are electrochemical systems for the energy conversion between chemical energy and electricity.^{66,67} They consist of an anode and a cathode, separated by an electrolyte. A pair of reduction and oxidation reactions on the electrode surfaces results in electric current generation. Applications of nanomaterials may significantly improve the efficiency of full cells and the energy storage density of batteries. One common factor limiting the efficiency of electrochemical systems is the ion conductivity of the electrolyte. In the literature, it is shown that ionic transport can be dramatically enhanced by using nanostructured composites. These phenomena, known as nanoionics effects, have been attributed to the fast ion transport in the space charge layer at the heterogeneous interface between an insulation material with high surface charge density and an ion conducting material.^{68,69} In a nanostructured composite, the reduction of the thickness of the space charge layer increases surface charge density, and the closely compacted structure also makes the nanoscale space charge zones connected to each other to provide ion transport pathways. For example, composites in which Lil is infiltrated in mesoporous Al₂O₃ may exhibit conductivities 100 times higher than that of pure Lil at room temperature.⁷⁰ This ion conductivity enhancement has also been observed in a nonaqueous liquid electrolyte after the addition of SiO₂ nanoparticles.⁷¹

The use of nanomaterials on the electrodes of electrochemical cells may enhance the charge storage capacity of barriers and the reaction rates of redox reactions in fuel cells.^{72,73} Nanostructured composites may have a very high charge storage capacity due to the nanoionics effect at interfaces.^{68,69} For example, nanostructured Li₂O/Ru composites show high Li⁺ storage capacity that is observed neither in pure Li₂O nor in pure Ru. For carbon-based electrodes, nanomaterials, such as carbon nanotubes, carbon nanohorns, and so forth, provide high surface area supports for metal catalysts and excellent conductivity for charge transport.^{74,75}

Nanotechnologies for Energy Conservation.

i. Thermoelectric Devices. Thermoelectric materials may efficiently convert waste heat generated by combustion engines to electricity, which improves the overall energy efficiency of engines. There are two required properties for a highly efficient thermoelectric material: (1) a high charge

carrier diffusion current under a temperature gradient in the material with minimized Joule heating, and (2) a low thermal conductivity so that a large temperature gradient can be attained in the material. For pure bulk materials, these two properties are difficult to optimize at the same time because the charge carrier, such as an electron, is also a thermal energy carrier. The increase of carrier density inevitably leads to an increase in the thermal conductivity. For many years, the energy efficiency of the pure bulk material based thermoelectric devices have remained at <5%, far below that of conventional thermal power generators.

Nanostructures and nanostructured materials hold the promise of more efficient thermoelectric energy conversion.⁷⁶ The basic idea comes from the observation of a disparity between the mean free path length of the dominant charge carrier and that of the thermal energy carrier, such as phonon in semiconductor materials. If the characteristic length of a nanomaterial is in between the two mean free path lengths, it may be possible to optimize one of the transport properties while leaving the other intact. The improvement of energy conversion efficiency has been demonstrated by several nanomaterials including the PbTe-based quantum dot superlattice system,⁷⁷ the Bi₂Te₃–Sb₂Te₂ two-dimensional superlattice system,⁷⁸ and the silicon nanowire systems.⁵¹ The enhanced efficiencies have been attributed to the impedance of the flow of heat by phonon scattering at the interfaces in these nanomaterials.

ii. Efficient Lighting Device. Lighting uses about 20% of the total electricity generated. Development of advanced lighting devices with high luminous efficiency will have significant impact on energy conservation.⁷⁹ In addition to high efficiency, a light source must be capable of rendering the true colors of an object, that is, the emitted light must cover a significant portion of the visible spectrum range. The light-emitting diode (LED) is one of the promising lighting sources currently under extensive research. The high efficiency and good rendering properties require that a semiconductor material used for LED applications have both high crystallinity and a tunable band gap.⁸⁰

As quantum dot size decreases, quantum confinement causes the band gap to increase and this leads to blue-shifted light emission.⁸¹ It has also been demonstrated that the composition of single-crystalline In_xGa_{1-x}N nanowires can be tuned across the entire compositional range from $x = 0$ to 1. The photoluminescence emission of these nanowires covers a wide spectrum range from near-ultraviolet to near-infrared.⁸² Because of the crystal quality and the tunable emission, semiconductor nanostructures have been actively investigated for the development of light emitting materials.

iii. Nanotribology. Friction is responsible for a large portion of energy wasted in modern machinery, such as

internal combustion and aircraft engines, gears, etc. Development of new lubrication materials is a major task for tribology, the science and technology of two interacting surfaces in relative motion.^{83–86} Conventional solid lubricants are thin films of graphite and the metal dichalcogenides MX₂ (where M is molybdenum or tungsten and X is sulfur or selenium). These materials are characterized by weak interatomic interactions between their layered structures, allowing low-strength shearing. Using these materials in a fullerene-like hollow nanoparticle form can further lower the friction and enhance the chemical inertness in humid environments.^{87,88} The hollow cage structure imparts elasticity and allows the particles to roll rather than to slide. The presence of the curved crystal surfaces prevents oxidation and preserves the layered structure inside the nanoparticles.

Outlook. The novel physical and chemical properties of nanomaterials promise many advanced applications in the development of new energy and chemical conversion technologies. In this perspective, we have discussed how nanomaterials can make significant contributions to the technologies in catalysis, solar energy harvesting, fuel cells and batteries, and energy conservation.

Accompanying these exciting opportunities, there are also major challenges before promising nanotechnologies eventually replace conventional technologies. In nanocatalysis, achieving 100% selectivity, as seen in enzyme catalytic reactions, is still a challenging task. In several other fields, such as photoelectrochemical cells for water and CO₂ splitting, and thermoelectric devices, the low efficiency of nanodevices is of major concern at present. One of the major challenges in many nanotechnology applications is the development of large-scale and well-controlled synthesis and assembly approaches for manufacturing complex and durable nanostructures. All these challenges call for an atomic level understanding of physical and chemical processes within nanostructures.

One of the major challenges in many nanotechnology applications is the development of large-scale and well-controlled synthesis and assembly approaches for manufacturing complex and durable nanostructures.

It is of great importance to develop in situ experimental techniques for characterizing nanomaterials under working conditions. For example, transmission electron microscopy⁸⁹ and X-ray absorption spectroscopy⁹⁰ can monitor the growth of nanoparticles in solutions. The understanding of nanoparticle growth mechanisms may lead to large-scale and well-controlled nanoparticle synthesis processes.^{91,92} Techniques, such as X-ray photoelectron spectroscopy, sum-frequency generation vibrational spectroscopy, and scanning tunneling microscopy, can be applied to identify active sites on catalyst surfaces and to study the deactivation of active sites under reaction conditions.²¹ This acquired knowledge is crucial for designing new nanocatalysts with high activity, high selectivity, and extended catalytic lifetime.

Because of device complexity in nanotechnologies, theoretical modeling is now playing an increasingly important role in device design. A good theory may help with understanding and predicting new properties associated with nanomaterials. Multiscale device modeling can estimate the theoretical limit on the efficiency of each component and identify the overall efficiency limiting factors. Rational design that combines theoretical modeling with advanced experimental techniques will significantly shorten the R&D cycle of new nanotechnologies.

Acknowledgment. This work was supported by the Director, Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231.

REFERENCES AND NOTES

- Somorjai, G. A.; Li, Y. *Introduction to Surface Chemistry and Catalysis*; John Wiley & Sons, Inc.: Hoboken, NJ, 2010.
- Linkov, I. *Nanomaterials*; Springer: New York, 2008.
- Vollath, D. *Nanomaterials: an introduction to synthesis, properties and application*; Wiley-VCH: Weinheim, 2008.
- Somorjai, G. A.; Tao, F.; Park, J. Y. *Top. Catal.* **2008**, *47*, 1.
- Terrones, M. *Ann. Rev. Mater. Res.* **2003**, *33*, 419.
- Zhao, D. Y.; et al. *Curr. Opin. Solid State Mater. Sci.* **1998**, *3*, 111.
- Murray, C. B.; Kagan, C. R.; Bawendi, M. G. *Annu. Rev. Mater. Sci.* **2000**, *30*, 545.
- Xia, Y. N.; et al. *Adv. Mater.* **2003**, *15*, 353.
- Law, M.; Goldberger, J.; Yang, P. D. *Annu. Rev. Mater. Res.* **2004**, *34*, 83.
- Yin, Y. D.; et al. *Science* **2004**, *304*, 711.
- Rioux, R. M.; et al. *J. Phys. Chem. B* **2005**, *109*, 2192.
- Yin, Y.; Alivisatos, A. P. *Nature* **2005**, *437*, 664.
- Zhang, Y. W.; et al. *J. Phys. Chem. C* **2007**, *111*, 12243.
- Huang, W.; et al. *Nano Lett.* **2008**, *8*, 2027.
- Somorjai, G. A.; Park, J. Y. *Top. Catal.* **2008**, *49*, 126.
- Grass, M. E.; et al. *J. Phys. Chem. C* **2008**, *112*, 4797.
- Rioux, R. M.; et al. *Top. Catal.* **2006**, *59*, 167.
- Grass, M. E.; et al. *J. Phys. Chem. C* **2009**, *113*, 8616.
- Somorjai, G. A.; Park, J. Y. *Angew. Chem., Int. Ed.* **2008**, *47*, 9212.
- Heiz, U.; Landman, U. *Nanocatalysis*; Springer, Berlin: New York, 2007.
- Somorjai, G. A.; Kliewer, C. J. *React. Kinet. Catal. Lett.* **2009**, *96*, 191.
- Bond, G. C.; Thompson, D. T. *Catal. Rev.—Sci. Eng.* **1999**, *41*, 319.
- Bell, A. T. *Science* **2003**, *299*, 1688.
- Harding, C.; et al. *J. Am. Chem. Soc.* **2009**, *131*, 538.
- Wei, J. M.; Iglesia, E. *Angew. Chem., Int. Ed.* **2004**, *43*, 3685.
- Zhang, J.; et al. *Science* **2008**, *322*, 73.
- Centi, G.; Perathoner, S. *Eur. J. Inorg. Chem.* **2009**, *26*, 3851.
- Zhao, H. B.; et al. *Science* **2007**, *316*, 1597.
- Rinaldi, R.; Palkovits, R.; Schuth, F. *Angew. Chem., Int. Ed.* **2008**, *47*, 8047.
- Hara, M. *Energy Environ. Sci.* **2010**, *3*, 601.
- Onda, A.; Ochi, T.; Yanagisawa, K. *Green Chem.* **2008**, *10*, 1033.
- Yan, N.; et al. *J. Am. Chem. Soc.* **2006**, *128*, 8714.
- Koszinowski, K.; Schroder, D.; Schwarz, H. *J. Phys. Chem. A* **2003**, *107*, 4999.
- Lang, S. M.; et al. *Angew. Chem., Int. Ed.* **2010**, *49*, 980.
- Crossley, S.; et al. *Science* **2010**, *327*, 68.
- Carlini, C.; et al. *Appl. Catal., A* **2005**, *289*, 197.
- Budroni, G.; Corma, A. *J. Catal.* **2008**, *257*, 403.
- Casanova, O.; Iborra, S.; Corma, A. *ChemSusChem* **2009**, *2*, 1138.
- Bianchi, C. L.; et al. *Catal. Today* **2005**, *102*, 205.
- Kuhn, J. N.; et al. *J. Am. Chem. Soc.* **2008**, *130*, 14026.
- Tsung, C. K.; et al. *J. Am. Chem. Soc.* **2009**, *131*, 5816.
- Sinfelt, J. H. *Surf. Sci.* **2002**, *500*, 923.
- Norskov, J. K.; et al. *Chem. Soc. Rev.* **2008**, *37*, 2163.
- Norskov, J. K.; et al. *Nature Chem.* **2009**, *1*, 37.
- Sinfelt, J. H.; Via, G. H.; Lytle, F. W. *Catal. Rev.—Sci. Eng.* **1984**, *26*, 81.
- Studt, F.; et al. *Science* **2008**, *320*, 1320.
- Tao, F.; et al. *Science* **2008**, *322*, 932.
- Joo, S. H.; et al. *Nat. Mater.* **2009**, *8*, 126.
- Shen, M.; Resasco, D. E. *Langmuir* **2009**, *25*, 10843.
- Dresselhaus, M. S.; Thomas, I. L. *Nature* **2001**, *414*, 332.
- Hochbaum, A. I.; Yang, P. D. *Chem. Rev.* **2010**, *110*, 527.
- Kamat, P. V. *J. Phys. Chem. C* **2007**, *111*, 2834.
- Park, S.; et al. *Sol. Energy Mater. Sol. Cells* **2009**, *93*, 684.
- Paxman, M.; et al. *J. Appl. Phys.* **1993**, *74*, 614.
- Yum, J. H.; et al. *ChemSusChem* **2008**, *1*, 699.
- Hardin, B. E.; et al. *Nat. Photonics* **2009**, *3*, 406.
- Nozik, A. J. *Chem. Phys. Lett.* **2008**, *457*, 3.
- Gratzel, M. *Inorg. Chem.* **2005**, *44*, 6841.
- Gratzel, M. *Nature* **2001**, *414*, 338.
- Bak, T.; et al. *Int. J. Hydrogen Energy* **2002**, *27*, 991.
- Ni, M.; et al. *Renewable Sustainable Energy Rev.* **2007**, *11*, 401.
- Centi, G.; Perathoner, S. *ChemSusChem* **2010**, *3*, 195.
- Roy, S. C.; et al. *ACS Nano* **2010**, *4*, 1259.
- Hisatomi, T.; et al. *J. Phys. Chem. C* **2009**, *113*, 21458.
- Maeda, K.; Teramura, K.; Domen, K. *J. Catal.* **2008**, *254*, 198.
- Steele, B. C. H.; Heinzel, A. *Nature* **2001**, *414*, 345.
- Winter, M.; Brodd, R. J. *Chem. Rev.* **2004**, *104*, 4245.
- Maier, J. *Nat. Mater.* **2005**, *4*, 805.
- Maier, J. *Phys. Chem. Chem. Phys.* **2009**, *11*, 3011.
- Maekawa, H.; et al. *Solid State Ionics* **2004**, *175*, 281.
- Aurbach, D. *J. Power Sources* **2000**, *89*, 206.
- Salitra, G.; et al. *J. Electrochem. Soc.* **2000**, *147*, 2486.
- Wang, Y.; Cao, G. Z. *Adv. Mater.* **2008**, *20*, 2251.
- McCreery, R. L. *Chem. Rev.* **2008**, *108*, 2646.
- Centi, G.; Perathoner, S. *Catal. Today* **2010**, *150*, 151.
- Venkatasubramanian, R. *Nature* **2010**, *463*, 619.
- Harman, T. C.; et al. *Science* **2002**, *297*, 2229.
- Venkatasubramanian, R.; et al. *Nature* **2001**, *413*, 597.
- Bergh, A.; et al. *Phys. Today* **2001**, *54*, 42.
- Schubert, E. F.; Kim, J. K. *Science* **2005**, *308*, 1274.
- Alivisatos, A. P. *J. Phys. Chem.* **1996**, *100*, 13226.
- Kuykendall, T.; et al. *Nat. Mater.* **2007**, *6*, 951.
- Bhushan, B. *Tribology: Friction, Wear, and Lubrication. In The Engineering Handbook*; Dorf, R. C., Ed.; CRC Press LLC: Boca Raton, FL, 2000.
- Bhushan, B. *Philos. Trans. R. Soc. London, Ser. A* **2008**, *366*, 1499.
- Bhushan, B. *J. Phys.: Condens. Matter* **2008**, *20*.
- Bhushan, B.; Israelachvili, J. N.; Landman, U. *Nature* **1995**, *374*, 607.
- Rapoport, L.; et al. *Nature* **1997**, *387*, 791.
- Chhowalla, M.; Amaratunga, G. A. J. *Nature* **2000**, *407*, 164.
- Zheng, H. M.; et al. *Science* **2009**, *324*, 1309.
- Polte, J.; et al. *ACS Nano* **2010**, *4*, 1076.
- Finney, E. E.; Finke, R. G. J. *Colloid Interface Sci.* **2008**, *317*, 351.
- Murray, C. B. *Science* **2009**, *324*, 1276.